



Fundamentals and Applications of FLAPW Method: HiLAPW Code

Tamio Oguchi

Institute of Scientific and Industrial Research
Osaka University



CMD Workshop





FLAPW Method

- The **FLAPW** is among the most precise and efficient first-principles methods which are able to solve density-functional-theory Kohn-Sham equations with the periodic boundary conditions.
- **FLAPW =**
Full-potential Linearized Augmented Plane Wave
- A great number of applications to a variety of solid systems



1. OUTLINE

- **Fundamentals of FLAPW Method**
 - One-electron equations and Bloch function
 - Augmented Plane Wave method
 - Linear method
 - Full-potential method
- **FLAPW Codes**
 - Packages open to public
 - HiLAPW code and some applications



2. OUTLINE

- Practical Aspects of FLAPW Methods
 - First-Principles Calculation – Kohn-Sham Eqs.
 - Crystal Structure and Atomic Position
 - Lattice – Primitive Translation Vector
 - Space Group
 - Reciprocal Lattice – Brillouin Zone
 - k-point Integration
 - Eigenvalue Problem
 - Self-Consistent Field
 - Mixing of Electron Density



Kohn-Sham Equations

$$\mathcal{H}\psi_j(\mathbf{r}) = \left[-\frac{\hbar^2}{2m} \nabla^2 + v_{\text{eff}}(\mathbf{r}) \right] \psi_j(\mathbf{r}) = \varepsilon_j \psi_j(\mathbf{r})$$

$$n(\mathbf{r}) = \sum_j |\psi_j(\mathbf{r})|^2$$

$$v_{\text{eff}}(\mathbf{r}) = v_{\text{ext}}(\mathbf{r}) + e^2 \int \frac{n(\mathbf{r}')}{|\mathbf{r} - \mathbf{r}'|} d\mathbf{r}' + \mu_{\text{xc}}(n(\mathbf{r}))$$

- ★ One-electron Kohn-Sham equations are given within the local density approximation (generalized gradient approximation) to the density functional theory.



Band Theory

How to solve the one-electron equations for particular condensed-matter systems

Periodic system → Band theory


Bloch Theorem

- A quantum-mechanical state in a periodic system can be specified with a wave number \mathbf{k}

$$\mathcal{H}\psi_j^{\mathbf{k}}(\mathbf{r}) = \varepsilon_j^{\mathbf{k}}\psi_j^{\mathbf{k}}(\mathbf{r})$$

Dispersion relation: band structure


Brillouin Zone and Bands

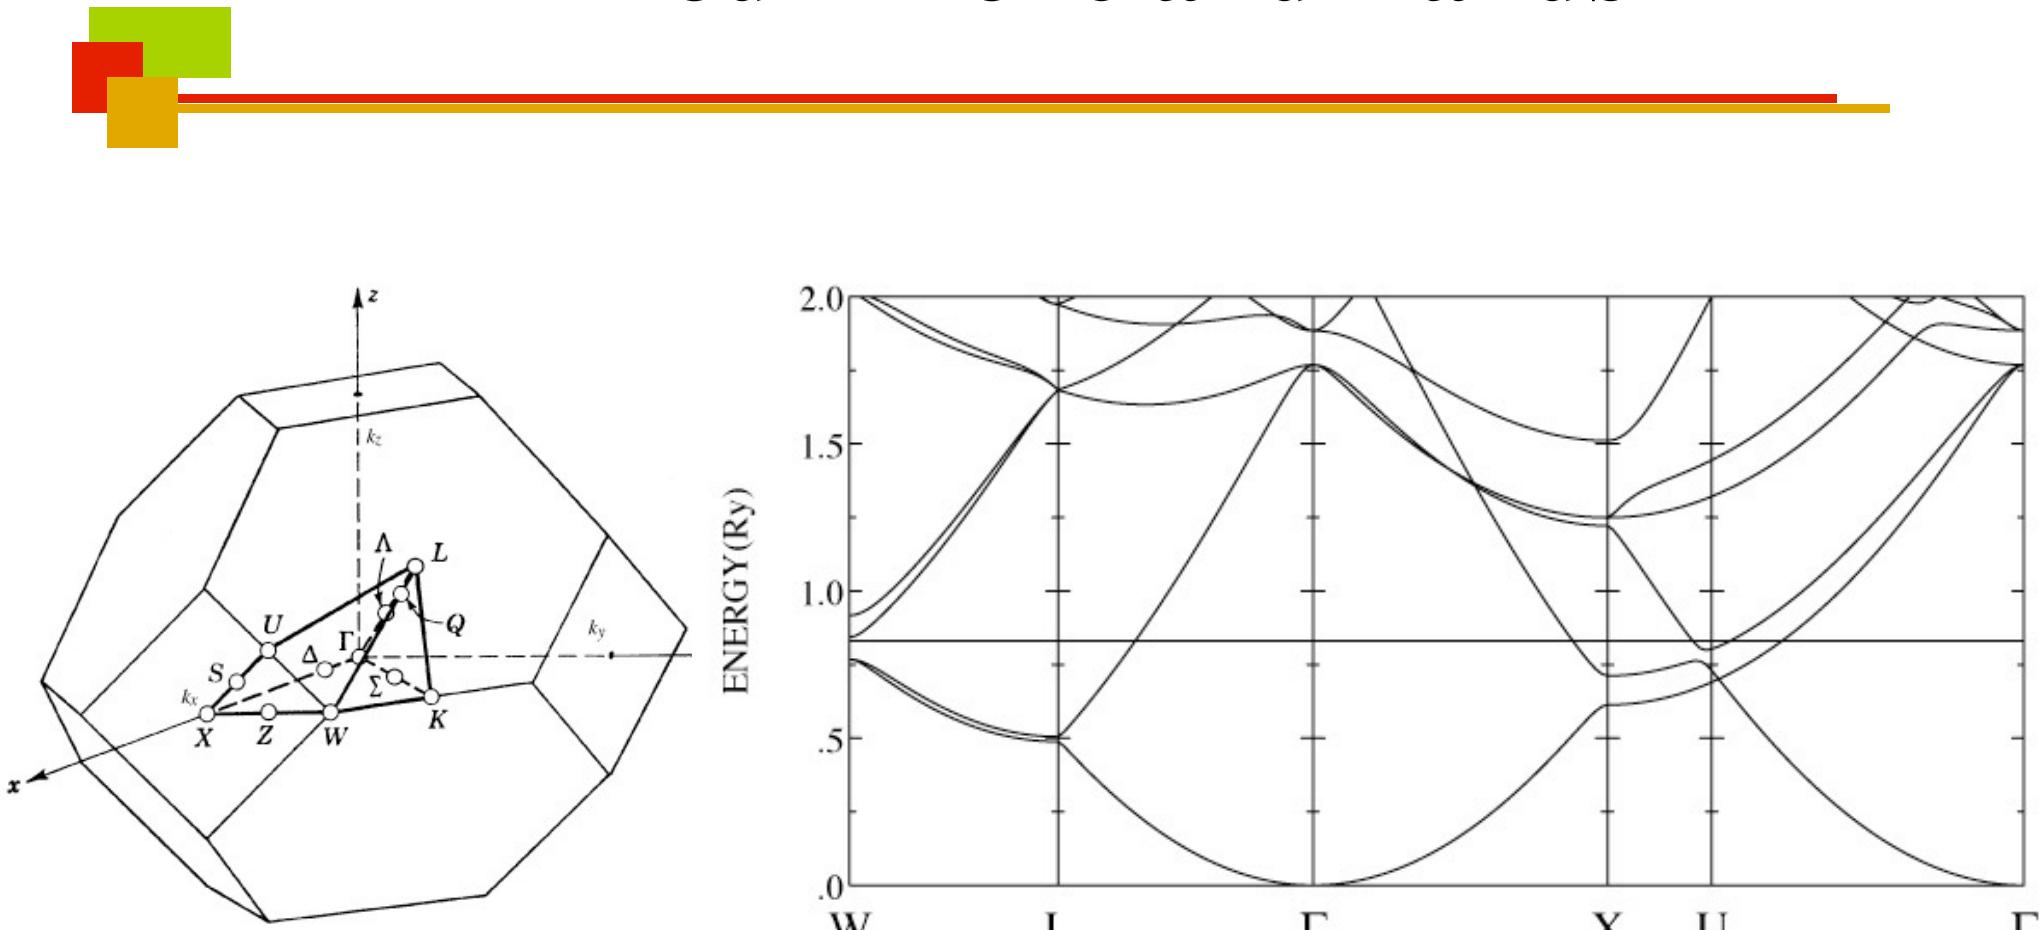

BZ of fcc lattice

Band structure of fcc Al

independent quantum number



Bloch Function

$$\psi_j^{\mathbf{k}}(\mathbf{r} + \mathbf{R}) = e^{i\mathbf{k}\cdot\mathbf{R}}\psi_j^{\mathbf{k}}(\mathbf{r}) : \text{Bloch theorem}$$

$$\psi_j^{\mathbf{k}}(\mathbf{r}) = e^{i\mathbf{k}\cdot\mathbf{r}}u_j^{\mathbf{k}}(\mathbf{r})$$

$$u_j^{\mathbf{k}}(\mathbf{r} + \mathbf{R}) = u_j^{\mathbf{k}}(\mathbf{r}) : \text{periodic function}$$

↓
represented in a
Fourier form

$$\begin{aligned}\psi_j^{\mathbf{k}}(\mathbf{r}) &= e^{i\mathbf{k}\cdot\mathbf{r}} \sum_{\mathbf{K}} a_{j,\mathbf{K}}^{\mathbf{k}} e^{i\mathbf{K}\cdot\mathbf{r}} \\ &= \sum_{\mathbf{K}} a_{j,\mathbf{K}}^{\mathbf{k}} e^{i(\mathbf{k}+\mathbf{K})\cdot\mathbf{r}}\end{aligned}$$


K: reciprocal lattice vector



Bloch Function

- Normalized in a macroscopic volume Ω
- k points in BZ are independent and sufficient

$$\psi_j^{\mathbf{k}}(\mathbf{r}) = \frac{1}{\sqrt{\Omega}} \sum_{\mathbf{K}} a_j^{\mathbf{k}+\mathbf{K}} e^{i(\mathbf{k}+\mathbf{K}) \cdot \mathbf{r}}$$



$$\mathcal{H}\psi_j^{\mathbf{k}}(\mathbf{r}) = \varepsilon_j^{\mathbf{k}} \psi_j^{\mathbf{k}}(\mathbf{r})$$




Secular Equation

$$\sum_{\mathbf{K}} \langle \mathbf{k} + \mathbf{K}' | \mathcal{H} - \varepsilon_j^{\mathbf{k}} | \mathbf{k} + \mathbf{K} \rangle a_j^{\mathbf{k}+\mathbf{K}} = 0$$

Matrix elements


$$\langle \mathbf{k} + \mathbf{K}' | \mathcal{H} | \mathbf{k} + \mathbf{K} \rangle = \frac{\hbar^2}{2m} |\mathbf{k} + \mathbf{K}|^2 \delta_{\mathbf{K}', \mathbf{K}} + V(\mathbf{K}' - \mathbf{K})$$

$$V(\mathbf{K}' - \mathbf{K}) = \frac{1}{\Omega} \int d\mathbf{r} e^{-i(\mathbf{K}' - \mathbf{K}) \cdot \mathbf{r}} v(\mathbf{r})$$




Fourier Transform of Potential

$$V(\mathbf{K}' - \mathbf{K}) = \frac{1}{\Omega} \int d\mathbf{r} e^{-i(\mathbf{K}' - \mathbf{K}) \cdot \mathbf{r}} v(\mathbf{r})$$

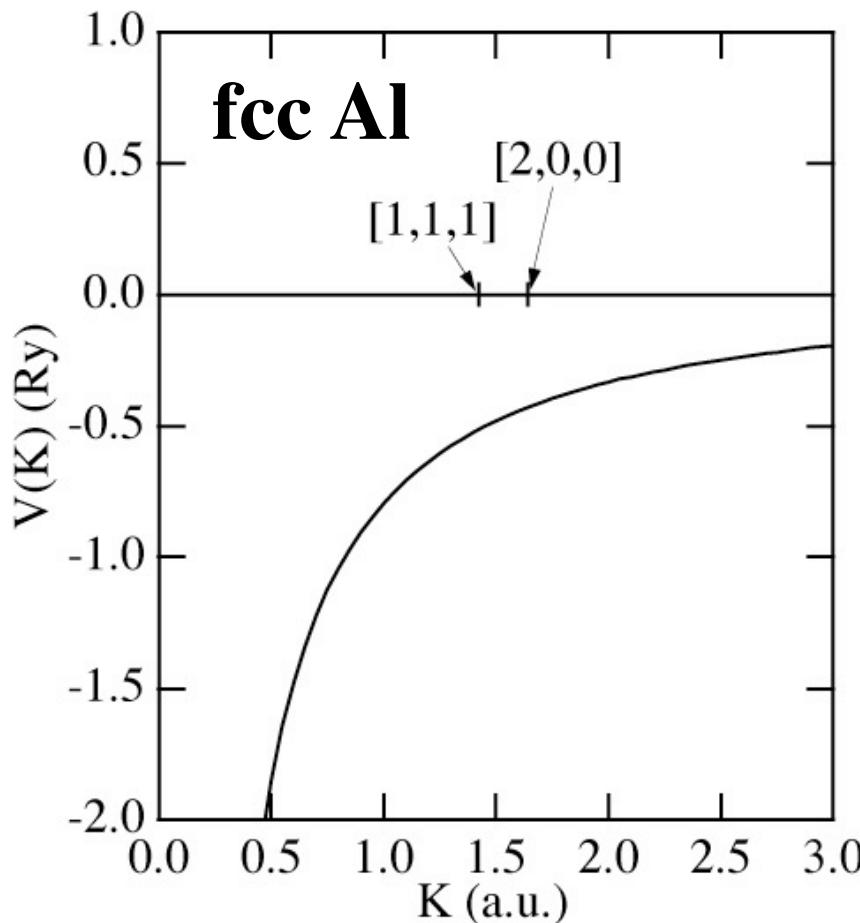

$$v(\mathbf{r}) \approx \sum_{\mathbf{R}} v_{\text{atom}}(|\mathbf{r} - \mathbf{R}|)$$


**Very slow convergency of FT
due to Coulombic behavior
requires a large number of
K vectors.**



Orthogonalization to Core Functions

$$\langle \mathbf{k} + \mathbf{K} | \phi_{\text{core}} \rangle = \frac{1}{\Omega} \int d\mathbf{r} e^{-i(\mathbf{k}+\mathbf{K}) \cdot \mathbf{r}} \phi_{\text{core}}(\mathbf{r})$$


Very slow convergency of the core functions because of localized nature.




How to Solve the Problems

1. Contributions from core (nucleus and core electron potentials, and orthogonality to core electron states) are replaced by a soft (easily Fourier transformed) potential.
→ **pseudopotential**
2. PW basis functions are augmented with localized functions.
→ **augmented basis**
3. Green's functions are used as a multiple scattering problem.
→ **Korringa-Kohn-Rostoker method**

Muffin-tin Potential Approximation




Crystal Potential

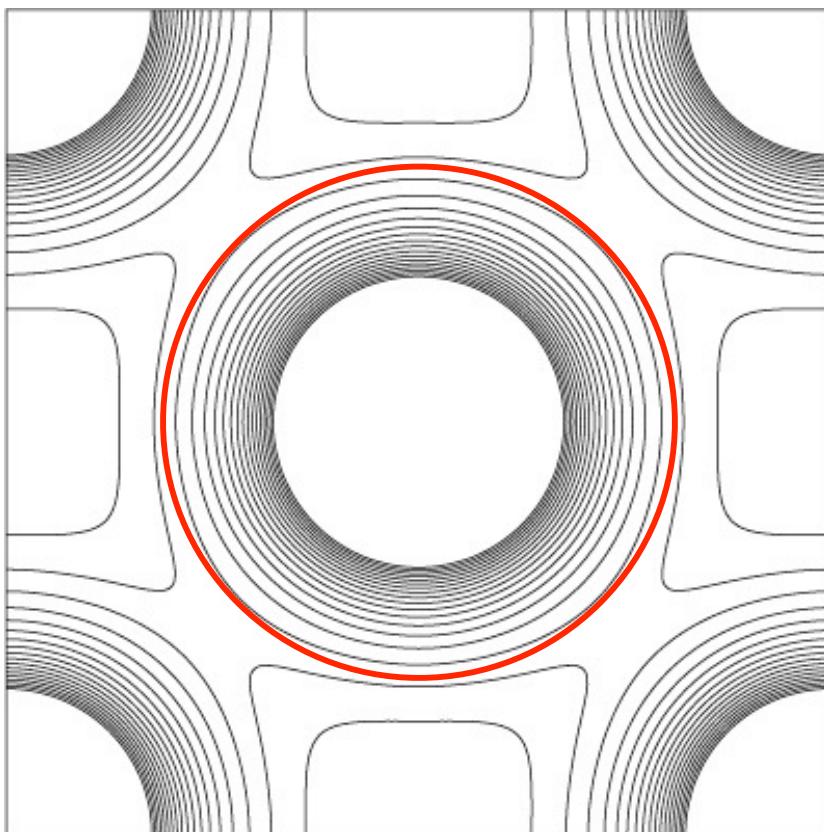

FCC Cu


- Spherical around atoms
- Constant in the interstitial

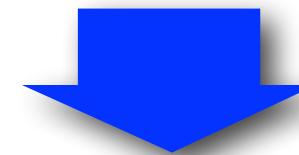

$$v(\mathbf{r}) = \begin{cases} v(|\mathbf{r} - \mathbf{R}|) & |\mathbf{r} - \mathbf{R}| \in S \\ v_{MTZ} & |\mathbf{r} - \mathbf{R}| \not\in S \end{cases}$$

Slater's Idea

Phys. Rev. 51(1937)846.



Plane waves

$$|\mathbf{r} - \mathbf{R}| \ni S$$

$$\phi^{\mathbf{k}+\mathbf{K}}(\mathbf{r}) = \frac{1}{\sqrt{\Omega}} e^{i(\mathbf{k}+\mathbf{K}) \cdot \mathbf{r}}$$

Augmentation waves


$$|\mathbf{r} - \mathbf{R}| \in S$$

$$\phi^{\mathbf{k}+\mathbf{K}}(\mathbf{r}) = \frac{1}{\sqrt{\Omega}} \sum_{lm} i^l a_{lm}^{\mathbf{k}+\mathbf{K}} R_l(|\mathbf{r} - \mathbf{R}|; E) Y_{lm}(\mathbf{r} - \mathbf{R})$$

$R_l(r; E)$: radial function for energy E

$Y_{lm}(\mathbf{r})$: spherical harmonics

Augmented Plane Wave




Secular Equation

$$\det ||\langle \mathbf{k} + \mathbf{K}' | \mathcal{H} - E | \mathbf{k} + \mathbf{K} \rangle|| = 0$$

$$\begin{aligned} \langle \mathbf{k} + \mathbf{K}' | \mathcal{H} - E | \mathbf{k} + \mathbf{K} \rangle &= \left\{ \frac{\hbar^2}{2m} |\mathbf{k} + \mathbf{K}|^2 - E \right\} \delta_{\mathbf{K}', \mathbf{K}} \\ &\quad + \Gamma_{\mathbf{K}', \mathbf{K}}^{\text{APW}}(E) \end{aligned}$$


Matrix elements have non-linear energy dependence due to logarithmic derivatives of the radial functions.

Problems in APW Method



1. Energy dependence of the matrix elements $\Gamma_{\mathbf{K}', \mathbf{K}}^{\text{APW}}(E)$ requires searching poles of the determinants
→ Linear Method by Andersen (1975) and
Koelling-Arbman (1975)
LAPW
2. Muffin-tin potential approximation doesn't work for less-packing or low-symmetry systems
→ Full-potential Method by Weinert (1981)
FLAPW

Linear Method



O.K. Andersen, PRB 12(1975)3060.

D.D. Koelling and G.O. Arbman, JPF 5(1975)2041.

- Remove the energy dependence of radial functions
using Tayler expansion

$$R_l(r; E) \approx R_l(r; E_0) + (E - E_0) \dot{R}_l(r; E_0) + \dots$$
$$\dot{R}_l(r; E_0) = \left. \frac{d}{dE} R_l(r; E) \right|_{E=E_0}$$

- Use radial function at E_0 and its energy derivative to represent a radial function with any logarithmic derivative


$$R_l(r; D) = R_l(r; E_0) + \omega(D) \dot{R}_l(r; E_0)$$

Linear Method



- APW → LAPW
- KKR → MTO → LMTO
 - KKR:** Korringa-Kohn-Rostoker
 - MTO:** Muffin-Tin Orbital
 - LMTO:** Linear Muffin-Tin Orbital

LAPW Method



Augmentation basis

$$\phi^{\mathbf{k}+\mathbf{K}}(\mathbf{r}) = \frac{1}{\sqrt{\Omega}} \sum_{lm} i^l \phi_{lm}^{\mathbf{k}+\mathbf{K}}(|\mathbf{r} - \mathbf{R}|) Y_{lm}(\mathbf{r} - \mathbf{R})$$

$$\phi_{lm}^{\mathbf{k}+\mathbf{K}}(r) = A_{lm}^{\mathbf{k}+\mathbf{K}} R_l(r; E_l) + B_{lm}^{\mathbf{k}+\mathbf{K}} \dot{R}_l(r; E_l)$$

$\begin{cases} A_{lm}^{\mathbf{k}+\mathbf{K}} \\ B_{lm}^{\mathbf{k}+\mathbf{K}} \end{cases}$ **determined from the boundary conditions**

E_l **energy parameter usually taken at the center of the occupied partial band**

Why the Linear Method Works Well?



Orthogonality to maximize the variational degree


$$\int_0^S R_l(r; E_l) \dot{R}_l(r; E_l) r^2 dr = 0$$

Orthogonality to the core functions

$$\int_0^S R_l(r; E_l) R_{\text{core}}(r; E_{\text{core}}) r^2 dr = 0$$

$$\int_0^S \dot{R}_l(r; E_l) R_{\text{core}}(r; E_{\text{core}}) r^2 dr = 0$$


Why the Linear Method Works Well?




Energy expectation value of the orbital with the exact logarithmic derivative

$$\langle E(D) \rangle = \frac{\langle \phi_l(D) | \mathcal{H} | \phi_l(D) \rangle_S}{\langle \phi_l(D) | \phi_l(D) \rangle_S}$$

$$= E + \mathcal{O}(E - E_l)^4$$

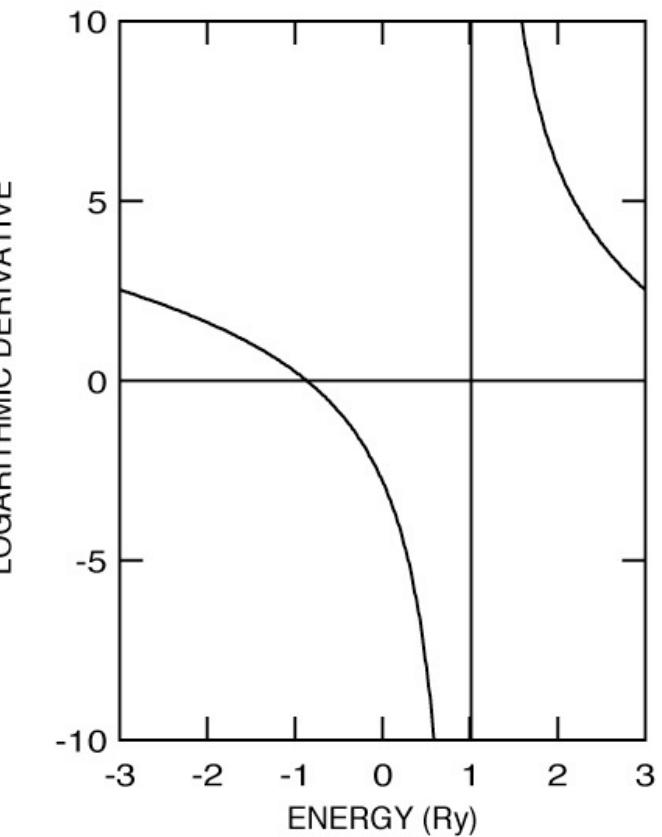

Coulomb Potential




- Coulomb potential for smooth density distribution


$$n(\mathbf{r}) = \sum_{\mathbf{G}} e^{i\mathbf{G} \cdot \mathbf{r}} n_{\mathbf{G}} \quad \nabla^2 v^C(\mathbf{r}) = 4\pi e^2 n(\mathbf{r})$$

$$v^C(\mathbf{r}) = \sum_{\mathbf{G}} e^{i\mathbf{G} \cdot \mathbf{r}} v_{\mathbf{G}}^C \quad v_{\mathbf{G}}^C = \frac{4\pi e^2 n_{\mathbf{G}}}{G^2}$$

- Realistic distribution

$$n_{\mathbf{G}} = \frac{1}{\Omega} \int e^{-i\mathbf{G} \cdot \mathbf{r}} n(\mathbf{r}) d\mathbf{r}$$

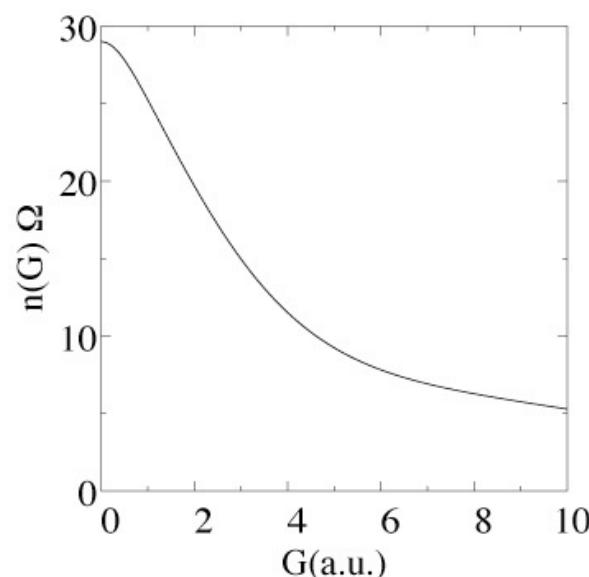



Full Potential Method


M. Weinert, J. Math. Phys. **22** (1981) 2433.

- Electron density inside the sphere is replaced by a smoothed density with the exact multipole moments.

$$n(\mathbf{r}) = \begin{cases} \tilde{n}(\mathbf{r}) & |\mathbf{r} - \mathbf{R}| \in S \\ n(\mathbf{r}) & |\mathbf{r} - \mathbf{R}| \ni S \end{cases}$$

- Potential outside the sphere is given with the smoothed density.
- Potential inside the sphere can be solved with the sphere boundary conditions.

Full Potential Method



- **Electron density inside the sphere**

$$n(\mathbf{r}) = \sum_{lm} n_{lm}(r) Y_{lm}(\mathbf{r})$$

- **Potential function inside the sphere**


$$v(\mathbf{r}) = \sum_{lm} v_{lm}(r) Y_{lm}(\mathbf{r})$$

- **Matrix element of potential**


$$\Delta H_{\mathbf{K}', \mathbf{K}} = \langle \mathbf{k} + \mathbf{K}' | \Delta v | \mathbf{k} + \mathbf{K} \rangle$$

non-spherical part

FLAPW Method






- **Two-dimensional slab models**
 - E. Wimmer, H. Krakauer, M. Weinert and A. J. Freeman, PRB 24, 864 (1981).
 - M. Weinert, E. Wimmer and A. J. Freeman, PRB 26, 4571 (1982).
- **Three-dimensional systems**
 - H. J. F. Jansen and A. J. Freeman, PRB 30 , 561 (1984).



FLAPW Packages Open to Public

$$\psi_j^{\mathbf{k}} = \tilde{\psi}_j^{\mathbf{k}} + \sum_{\nu} \left[\psi_{\nu j}^{\mathbf{k}} - \tilde{\psi}_{\nu j}^{\mathbf{k}} \right]$$

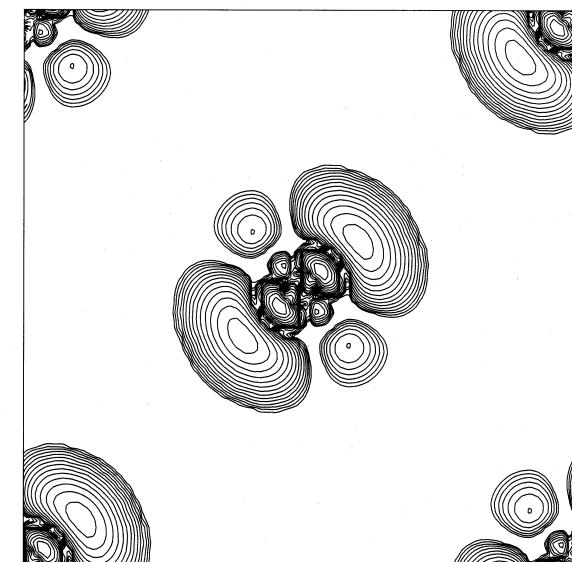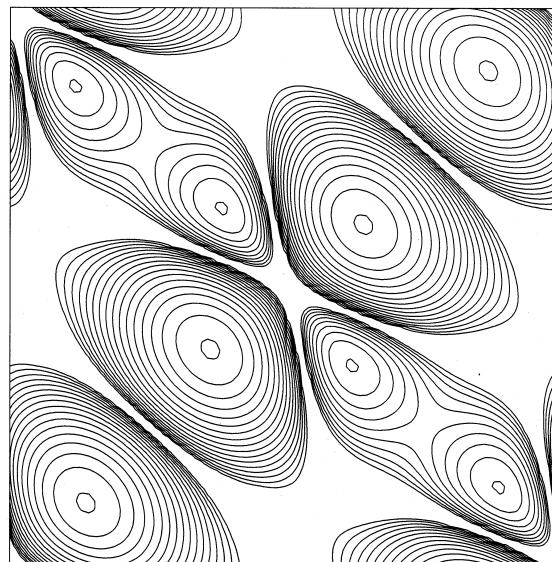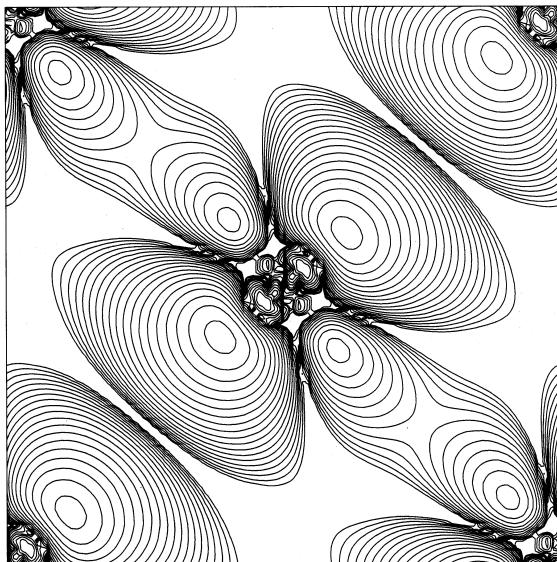

- ABCAP

- FLEUR


- HiLAPW

- QMD-FLAPW

- KANSAI

- WIEN


HiLAPW



- 100% Original Code
 - LAPW basis functions
 - LSDA, GGA, Hubbard-*U*
 - Scalar relativity, Spin-orbit coupling
 - All-electron SCF full-potential scheme
 - BZ integration with tetrahedron method
 - Group theory
 - Crystal structure & element database
 - Total E, forces, DOS, ...
 - XAS, Berry phase, dielectric function, ...

optional functionalities


HiLAPW



- 100% Original Code
 - Modular executables
 - fortran90
 - dynamical memory allocation
 - BLAS and LAPACK libraries
 - PSP : PostScript Plot routines
 - MPI parallelization
- Manuals and some useful data
 - www.cmp.sanken.osaka-u.ac.jp/~oguchi/HiLAPW/




HiLAPW – Executables



executables	contents
xsets	initialization
xlapw	SCF calculation
xdoss	DOS
xnewa	modification k-point data
xwbox	electron density on 3D mesh
xpbox	potential on 3D mesh
xspin	addition of spin polarization
xsymm	irreducible representation extract
xrept	rearrangement of eigenvalues

HiLAPW – Executables

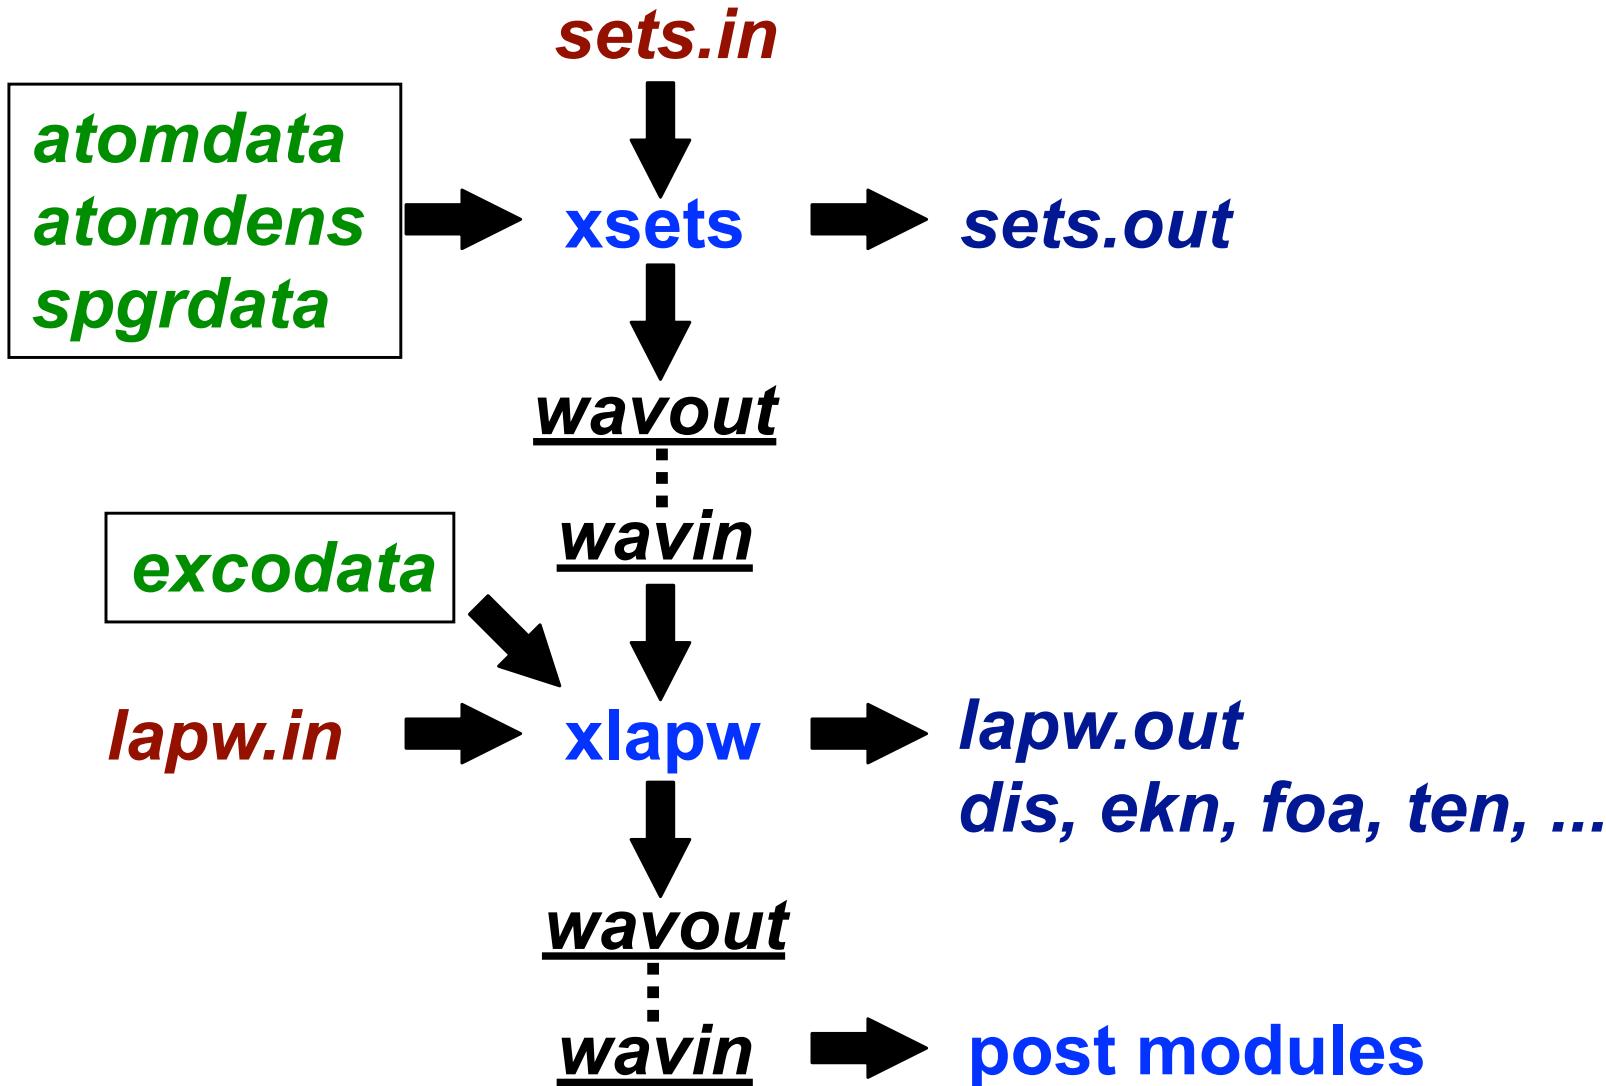




2. OUTLINE

- Practical Aspects of FLAPW Methods
 - First-Principles Calculation – Kohn-Sham Eqs.
 - Crystal Structure and Atomic Position
 - Lattice – Primitive Translation Vector
 - Space Group
 - Reciprocal Lattice – Brillouin Zone
 - k-point Integration
 - Eigenvalue Problem
 - Self-Consistent Field
 - Mixing of Electron Density

First-Principles Calculation



- Local Density Approximation to Density Functional Theory – Kohn-Sham Equations

$$\mathcal{H}\psi_j^{\mathbf{k}}(\mathbf{r}) = \left[-\frac{\hbar^2}{2m} \nabla^2 + v(\mathbf{r}) \right] \psi_j^{\mathbf{k}}(\mathbf{r}) = \varepsilon_j^{\mathbf{k}} \psi_j^{\mathbf{k}}(\mathbf{r})$$

$$n(\mathbf{r}) = \sum_{j,\mathbf{k}}^{\text{occ.}} |\psi_j^{\mathbf{k}}(\mathbf{r})|^2$$

$$v(\mathbf{r}) = -e^2 \sum_{\nu} \frac{Z_{\nu}}{|\mathbf{r} - \mathbf{R}_{\nu}|} + e^2 \int \frac{n(\mathbf{r}')}{|\mathbf{r} - \mathbf{r}'|} d\mathbf{r}' + \mu_{\text{xc}}(n(\mathbf{r}))$$

basic input

Crystal Structure and Atomic Position




$$\mathbf{R}_\nu = \mathbf{R}_{lmn} + \boldsymbol{\tau}_\alpha \quad \nu = (lmn\alpha)$$

- Lattice Vector

$$\mathbf{R}_{lmn} = l\mathbf{t}_1 + m\mathbf{t}_2 + n\mathbf{t}_3$$

$$\begin{pmatrix} R_{lmn}^x \\ R_{lmn}^y \\ R_{lmn}^z \end{pmatrix} = \underbrace{\begin{pmatrix} t_1^x & t_2^x & t_3^x \\ t_1^y & t_2^y & t_3^y \\ t_1^z & t_2^z & t_3^z \end{pmatrix}}_{\text{Primitive translation vector}}$$

Primitive translation vector

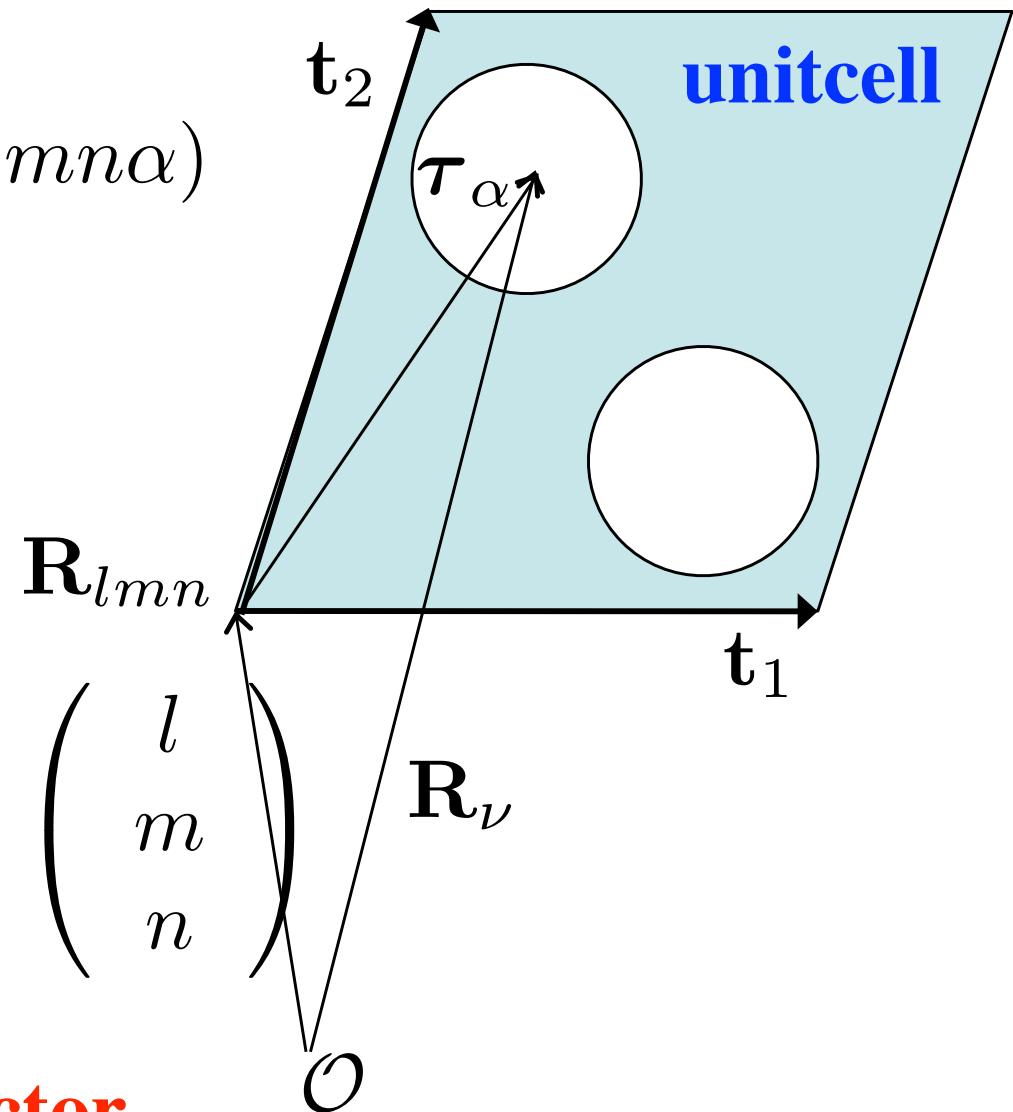

Lattice Translation Vector



- Primitive Translation Vector (Bravais lattice)

$$\begin{pmatrix} t_1^x & t_2^x & t_3^x \\ t_1^y & t_2^y & t_3^y \\ t_1^z & t_2^z & t_3^z \end{pmatrix} = \begin{pmatrix} a_1^x & a_2^x & a_3^x \\ a_1^y & a_2^y & a_3^y \\ a_1^z & a_2^z & a_3^z \end{pmatrix} \begin{pmatrix} T_{11} & T_{12} & T_{13} \\ T_{21} & T_{22} & T_{23} \\ T_{31} & T_{32} & T_{33} \end{pmatrix}$$

- Conventional Translation Vector

$$\begin{pmatrix} a_1^x & a_2^x & a_3^x \\ a_1^y & a_2^y & a_3^y \\ a_1^z & a_2^z & a_3^z \end{pmatrix} \Leftarrow (a, b, c, \alpha, \beta, \gamma)$$


Lattice constants

Lattice: System and Type




- Lattice system

$$\begin{pmatrix} a_1^x & a_2^x & a_3^x \\ a_1^y & a_2^y & a_3^y \\ a_1^z & a_2^z & a_3^z \end{pmatrix} \Leftarrow (a, b, c, \alpha, \beta, \gamma)$$

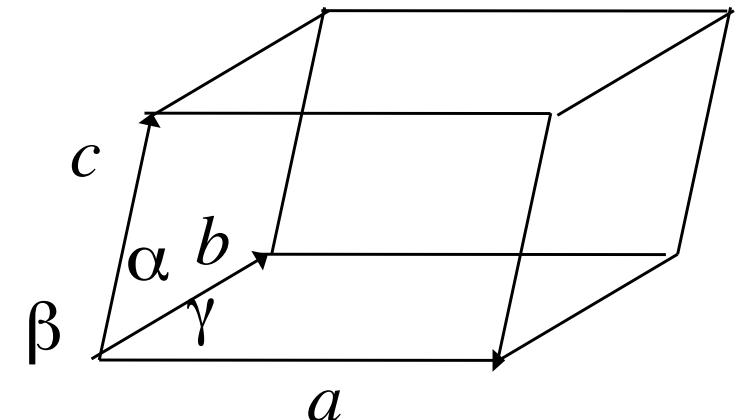

system	a	b	c	α	β	γ	type
cubic	a	a	a	90	90	90	P, I, F
tetragonal	a	a	c	90	90	90	P, I
orthorhombic	a	b	c	90	90	90	P, I, F, C
hexagonal	a	a	c	90	90	120	P
trigonal	a	a	a	α	α	α	R
(trigonal	a	a	c	90	90	120	P)
monoclinic	a	b	c	90	90	γ	P, B
triclinic	a	b	c	α	β	γ	P

Lattice: System and Type



- Lattice type



$$P = \begin{pmatrix} 1 & 0 & 0 \\ 0 & 1 & 0 \\ 0 & 0 & 1 \end{pmatrix}$$

$$F = \begin{pmatrix} 0 & \frac{1}{2} & \frac{1}{2} \\ \frac{1}{2} & 0 & \frac{1}{2} \\ \frac{1}{2} & \frac{1}{2} & 0 \end{pmatrix}$$

$$I = \begin{pmatrix} -\frac{1}{2} & \frac{1}{2} & \frac{1}{2} \\ \frac{1}{2} & -\frac{1}{2} & \frac{1}{2} \\ \frac{1}{2} & \frac{1}{2} & -\frac{1}{2} \end{pmatrix} \quad A = \begin{pmatrix} 1 & 0 & 0 \\ 0 & \frac{1}{2} & \frac{1}{2} \\ 0 & -\frac{1}{2} & \frac{1}{2} \end{pmatrix}$$


$$B = \begin{pmatrix} \frac{1}{2} & 0 & -\frac{1}{2} \\ 0 & 1 & 0 \\ \frac{1}{2} & 0 & \frac{1}{2} \end{pmatrix} \quad C = \begin{pmatrix} \frac{1}{2} & \frac{1}{2} & 0 \\ -\frac{1}{2} & \frac{1}{2} & 0 \\ 0 & 0 & 1 \end{pmatrix}$$


Lattice: System and Type

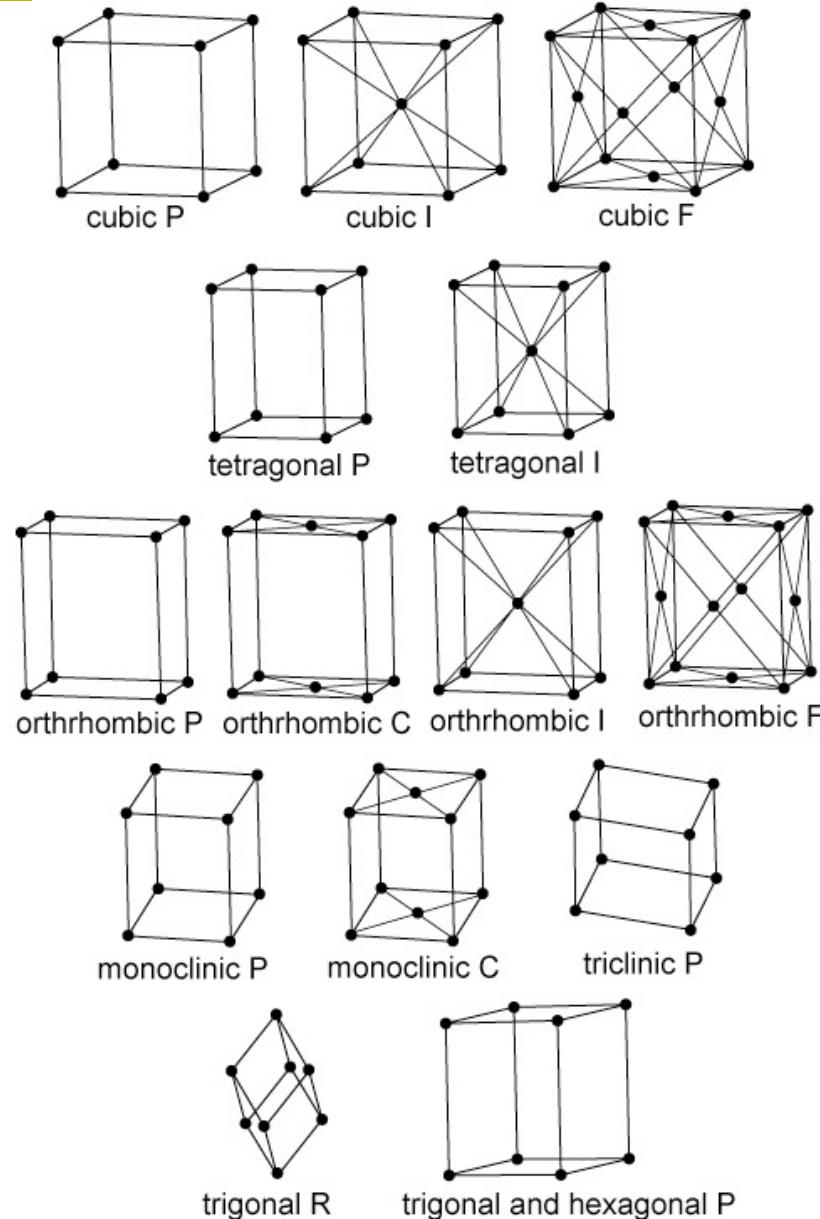

- Number of mathematically independent lattice is 14 called **Bravais Lattice**.
- For example, a face-centered tetragonal lattice can be represented as body-centered tetragonal.
- Some of trigonal systems are represented as **rhombohedral R or hexagonal P**.

Atomic Position in a Unitcell

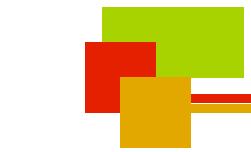
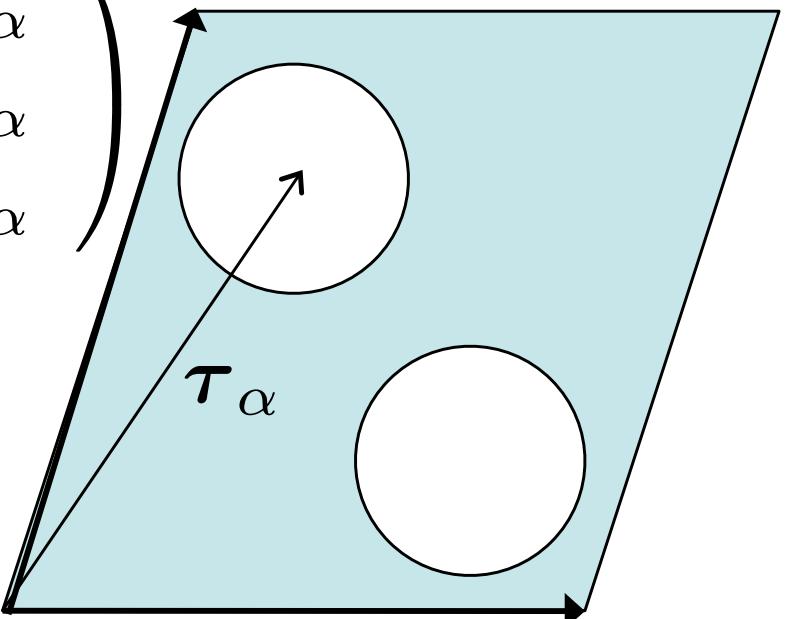
$$\begin{pmatrix} \tau_{\alpha}^x \\ \tau_{\alpha}^y \\ \tau_{\alpha}^z \end{pmatrix} = \begin{pmatrix} a_1^x & a_2^x & a_3^x \\ a_1^y & a_2^y & a_3^y \\ a_1^z & a_2^z & a_3^z \end{pmatrix} \begin{pmatrix} \tau_{1\alpha} \\ \tau_{2\alpha} \\ \tau_{3\alpha} \end{pmatrix}$$


Atomic positions are represented on the basis of the conventional lattice vectors.



Space Group

- Symmetry operation $\{\beta|\mathbf{v}_\beta + \mathbf{R}_{lmn}\}$

$\{\beta|\mathbf{v}_\beta\} \mathbf{r} = \beta \mathbf{r} + \underline{\mathbf{v}_\beta}$ **non-primitive translation vector**


$$= \begin{pmatrix} \beta_{11} & \beta_{12} & \beta_{13} \\ \beta_{21} & \beta_{22} & \beta_{23} \\ \beta_{31} & \beta_{32} & \beta_{33} \end{pmatrix} \begin{pmatrix} x \\ y \\ z \end{pmatrix} + \begin{pmatrix} v_\beta^x \\ v_\beta^y \\ v_\beta^z \end{pmatrix}$$



Example: Diamond Structure

- fcc $a=b=c, \alpha=\beta=\gamma=90^\circ$
- space group Fd-3m (#227)
generators $C_4[001] + (1/4,1/4,1/4)$
 $C_3[111]$
 $I + (1/4,1/4,1/4)$
- atomic positions $(0,0,0); (1/4,1/4,1/4)$


International Tables for Crystallography




k Group

$$\beta k = k + K$$

The Bloch wave function belongs to an irreducible representation of the k group.

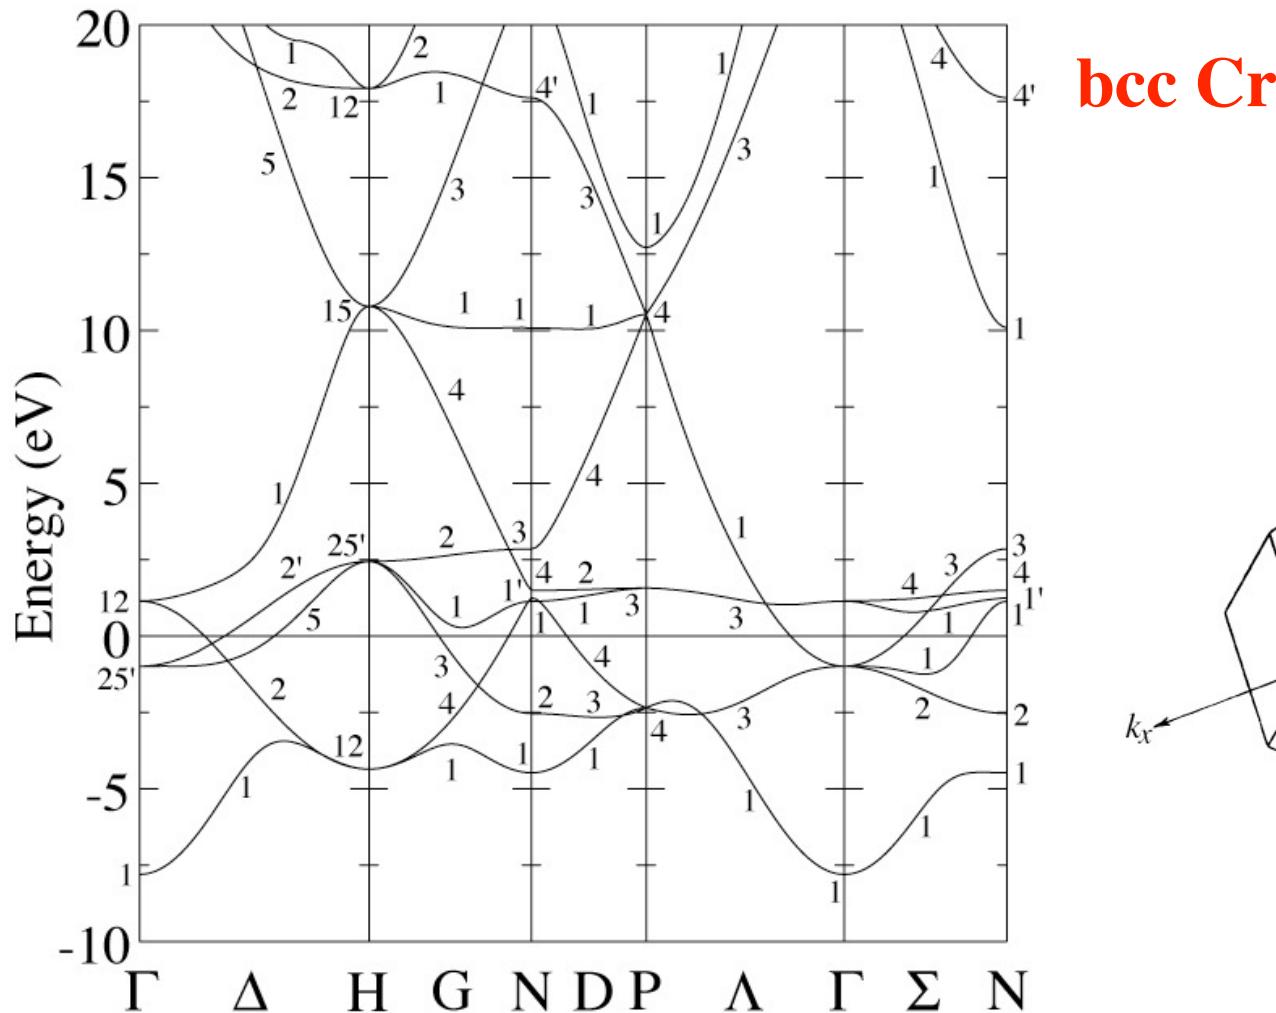

bcc Cr

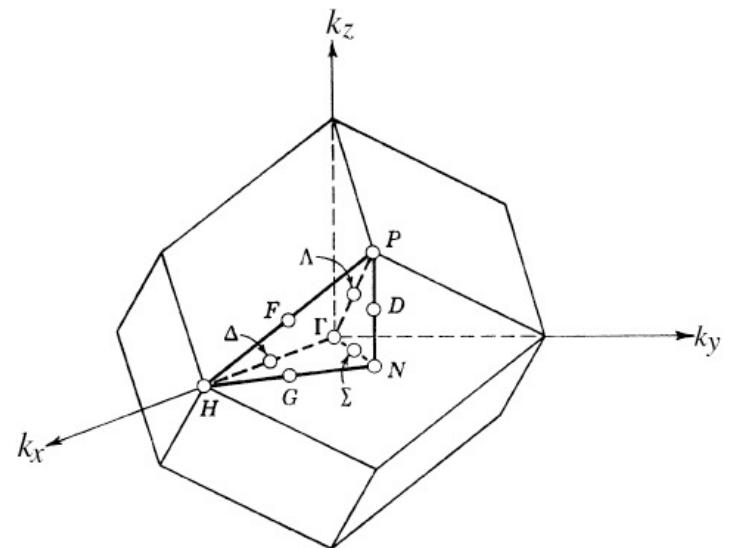



Space Group Symbol

1,2,3,4,6 : rotation axis

m : mirror plane

2₁ : twofold screw with $v=1/2$

4₂ : fourfold screw with $v=2/4$

a, b, c : axial glide with $v=1/2$ along each axis

n : diagonal glide

d : diamond glide

- : inversion

4/m : fourfold axis and mirror plane perpendicular to it

4/n : fourfold axis and n-glide plane perpendicular to it



Reciprocal Lattice

- Definition

$$\underline{\mathbf{R} \cdot \mathbf{K}} = 2\pi I \quad I : \text{any integer}$$

lattice vector

$$\mathbf{K}_{lmn} = l\mathbf{b}_1 + m\mathbf{b}_2 + n\mathbf{b}_3$$

$$\mathbf{b}_i = 2\pi \frac{\mathbf{t}_j \times \mathbf{t}_k}{\mathbf{t}_i \cdot (\mathbf{t}_j \times \mathbf{t}_k)}$$

- Brillouin zone (BZ) = unitcell of reciprocal lattice
- States with \mathbf{k} inside BZ are independent
→ State sum = \mathbf{k} -integration inside BZ



Brillouin Zone




Unitcell of reciprocal lattice

- parallelepiped $(\mathbf{b}_1, \mathbf{b}_2, \mathbf{b}_3)$
easy to treat numerically
- Voronoi Polyhedron

Wigner-Seitz cell

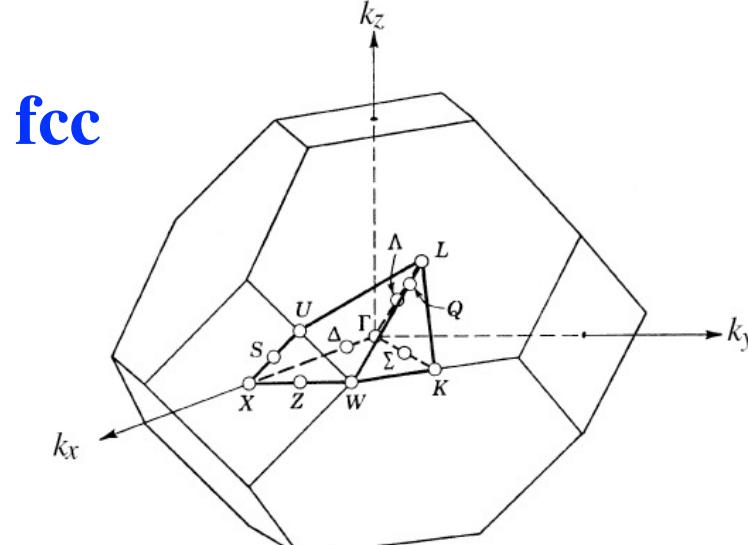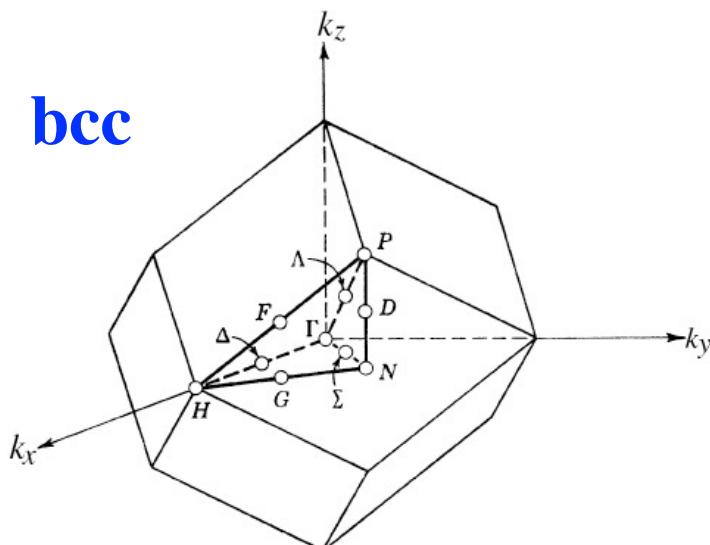


k Integration



k-point mesh


(N_1, N_2, N_3) division of parallelepiped BZ

$$n(\mathbf{r}) = \sum_{j,\mathbf{k}}^{\text{occ.}} |\psi_j^\mathbf{k}(\mathbf{r})|^2$$

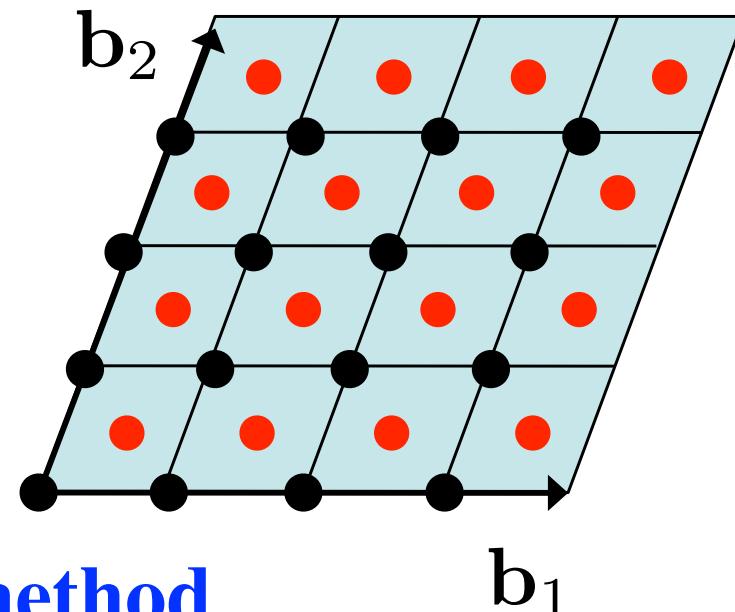

- **Linear Tetrahedron method**
- **Broadening method**

Eigenvalue Problem



- Basis function expansion

$$\psi_j^{\mathbf{k}}(\mathbf{r}) = \sum_{\mathbf{i}} \phi_i^{\mathbf{k}} C_{ij}^{\mathbf{k}}$$

- Secular equation

$$\mathbf{H}\mathbf{C} = \mathbf{S}\mathbf{C}\mathbf{E}$$

- Matrix elements

$$H_{ij} = \langle \phi_i^{\mathbf{k}} | \mathcal{H} | \phi_j^{\mathbf{k}} \rangle \quad S_{ij} = \langle \phi_i^{\mathbf{k}} | \phi_j^{\mathbf{k}} \rangle$$



Basis Functions

- **Plane waves**
 - pseudopotential
 - simple, fast, extendable, transferability
- **Plane waves + Augmentation functions**
 - all-electron scheme
 - robust, precise, complicated
- **Local orbitals**
 - minimal
 - real space $\rightarrow \mathbf{O}(N)$

Self-Consistent Field



$$\{Z_\nu, \mathbf{R}_\nu\}$$



$$n_{\text{in}}(\mathbf{r})$$



$$v(\mathbf{r})$$



$$\mathbf{HC} = \mathbf{SCE}$$



$$n_{\text{out}}(\mathbf{r})$$



$$\langle |n_{\text{in}}(\mathbf{r}) - n_{\text{out}}(\mathbf{r})| \rangle > \delta$$



$$E(\{Z_\nu, \mathbf{R}_\nu\}) \quad n(\mathbf{r})$$

$$\langle |n_{\text{in}}(\mathbf{r}) - n_{\text{out}}(\mathbf{r})| \rangle \leq \delta$$



Mixing of Electron Density

- Simple Method

$$n_{\text{in}}^{(i+1)} = (1 - \alpha)n_{\text{in}}^{(i)} + \alpha n_{\text{out}}^{(i)}$$

- Extended Anderson Method



$$n_{\text{in}}^{(i+1)} = (1 - \alpha)\bar{n}_{\text{in}}^{(i)} + \alpha\bar{n}_{\text{out}}^{(i)}$$

$$\bar{n}_{\text{in}}^{(i)} = \sum_{j=i-M}^i \beta^{(j)} n_{\text{in}}^{(j)}$$

$$\bar{n}_{\text{out}}^{(i)} = \sum_{j=i-M}^i \beta^{(j)} n_{\text{out}}^{(j)}$$

$$\min_{\beta} \int \left(\bar{n}_{\text{in}}^{(i)} - \bar{n}_{\text{out}}^{(i)} \right)^2 d\mathbf{r} \quad \sum_{j=i-M}^i \beta^{(j)} = 1$$

Mixing of Electron Density

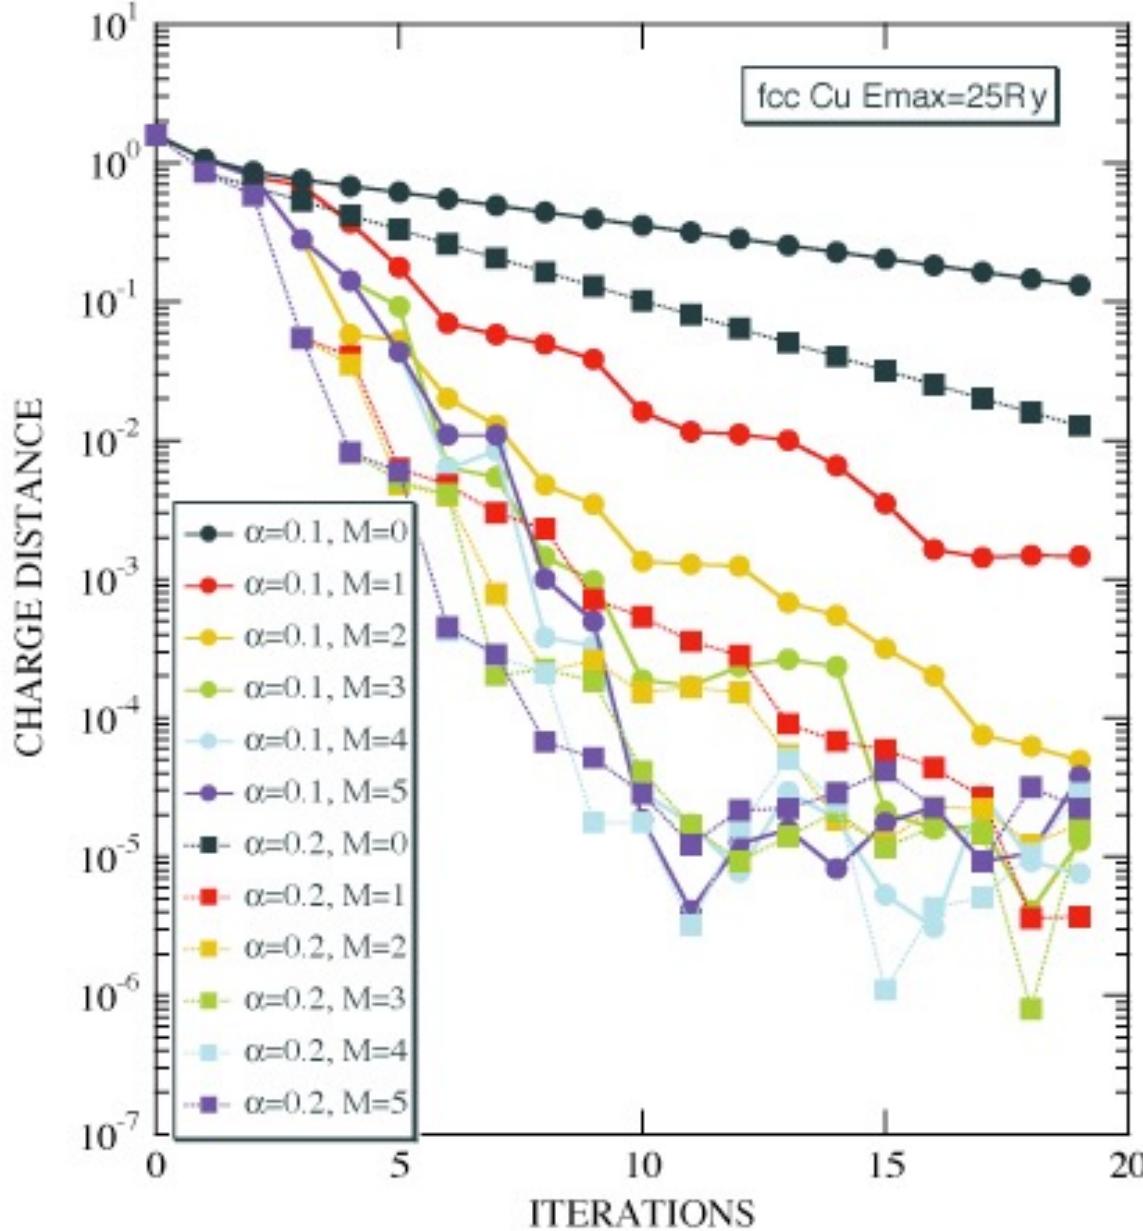


$$\left[\int |n_{\text{in}} - n_{\text{out}}|^2 d\mathbf{r} \right]^{1/2}$$

Convergency to SCF



CHARGE DISTANCE

TOTAL ENERGY(Ry)

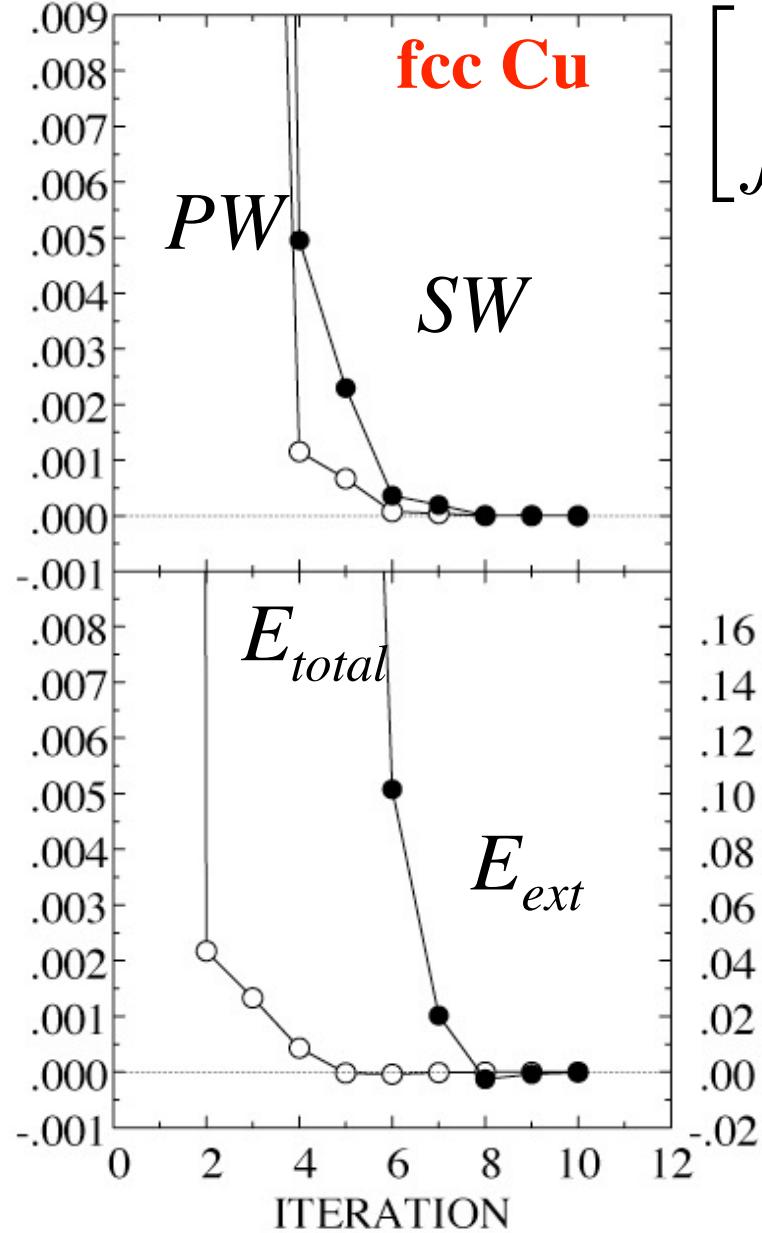


$$\begin{aligned}
 & \left[\int |n_{\text{in}}(\mathbf{r}) - n_{\text{out}}(\mathbf{r})|^2 d\mathbf{r} \right]^{1/2} \\
 & [-\Delta + v[n_{\text{in}}]] \underset{\text{occ.}}{\psi_j^{\mathbf{k}}(\mathbf{r})} = \varepsilon_j^{\mathbf{k}} \psi_j^{\mathbf{k}}(\mathbf{r}) \\
 & n_{\text{out}} = \sum_{j,\mathbf{k}} |\psi_j^{\mathbf{k}}|^2 \\
 & [-\Delta + v[n_{\text{out}}] + v_{\text{ext}}] \psi_j^{\mathbf{k}}(\mathbf{r}) \\
 & = \varepsilon_j^{\mathbf{k}} \psi_j^{\mathbf{k}}(\mathbf{r}) \\
 & v_{\text{ext}} = v[n_{\text{in}}] - v[n_{\text{out}}] \\
 & E_{\text{ext}} = \int v_{\text{ext}} n_{\text{out}} d\mathbf{r}
 \end{aligned}$$



Appendix


- **Logarithmic Derivatives**
- **Density of States**
- **Precision of FLAPW**
- **All-Electron vs. Pseudopotential**
- **Murnaghan's Equation of State**

Logarithmic Derivative



$$L_l(E) = \frac{R'_l(S; E)}{R_l(S; E)} = \left. \frac{d}{dr} \ln R_l(r; E) \right|_{r=S}$$

The APW eigenfunction satisfies the boundary conditions (logarithmic derivatives) on the spheres among the general solutions.

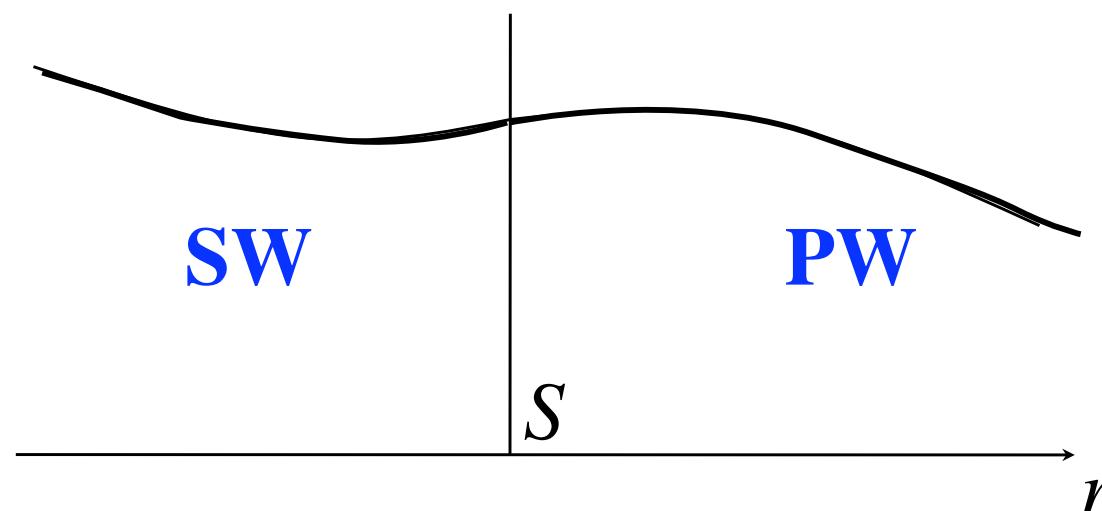

Single-MT Problem



Radial Equation in Rydberg units

$$\left[-\frac{d^2}{dr^2} - \frac{2}{r} \frac{d}{dr} + \frac{l(l+1)}{r^2} + v(r) - E \right] R_l(r; E) = 0$$

Normalization

$$\int_0^S R_l^2(r; E) r^2 dr = 1$$


Radial function

$$P_l(r; E) = r R_l(r; E)$$


$$\left[-\frac{d^2}{dr^2} + \frac{l(l+1)}{r^2} + v(r) - E \right] P_l(r; E) = 0$$

$$\int_0^S P_l^2(r; E) dr = 1$$


Energy Dependence of Radial Function




$$\frac{d^2 P_l(r; E)}{dr^2} = \left[\frac{l(l+1)}{r^2} + v(r) - E \right] P_l(r; E)$$

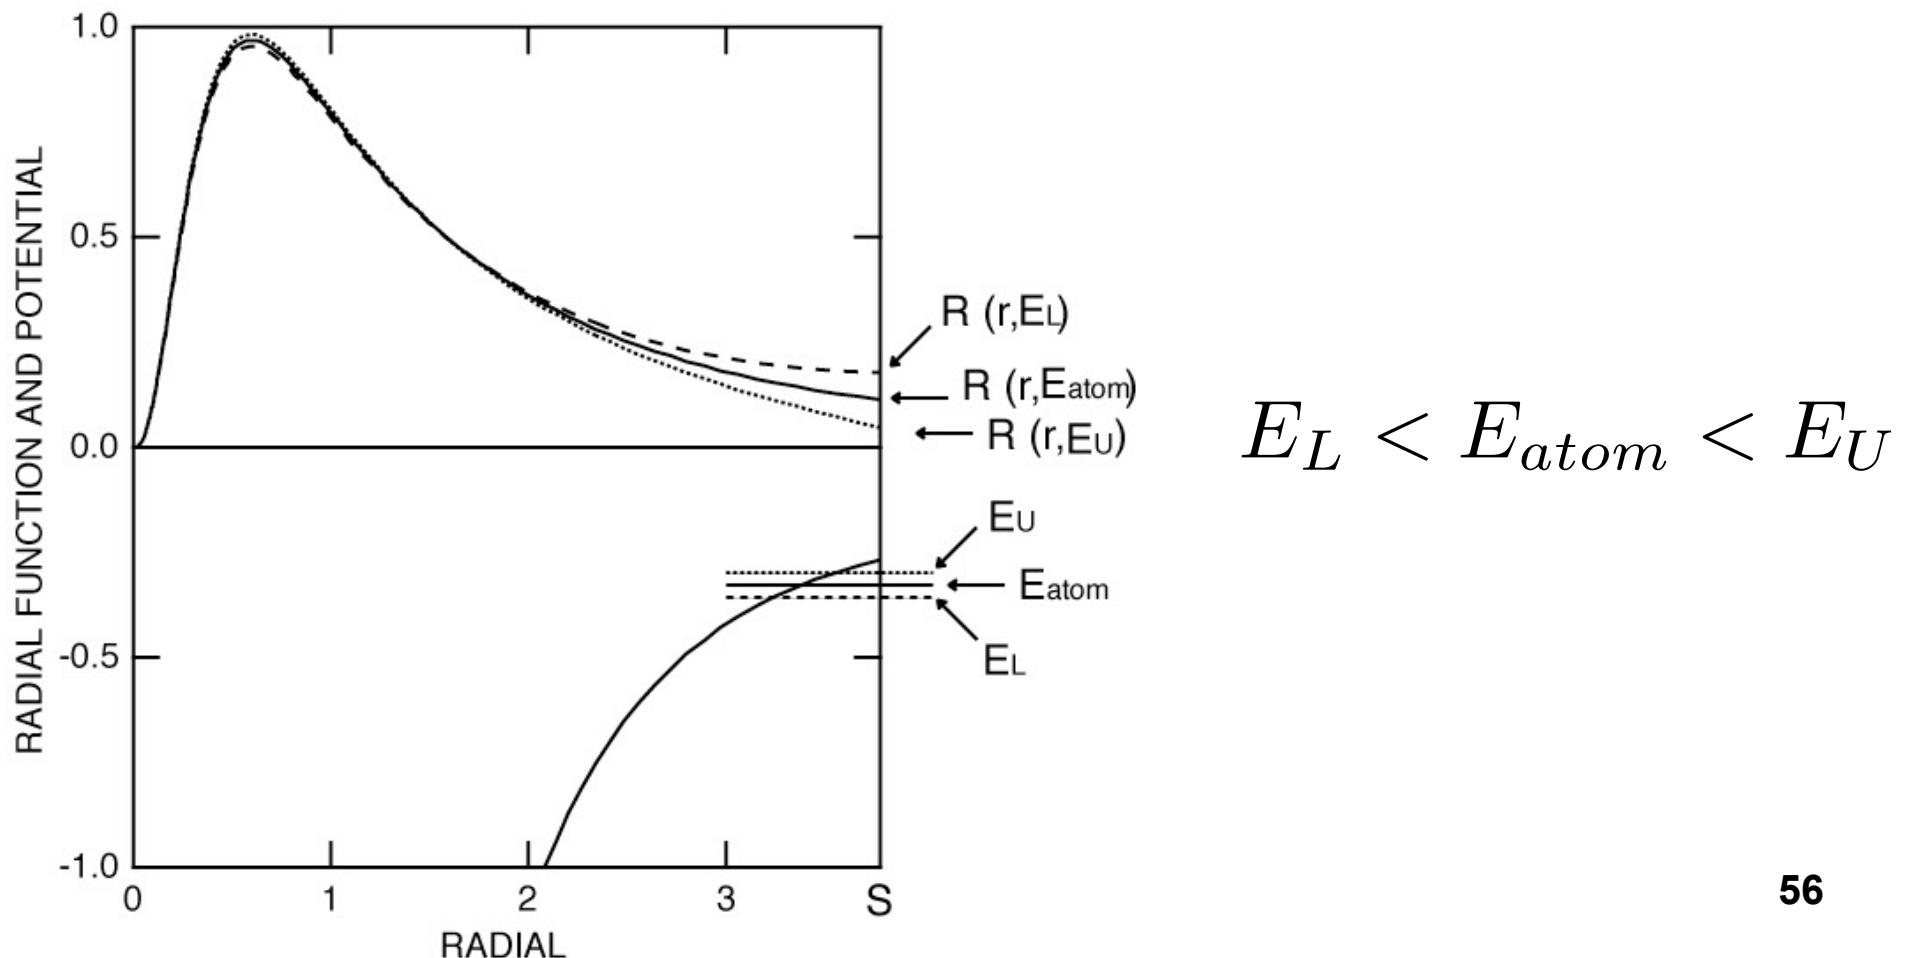

Logarithmic Derivative



$$L_l(E) = \frac{R'_l(S; E)}{R_l(S; E)} = \left. \frac{d}{dr} \ln R_l(r; E) \right|_{r=S}$$

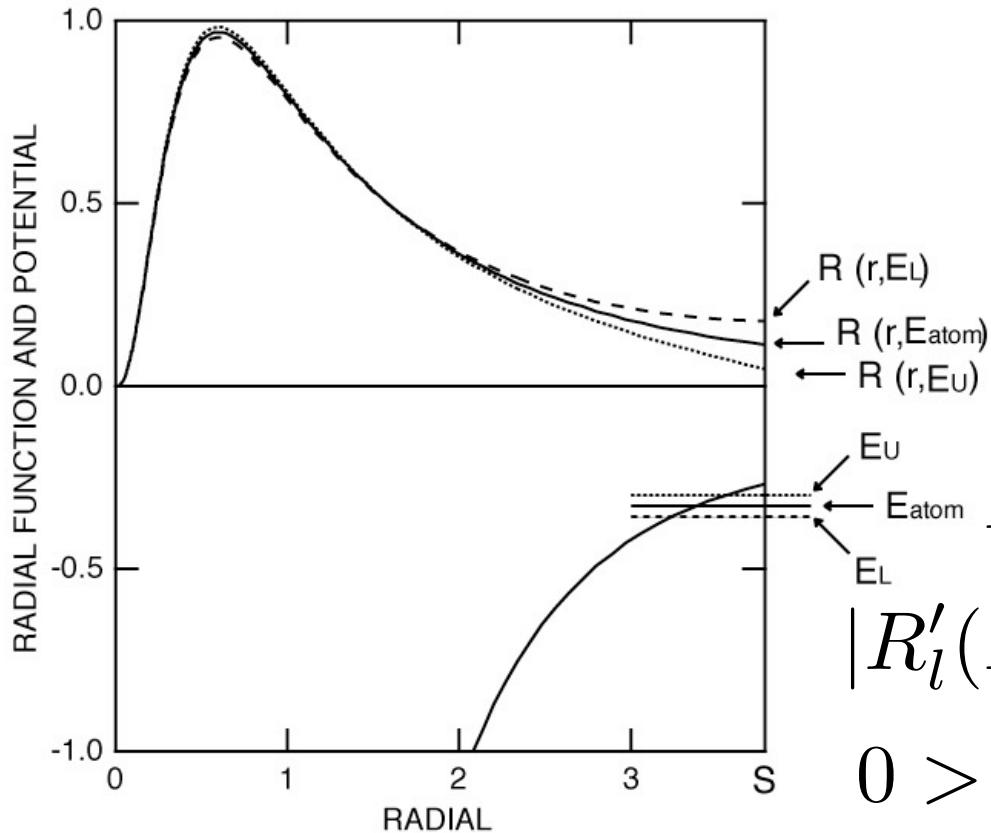


$$E_L < E_{atom} < E_U$$

$$R_l(E_L) > R_l(E_{atom}) > R_l(E_U)$$

$$|R'_l(E_L)| < |R'_l(E_{atom})| < |R'_l(E_U)|$$


$$0 > L_l(E_L) > L_l(E_{atom}) > L_l(E_U)$$

Logarithmic Derivative




$$L_l(E)$$


bcc W-d

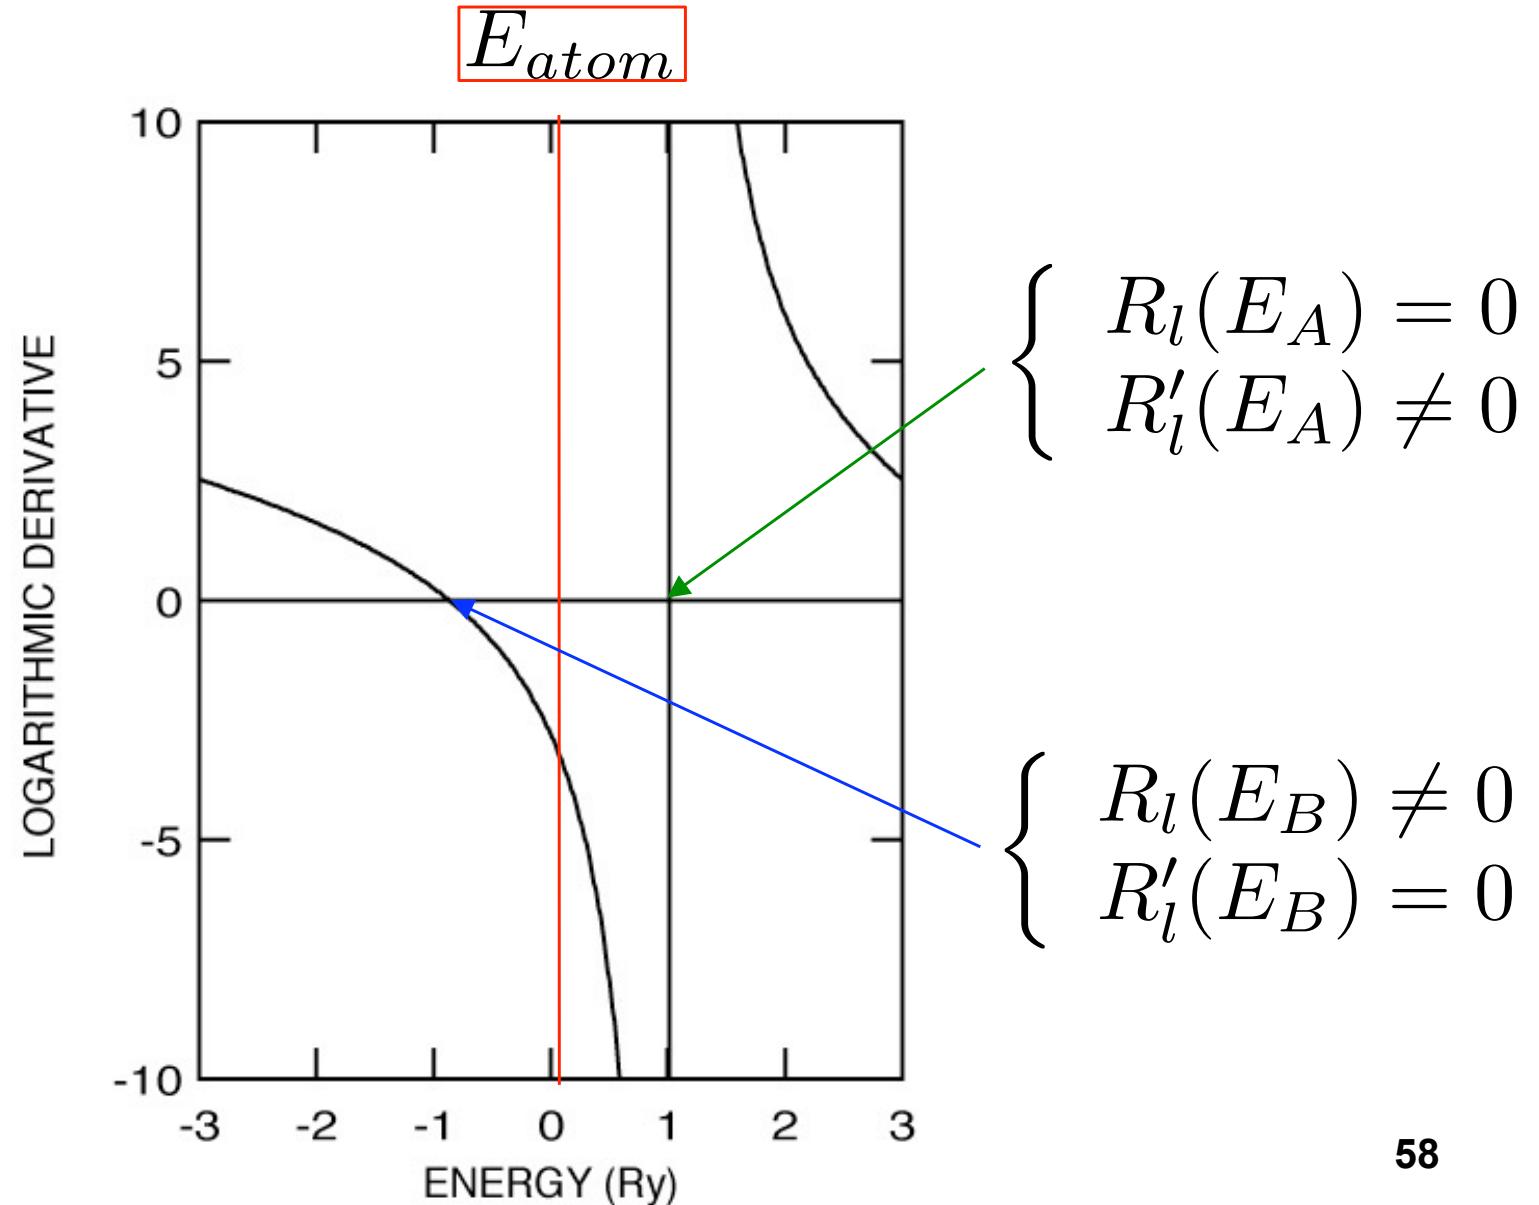

Logarithmic Derivative




$$\begin{cases} R_l(E_A) = 0 \\ R'_l(E_A) \neq 0 \end{cases}$$

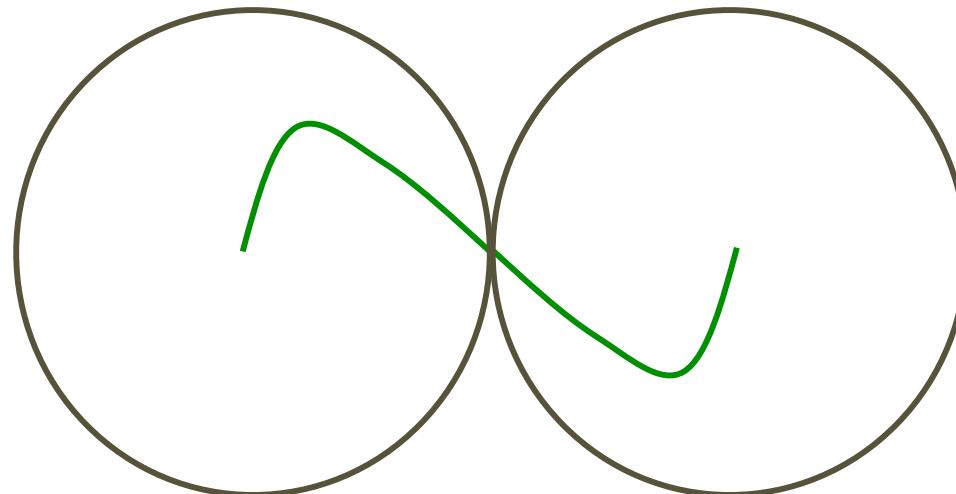



Anti-bonding state

$$\begin{cases} R_l(E_B) \neq 0 \\ R'_l(E_B) = 0 \end{cases}$$

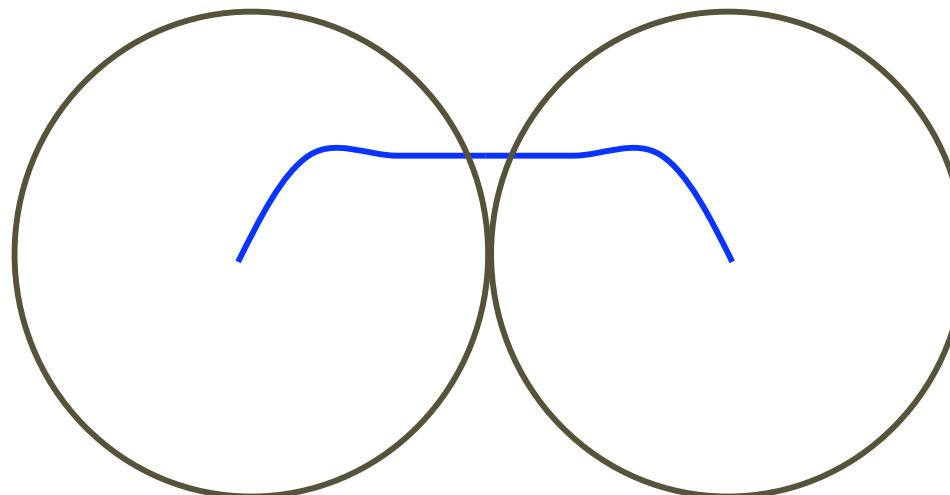

Bonding state

Density of States

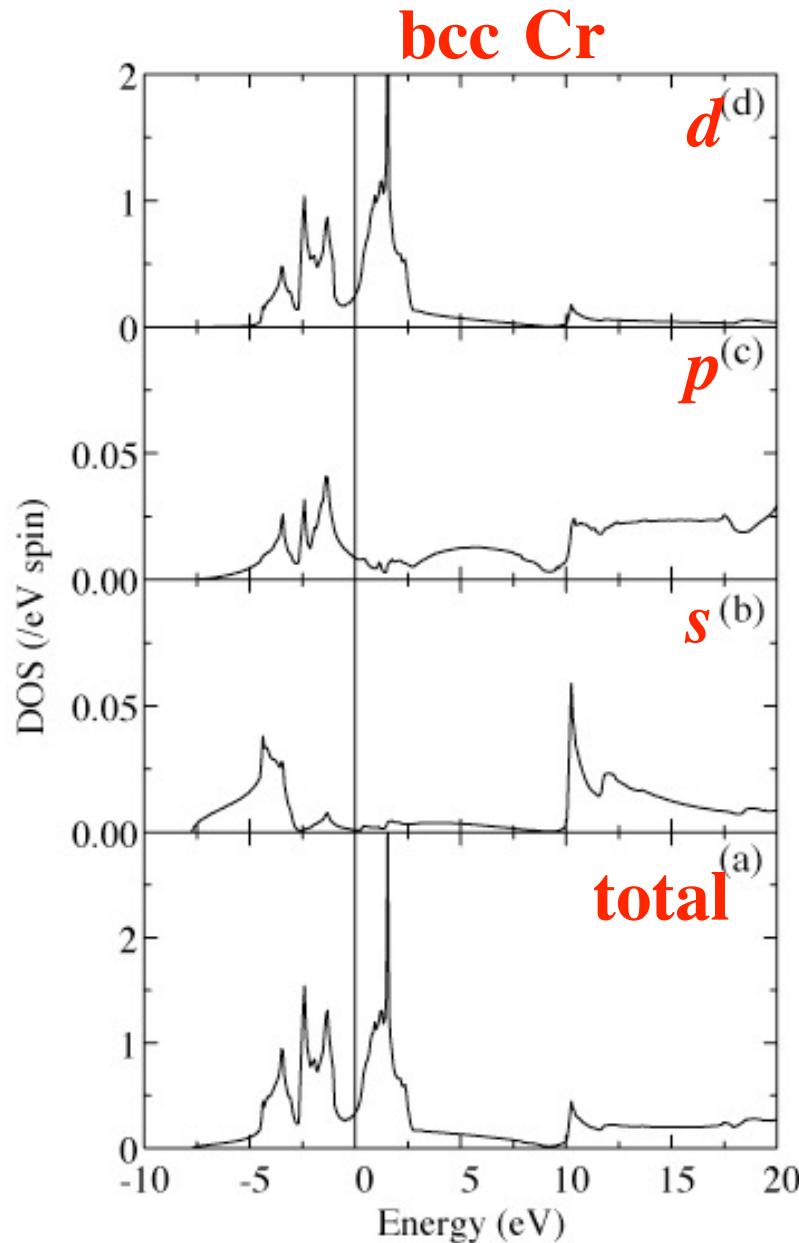

$$\begin{aligned}
 D(E) &= \sum_{j,\mathbf{k}} \delta(E - \varepsilon_j^{\mathbf{k}}) \\
 &= \sum_{j,\mathbf{k}} \langle \psi_j^{\mathbf{k}} | \psi_j^{\mathbf{k}} \rangle \delta(E - \varepsilon_j^{\mathbf{k}}) \\
 &\quad \uparrow \\
 &\quad \sum_m |m\rangle\langle m| = 1 \\
 &= \sum_m \left[\sum_{j,\mathbf{k}} |\langle \psi_j^{\mathbf{k}} | m \rangle|^2 \delta(E - \varepsilon_j^{\mathbf{k}}) \right] \\
 &= \sum_m D_m(E)
 \end{aligned}$$

partial DOS 60



Wave Functions

- **LAPW Basis**

$$\tilde{\phi}^{\mathbf{k}+\mathbf{K}}(\mathbf{r}) = \frac{1}{\sqrt{\Omega}} e^{i(\mathbf{k}+\mathbf{K}) \cdot \mathbf{r}}$$


$$\phi^{\mathbf{k}+\mathbf{K}}(\mathbf{r}) = \sum_{\alpha lm} \left[A_{\alpha lm}^{\mathbf{k}+\mathbf{K}} R_l(r_\alpha) + B_{\alpha lm}^{\mathbf{k}+\mathbf{K}} \dot{R}_l(r_\alpha) \right] i^l Y_{lm}(\hat{\mathbf{r}}_\alpha)$$

- **Degrees of Variational Freedom**

$$K_{\max} \qquad \qquad l_{\max}$$

- **Choice of MT Sphere Radius**

Electron Density and Potential



$$\tilde{n}(\mathbf{r}) = \sum_{\mathbf{G}} e^{i\mathbf{G}\cdot\mathbf{r}} n_{\mathbf{G}} \quad n(\mathbf{r}) = \sum_{\alpha LM} n_{\alpha LM}(r_{\alpha}) i^L Y_{LM}(\hat{\mathbf{r}}_{\alpha})$$

$$\tilde{v}(\mathbf{r}) = \sum_{\mathbf{G}} e^{i\mathbf{G}\cdot\mathbf{r}} v_{\mathbf{G}} \quad v(\mathbf{r}) = \sum_{\alpha LM} v_{\alpha LM}(r_{\alpha}) i^L Y_{LM}(\hat{\mathbf{r}}_{\alpha})$$

- Accuracy of Expansion

$$G_{\max} \qquad L_{\max}$$

variational parameters?

- Choice of MT Sphere Radius



Perturbative Consideration


- **Second-Order Perturbation**

$$\Delta\epsilon^{\mathbf{k}} = -\frac{|\langle \mathbf{k} + \mathbf{K} | \mathcal{H} | \mathbf{k} \rangle|^2}{|\mathbf{k} + \mathbf{K}|^2 - \epsilon^{\mathbf{k}}}$$

- **Variational Parameters of the Wave Functions**

$$|\mathbf{k} + \mathbf{K}| \leq K_{\max}$$

$$l_{\max}$$



Muffin-Tin Sphere Radius

When a sufficient l_{\max} is assumed,

- In case of large MT sphere radius, because of smaller volume in the interstitial region fewer PW expansion is needed.
- In case of small MT sphere radius, because of larger volume in the interstitial region more PW expansion is needed.
- A variational dimensionless parameter

$$RK_{\max}$$

Wave Functions and Electron Density



$$n(\mathbf{r}) = \sum_{\mathbf{k}, n} |\psi_n^{\mathbf{k}}(\mathbf{r})|^2$$

$$G_{\max} \geq 2K_{\max}$$

$$L_{\max} \geq 2l_{\max}$$



- Convergency of the electron density and potential expansion should be checked, especially when GGA is used.
- For small MT spheres used, higher G_{\max} may be required to represent pseudized charge density.



Muffin-Tin Sphere Radius

- Non-overlapping spheres
 - A margin should be considered if the atomic positions are changed, for example in a structural optimization calculation.
- Negligible penetration of the core functions outside
 - Within both assumptions with sufficient l_{\max} and L_{\max} , the accuracy does not depend on the choice of MT sphere radius but does on RK_{\max} .

Total Energy vs. Muffin-Tin Radius

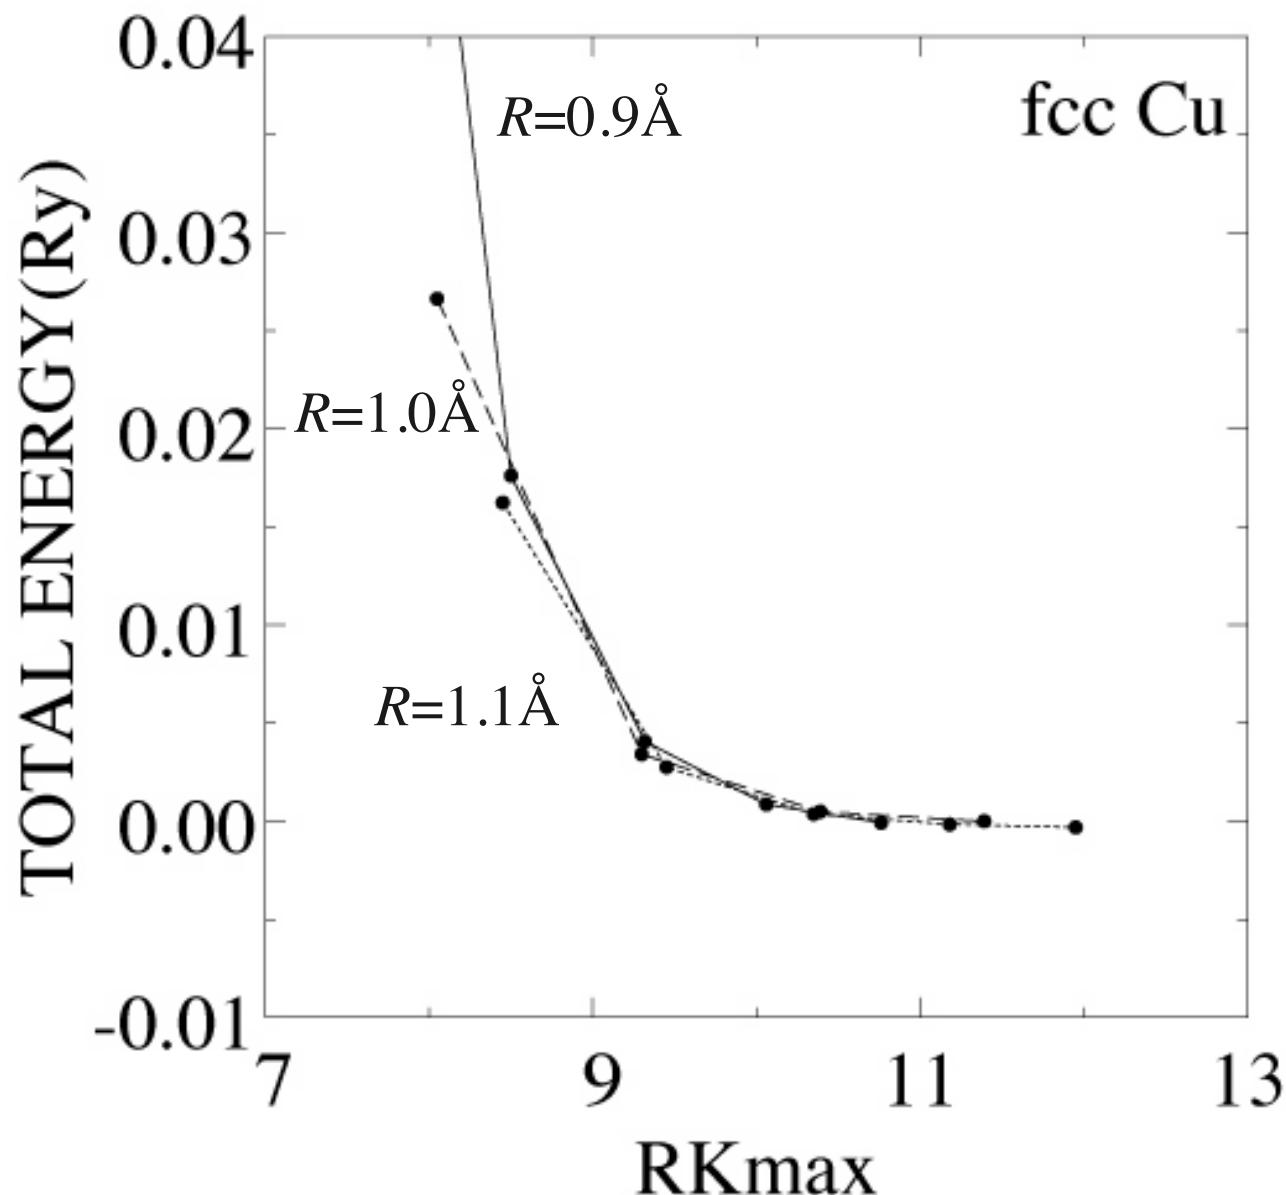



Precision of FLAPW Method

- Wave Functions RK_{\max}

- Electron Density and Potential

$$G_{\max} \geq 2K_{\max} \quad L_{\max} \geq 2l_{\max}$$


- Choice of MT Sphere Radius

- Over-completeness of APW Basis Functions

Since the PW basis is a complete set in all the space, an APW basis with the excessive number of PW results in indefinite solutions.


All-Electron vs. Pseudopotential

Δ -gauge

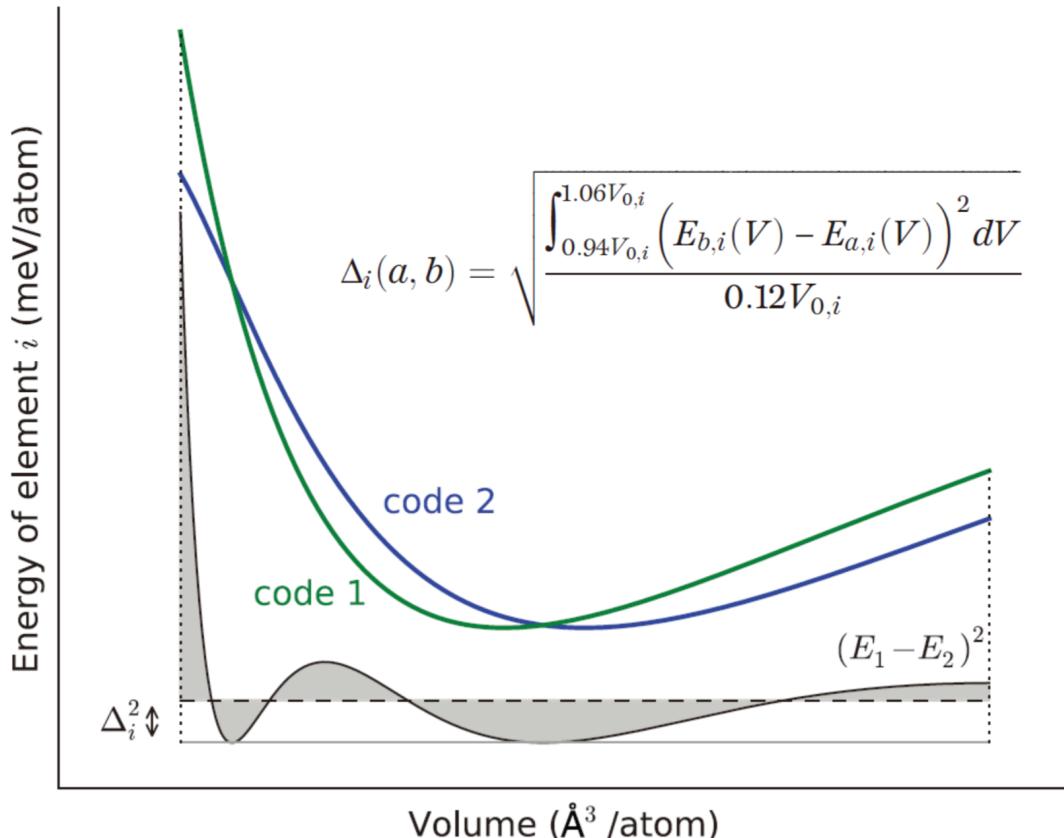

Science 351, aad3000 (2016)

		AE								
		average $\langle \Delta \rangle$	Elk	exciting	FHI-aims/tier2	FLEUR	FPLO/T+F+s	RSPT	WIEN2k/acc	
AE		0.6	0.3	0.3	0.6	1.0	0.9	0.3		
	Elk	0.6								
	exciting	0.5	0.3		0.1	0.5	0.9	0.8	0.2	
	FHI-aims/tier2	0.5	0.3	0.1		0.5	0.9	0.8	0.2	
	FLEUR	0.6	0.6	0.5	0.5		0.8	0.6	0.4	
	FPLO/T+F+s	0.9	1.0	0.9	0.9	0.8		0.9	0.9	
	RSPT	0.8	0.9	0.8	0.8	0.6	0.9		0.8	
	WIEN2k/acc	0.5	0.3	0.2	0.2	0.4	0.9	0.8		
PAW		GBRV12/ABINIT	0.9	0.9	0.8	0.9	1.3	1.1	0.8	
	GPAW09/ABINIT	1.4	1.3	1.3	1.3	1.3	1.7	1.5	1.3	
	GPAW09/GPAW	1.6	1.5	1.5	1.5	1.5	1.8	1.7	1.5	
	JTH02/ABINIT	0.6	0.6	0.6	0.6	0.9	0.7	0.5		
	pslib100/QE	0.9	0.9	0.8	0.8	1.3	1.1	0.8		
VASP		VASPGW2015/VASP	0.6	0.4	0.4	0.6	1.0	0.8	0.3	
USPP		GBRV14/CASTEP	1.1	1.1	1.0	1.0	1.4	1.3	1.0	
	GBRV14/QE	1.1	1.0	1.0	0.9	1.0	1.4	1.3	1.0	
	OTFG9/CASTEP	0.7	0.4	0.5	0.5	0.7	1.0	1.0	0.5	
	SSSP/QE	0.5	0.4	0.3	0.3	0.5	0.9	0.8	0.3	
	Vdb2/DACAPO	6.3	6.3	6.3	6.3	6.4	6.5	6.2		
NCPP		FHI98pp/ABINIT	13.3	13.5	13.4	13.4	13.2	13.0	13.2	13.4
	HGH/ABINIT	2.2	2.2	2.2	2.2	2.0	2.3	2.2	2.1	
	HGH-NLCC/BigDFT	1.1	1.1	1.1	1.1	1.0	1.2	1.1	1.0	
	MBK2013/OpenMX	2.0	2.1	2.1	2.1	1.9	1.8	1.8	2.0	
	ONCVPPSP (PD0.1)/ABINIT	0.7	0.7	0.7	0.7	0.6	1.0	0.8	0.6	
	ONCVPPSP (SG15)1/QE	1.4	1.4	1.3	1.3	1.3	1.6	1.5	1.3	
	ONCVPPSP (SG15)2/CASTEP	1.4	1.4	1.4	1.3	1.3	1.6	1.5	1.4	



Murnaghan's Equation of State

$$p = \frac{B_0}{B'} \left[\left(\frac{\Omega}{\Omega_0} \right)^{-B'} - 1 \right]$$

$$B_0 = - \left(\Omega \frac{dp}{d\Omega} \right)_0 \quad B' = - \frac{1}{B_0} \left(\Omega \frac{dB}{d\Omega} \right)_0$$

$$E(\Omega) = \frac{B_0 \Omega}{B'} \left[\frac{1}{B' - 1} \left(\frac{\Omega}{\Omega_0} \right)^{-B'} + 1 \right] + E'$$

1 a.u. in pressure = 1.47108×10^4 GPa