

5th Lecture: Spintronics, Design, Magnetization Control I

Tatsuki Oda

Institute of Science and Engineering, Kanazawa University

Spintronics Design Course in CMD-WS36

10:40～12:10, 18th February, 2020

(90 minutes)

第5講義：スピントロニクス・デザイン・磁化制御 I :90分 小田竜樹(金沢大理工)

検索：

計算ナノ科学

Email: oda@cphys.s.kanazawa-u.ac.jp

<http://cphys.s.kanazawa-u.ac.jp/~oda-web/index.html>

1

Contents in 5th lecture

- (5-1) Electronics structure: Ferromagnetism, Antiferromagnetism
 - (5-2) Magnetic moment: spin, orbital, localized and itinerant
 - (5-3) Zeeman energy
 - (5-4) Distance and interaction between magnetic carriers, magnetic dipole interaction
 - (5-5) Spin-orbit interaction, spin-texture in the reciprocal space
 - (5-6) Spin transfer Torque
 - (5-7) Magnetic anisotropy energy: electron orbital, magnet shape
 - (5-8) Magnetic anisotropy: in-plane, perpendicular
 - (5-9) Voltage-induced spin torque
 - (5-10) Landau–Lifshitz–Gilbert equation
 - (5-11) Design on magnetic anisotropy in magnetic materials
-
- (5-1) 電子構造(強磁性、反強磁性)、
 - (5-2) 磁気モーメント(スピン、軌道、局在・遍歴)
 - (5-3) ゼーマンエネルギー
 - (5-4) 磁性担体距離と磁気相互作用、磁気双極子相互作用
 - (5-5) スピン軌道相互作用、逆格子空間スピントクスチャ
 - (5-6) スピントランスマートルク
 - (5-7) 磁気異方性エネルギー(電子軌道、磁性体形状)
 - (5-8) 磁気異方性(面内、面直)
 - (5-9) 電圧スピントルク
 - (5-10) ランダウ＝リフシツ＝ギルバート方程式
 - (5-11) 磁性薄膜材料の磁気異方性デザイン

2

(5-1) Electronics structure: Ferromagnetism, Anti-ferromagnetism

One electron approx.

$$\left\{ -\frac{\hbar^2}{2m} \nabla^2 + V(\mathbf{r}) \right\} \Psi_{n\mathbf{k}\sigma}(\mathbf{r}) = \epsilon_{n\mathbf{k}\sigma} \Psi_{n\mathbf{k}\sigma}(\mathbf{r})$$

$(n\mathbf{k}\sigma)$: quantum number

$\Psi_{n\mathbf{k}\sigma}(\mathbf{r})$: wave function


$\epsilon_{n\mathbf{k}\sigma}$: eigenvalue

n : band index

\mathbf{k} : wave number

σ : spin index ($\sigma = \uparrow, \downarrow$)

Band dispersion

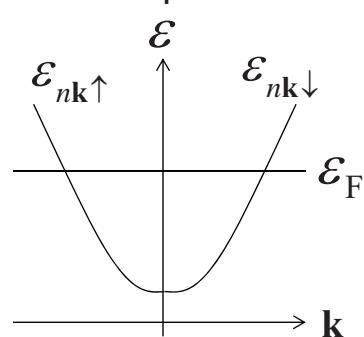


Ferromagnet(F)

$$\epsilon_{n\mathbf{k}\uparrow} \neq \epsilon_{n\mathbf{k}\downarrow}$$

Anti-Ferromagnet(AF)

$$\epsilon_{n\mathbf{k}\uparrow} = \epsilon_{n\mathbf{k}\downarrow}$$

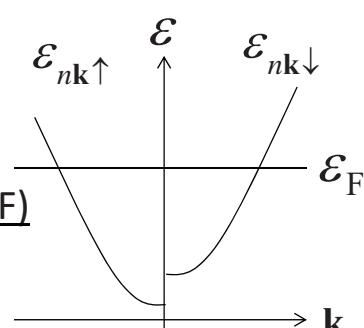

3

(5-1-2) Electronics structure: Density of states


Density of states(DOS)

$$n(\mathbf{r}) = \sum_{\sigma} \sum_{n\mathbf{k}} \delta(\epsilon - \epsilon_{n\mathbf{k}\sigma})$$

$$n_{\sigma}(\mathbf{r}) = \sum_{n\mathbf{k}} \delta(\epsilon - \epsilon_{n\mathbf{k}\sigma})$$

σ : spin index ($\sigma = \uparrow, \downarrow$)


Spin-up state Spin-down state

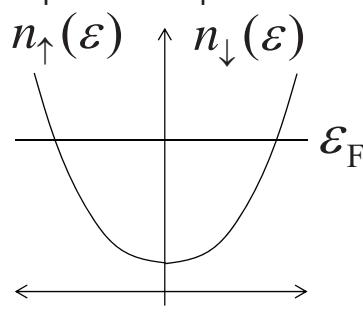

[states/(energy unit)/cell]


Ferromagnet(F)

Majority spin state Minority spin state

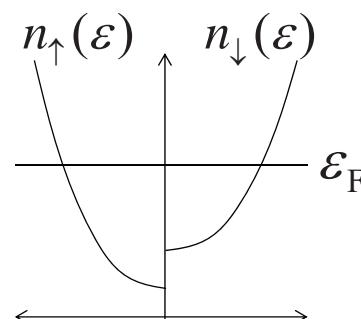

Effective potential
 $V(\mathbf{r})$

Anti-Ferromagnet(AF)

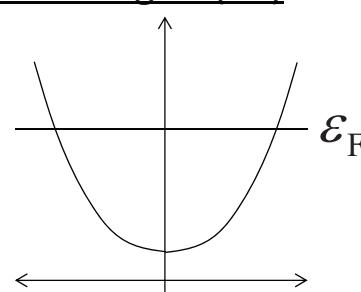

4

(5-2) Magnetic moment: spin, orbital, localized and itinerant


Origin of magnetism Most of magnetism in materials comes from the electrons which are contained.

electron : spin angular momentum


like being supposed to rotate on its own axis

$$\frac{1}{2} \hbar$$

two different spin states in an electron,
different energy levels
for external magnetic field

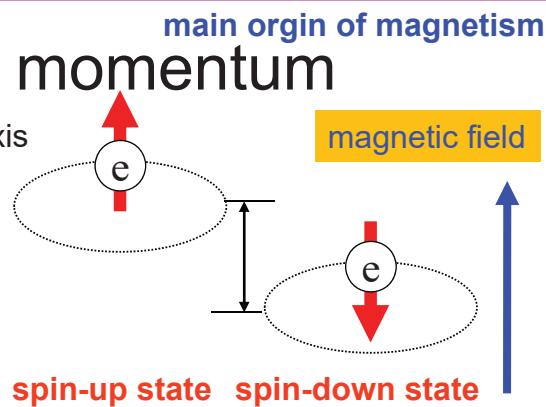

note) The orbital angular momentum appears from the orbit motion of electrons



$$0, \hbar, 2\hbar, \dots$$

(5-2-2) Orbital magnetic moment

Coulomb gauge
 $\vec{\nabla} \cdot \vec{A} = 0$

An electron in a magnetic field along z-axis

$$\begin{aligned} \mathcal{H} &= \frac{1}{2m} \left(\vec{p} + \frac{e}{c} \vec{A} \right)^2 + V(\vec{r}) & \vec{p} &= -i\hbar \vec{\nabla} & \vec{A} &= \frac{1}{2} H \left(-y \vec{e}_x + x \vec{e}_y \right) \\ \mathcal{H} &= -\frac{\hbar^2}{2m} \nabla^2 + \frac{e\hbar H}{2imc} \left(x \frac{\partial}{\partial y} - y \frac{\partial}{\partial x} \right) + \frac{e^2 H^2}{8mc^2} (x^2 + y^2) + V(\vec{r}) & (e > 0) \\ -\frac{\partial \mathcal{H}}{\partial H} &= -\frac{e}{2mc} \left(x \frac{\hbar}{i} \frac{\partial}{\partial y} - y \frac{\hbar}{i} \frac{\partial}{\partial x} \right) - \frac{e^2 H}{4mc^2} (x^2 + y^2) & \rightarrow -\mu_B \vec{\ell} \cdot \vec{H} = -\vec{\mu}_{\ell} \cdot \vec{H} \end{aligned}$$

$$\vec{\mu}_{\ell} = -\frac{e\hbar}{2mc} \vec{\ell} = -\mu_B \vec{\ell}$$

orbital magnetic moment

$$\frac{\ell}{\hbar} \rightarrow \ell$$

$$\mu_d = -\frac{e^2 H}{4mc^2} (x^2 + y^2)$$

$$\mu_d = -\frac{e^2 H}{4mc^2} \langle x^2 + y^2 \rangle = -\frac{e^2 H}{6mc^2} \langle r^2 \rangle$$

diamagnetic moment

(5-2-3) Spin magnetic moment

Spin angular momentum

Stern-Gerlach, anomalous Zeeman's effect,

Doublet of the D-line in sodium

Zeeman's energy term in Dirac equation

$$\frac{\hbar e}{2mc} \vec{\sigma} \cdot \vec{H} = \mu_B 2 \vec{s} \cdot \vec{H} = g \mu_B \vec{s} \cdot \vec{H}$$

spin angular momentum $\vec{\mu}_s = -g\mu_B \vec{s}$ $\frac{s}{\hbar} \rightarrow s$

$$s_z |m_s\rangle = \begin{cases} \frac{\hbar}{2} |m_s\rangle & m_s = \frac{\hbar}{2} \\ -\frac{\hbar}{2} |m_s\rangle & m_s = -\frac{\hbar}{2} \end{cases} \quad (\vec{s})^2 = s(s+1)$$

Contribution from the i 'th electron $\vec{\mu}_i = -(2\vec{s}_i + \vec{\ell}_i)\mu_B$

7

Dirac equation (as a reference, see Appendix 4)

$$\left\{ p_0 + \frac{e}{c} A_0 - \rho_1 \left(\vec{\sigma}, \vec{p} + \frac{e}{c} \vec{A} \right) - \rho_3 mc \right\} \Psi = 0$$

$$p_0 = i\hbar \frac{\partial}{\partial(ct)} \quad \rho_1, \rho_3, \sigma \quad \text{4} \times \text{4 matrixes}$$

$$\vec{p} = -i\hbar \frac{\partial}{\partial \vec{r}} \quad \rho_1 = \begin{pmatrix} 0 & 1 \\ 1 & 0 \end{pmatrix} \quad \rho_2 = \begin{pmatrix} 0 & i \\ i & 0 \end{pmatrix} \quad \rho_3 = \begin{pmatrix} \sigma_x & 0 \\ 0 & \sigma_x \end{pmatrix} \quad \sigma_1 = \begin{pmatrix} \sigma_y & 0 \\ 0 & \sigma_y \end{pmatrix} \quad \sigma_2 = \begin{pmatrix} \sigma_z & 0 \\ 0 & \sigma_z \end{pmatrix}$$

$$- eA_0 (\equiv V(\vec{r}))$$

A_0 scalar potential

\vec{A} vector potential

$$\Psi = \begin{pmatrix} \varphi_1 \\ \varphi_2 \\ \varphi_3 \\ \varphi_4 \end{pmatrix} = \begin{pmatrix} \varphi_L \\ \varphi_S \end{pmatrix} \quad \varphi_L = \begin{pmatrix} \varphi_1 \\ \varphi_2 \end{pmatrix} \quad \varphi_S = \begin{pmatrix} \varphi_3 \\ \varphi_4 \end{pmatrix}$$

8

(5-3) Zeeman energy

$$\left[\frac{1}{2m} \left(\vec{p} + \frac{e}{c} \vec{A} \right)^2 + V + \frac{\hbar e}{2mc} \vec{\sigma} \cdot \vec{H} \right] \vec{H} = \vec{\nabla} \times \vec{A}$$

Zeeman energy

$$+ \frac{\hbar}{4m^2 c^2} \vec{\sigma} \cdot \left\{ (\text{grad } V) \times \left(\vec{p} + \frac{e}{c} \vec{A} \right) \right\}$$

Spin-orbit interaction

$$+ \frac{\hbar^2}{8m^2 c^2} \text{div} (\text{grad } V) \right] \varphi_L = (\varepsilon - mc^2) \varphi_L$$

Darwin term

$\varphi_L = \begin{pmatrix} \varphi_1 \\ \varphi_2 \end{pmatrix}$ Wave function of
2-component spinor

9

(5-4) Distance and interaction between magnetic carriers, magnetic and crystal structures

Magnetic dipole term in Breit's interaction

$$E_{\text{Breit}}^{\text{magnetic dipole}} = \frac{e^2}{4m^2 c^2} \frac{\vec{\sigma}_1 \cdot \vec{\sigma}_2 - 3(\vec{\sigma}_1 \cdot \hat{\mathbf{r}}_{12})(\vec{\sigma}_2 \cdot \hat{\mathbf{r}}_{12})}{r_{12}^3}$$

Interaction between atomic magnetic moments


$$E_{ij}^{\text{dipole}} = \frac{e^2}{4m^2 c^2} \frac{\vec{\mu}_i \cdot \vec{\mu}_j - 3(\vec{\mu}_i \cdot \hat{\mathbf{R}}_{ij})(\vec{\mu}_j \cdot \hat{\mathbf{R}}_{ij})}{R_{ij}^3}$$

10

(5-4-2) Magnetic dipole-dipole interaction (MDDI)

Classical magnetic interaction

$$E_{ij}^{\text{dipole}} = \frac{\boldsymbol{\mu}_i \cdot \boldsymbol{\mu}_j - 3(\boldsymbol{\mu}_i \cdot \hat{\mathbf{R}}_{ij})(\boldsymbol{\mu}_j \cdot \hat{\mathbf{R}}_{ij})}{R_{ij}^3}$$

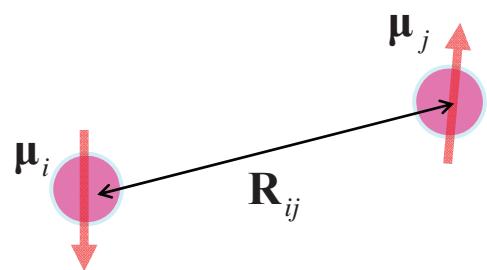

$$\begin{aligned} & -\frac{2\mu_i\mu_j}{R_{ij}^3} \quad \text{Total energy} \\ & + \frac{2\mu_i\mu_j}{R_{ij}^3} \quad \text{Parallel component} \\ & + \frac{\mu_i\mu_j}{R_{ij}^3} \quad \text{Antiparallel component} \\ & - \frac{\mu_i\mu_j}{R_{ij}^3} \quad \text{Perpendicular component} \end{aligned}$$

11


(5-4-3) MDDI: Ferromagnetic 1D-chain and 2D-square lattice

➤ 1D-chain

$$E_{dd}(\theta) = \frac{e^2}{4m^2c^2} \frac{C_M \mu^2}{a^3} \left(\frac{3}{2} \cos^2 \theta - \frac{1}{2} \right) \quad C_M = 4.804$$

μ : Magnetic moment in μ_B

$$E_{dd}(\theta)[\text{Ryd}] \quad m = e = 1 \quad c = 137. \quad a : \text{Lattice constant in } a_B$$

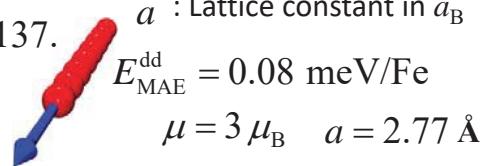


➤ 2D-dimensional case

2D Madelung constant approach

Ref.) L. Szunyogh et al., Phys. Rev. B, **51**, 9552, (1995)

2D square lattice



$$E_{\text{MAE}}^{\text{dd}} = 0.15 \text{ meV/Fe}$$

$$\mu = 3.1 \mu_B$$

$$E_{dd}(\theta) = \frac{e^2}{4m^2c^2} \frac{C_M \mu^2}{a^3} \left(\frac{3}{2} \cos^2 \theta - \frac{1}{2} \right) \quad C_M = 9.03362$$

$$a = 2.87 \text{ \AA}$$


$$E_{dd}(\theta)[\text{Ryd}] \quad m = e = 1 \quad c = 137.$$

$$\mu : \text{Magnetic moment in } \mu_B$$

$$a : \text{Lattice constant in } a_B$$

12

(5-4-4) MDDI: Antiferromagnetic 2D-square lattice

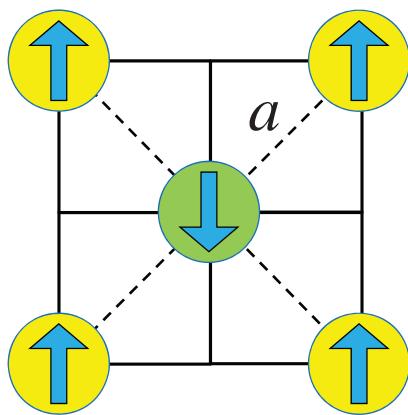

Perpendicular anisotropy

$$E_{\text{MAE}}^{\text{dd}} = -0.082 \text{ meV/Mn}$$

$$\mu = 4.2 \mu_B$$

$$a = 2.83 \text{ \AA}$$

Note)

$$E_{\text{MAE}}^{\text{dd}} = -0.175 \text{ meV/Mn (SDA)}$$

SDA: Spin density approach (see Appendix 7)

TO, I. Paredede et al, IEEE Trans. Magn., 55(2), Art. Num. 1300104, (2019).

13

(5-5) Spin-orbit interaction

$$H_{\text{SOI}} = \frac{\hbar}{4m^2c^2} \vec{\sigma} \cdot (\underline{\text{grad } V(\vec{r})} \times \vec{p}) \quad \vec{\sigma} \text{ Pauli's matrix}$$

$$V(\mathbf{r}) \approx -\frac{Ze^2}{r} \quad \text{grad } V(r) \approx \frac{dV}{dr} \frac{\mathbf{r}}{r}$$




The effect is emphasized at surface/interface: becoming not spherical.

$$H_{\text{SOI}} = \xi \vec{\ell} \cdot \vec{\sigma} = \xi (\ell_x \sigma_x + \ell_y \sigma_y + \ell_z \sigma_z)$$

$$\xi(r) = \frac{\hbar^2}{4m^2c^2r} \frac{dV}{dr} \quad \text{connects orbital and spin spaces}$$

²
Biot-Savart law
in the classical
electromagnetics
spin-orbit interaction

$$E_{\text{SO}}^j = \lambda \vec{\ell} \cdot \vec{s} = \frac{\lambda}{2} \{ j(j+1) - s(s+1) - \ell(\ell+1) \}$$

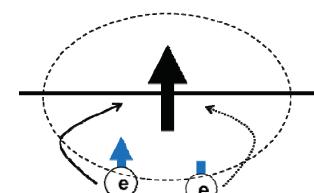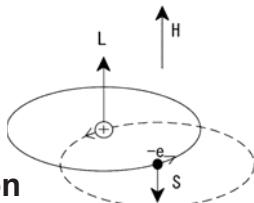

Due to the surface/interface
the inversion symmetry breaks.

→ Rashba effect, etc.


14

(5-5-2) Spin-texture in the reciprocal space: Rashba effect 1

2 dimensional free electron with spin-orbit interaction

$$H = -\frac{\hbar^2}{2m} \nabla^2 + \vec{\sigma} \cdot (\vec{\alpha} \times \vec{p}) \quad \vec{\alpha} \propto \left\langle \text{grad } V(r) = \frac{1}{r} \frac{dV(r)}{dr} \mathbf{r} \right\rangle$$

Plane wave $\varphi_{\vec{k}} = \frac{1}{\sqrt{\Omega}} e^{i\vec{k} \cdot \vec{r}} \begin{pmatrix} u_1 \\ u_2 \end{pmatrix} \propto \vec{e}_z$



$$H = \frac{\hbar^2 k^2}{2m} + \vec{\sigma} \cdot (\vec{\alpha} \times \vec{k}) = \frac{\hbar^2 k^2}{2m} + \alpha_z (\vec{k} \times \vec{\sigma})_z$$

$$= \frac{\hbar^2 k^2}{2m} + \alpha_z (k_x \sigma_y - k_y \sigma_x) \quad \vec{k} = (k_x, k_y) \quad k = \sqrt{k_x^2 + k_y^2}$$

$$E_+ = \frac{\hbar^2 k^2}{2m} + \alpha_z k \quad \varphi_{\vec{k}}^+ = \frac{1}{\sqrt{\Omega}} e^{i\vec{k} \cdot \vec{r}} \frac{1}{\sqrt{2}} \begin{pmatrix} -1 \\ -ie^{i\theta_k} \end{pmatrix} \propto \frac{1}{\sqrt{2}} \begin{pmatrix} e^{-i(\theta_k + \pi/2)/2} \\ e^{i(\theta_k + \pi/2)/2} \end{pmatrix}$$



$$E_- = \frac{\hbar^2 k^2}{2m} - \alpha_z k \quad \varphi_{\vec{k}}^- = \frac{1}{\sqrt{\Omega}} e^{i\vec{k} \cdot \vec{r}} \frac{1}{\sqrt{2}} \begin{pmatrix} 1 \\ -ie^{i\theta_k} \end{pmatrix} \propto \frac{1}{\sqrt{2}} \begin{pmatrix} -e^{-i(\theta_k + \pi/2)/2} \\ e^{i(\theta_k + \pi/2)/2} \end{pmatrix}$$

(5-5-3) Spin-texture in the reciprocal space: Rashba effect 2

$$\langle \varphi_{\vec{k}}^+ | \vec{\sigma} | \varphi_{\vec{k}}^+ \rangle = (-\sin \theta_k, \cos \theta_k, 0)$$

$$\langle \varphi_{\vec{k}}^- | \vec{\sigma} | \varphi_{\vec{k}}^- \rangle = (\sin \theta_k, -\cos \theta_k, 0)$$

$$E_{\pm} = \frac{\hbar^2}{2m} \left(k \pm \frac{m\alpha_z}{\hbar^2} \right)^2 - \frac{\hbar^2}{2m} \left(\frac{m\alpha_z}{\hbar^2} \right)^2$$

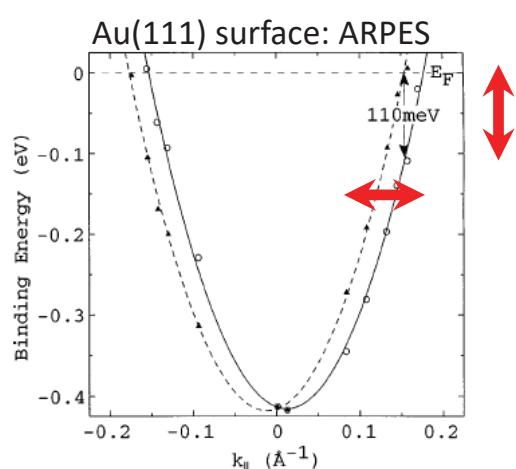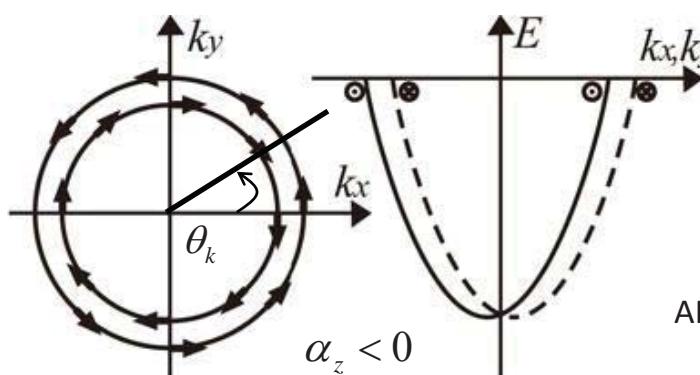

➤ High resolution

Lashell et al., Phys. Rev. Lett. 77, 3419 (1996)

ARPES: Angle Resolved Photoelectron Spectroscopy

(5-5-4) Spin-orbit interaction 2

$$H_{\text{SOI}} = \frac{\hbar}{4m^2c^2} \vec{\sigma} \cdot \left((\vec{\nabla}V(\vec{r})) \times \vec{p} \right)$$

$$= \frac{\hbar}{4m^2c^2} \left\{ \left(-\frac{\partial V}{\partial z} \right) (\sigma_x p_y - \sigma_y p_x) + \sigma_z \left(\frac{\partial V}{\partial x} p_y - \frac{\partial V}{\partial y} p_x \right) + \left(\sigma_x \frac{\partial V}{\partial y} - \sigma_y \frac{\partial V}{\partial x} \right) p_z \right\}$$

Normal Rashba term
General Rashba term
Effective in-plane potential gradient

Spin-orbit interaction (Rashba term + damping rate term)

17

(5-5-5) Interpretation of Spin-orbit interaction

$$H_{\text{SOI}} = \frac{\hbar}{4m^2c^2} \vec{\sigma} \cdot \left((\vec{\nabla}V(\vec{r})) \times \vec{p} \right)$$


$$H_{\text{SOI}} = 2 \frac{\hbar e}{2mc} \frac{\vec{\sigma}}{2} \cdot \left\{ \frac{1}{2mce} (\vec{\nabla}V(\vec{r})) \times \vec{p} \right\} = 2\mu_B \frac{\vec{\sigma}}{2} \cdot \left\{ \frac{1}{2mce} (\vec{\nabla}V(\vec{r})) \times \vec{p} \right\}$$

Bohr magneton
Effective magnetic field

$$H_{\text{SOI}} = \frac{\hbar}{4m^2c^2} \{ \vec{\sigma} \times \vec{\nabla}V(\vec{r}) \} \cdot \vec{p} = \frac{\hbar}{m} \frac{1}{4mc^2} \{ \vec{\sigma} \times \vec{\nabla}V(\vec{r}) \} \cdot \vec{p}$$

$$H_{\text{SOI}} = -e \frac{\hbar}{4m^2c^2} (\vec{\sigma} \times \vec{p}) \cdot \frac{1}{e} \vec{\nabla}V(\vec{r})$$

Effective electric dipole
Electric field
Effective wave number




(5-5-6) Electric field effects in electronic structures of the surface/interface

- Stark effect

$$H_{\text{ED}} = -e \vec{r} \cdot \vec{E}_{\text{ext}}$$

Electric dipole

Orbital coupling between the states of different angular quantum number $\Delta\ell = \pm 1$.



- Rashba (SOI) effect

$$H_{\text{SOI}} = -e \frac{\hbar}{4m^2c^2} (\vec{\sigma} \times \vec{p}) \cdot \vec{E}_{\text{ext}}$$

Modification of the Rashba effect.

- Electron depletion (accumulation)

When imposing the EF, for PDOS ~ 1 states/eV

Induced change in the number of electrons ~ 0.01 ~ 0.01 eV

Induced change in the number of electrons ~ 0.1 ~ 0.1 eV


by lattice constant, or modification surface/interface, etc.

19

(5-6) Spin transfer torque

Spin current \longrightarrow **Spin torque provided to free layer**
produced in fixed layer

$$N_{\text{stt}} = \frac{d\vec{M}_{\text{free}}}{dt} \propto -I_s \vec{M}_{\text{free}} \times (\vec{M}_{\text{free}} \times \vec{M}_{\text{fix}})$$

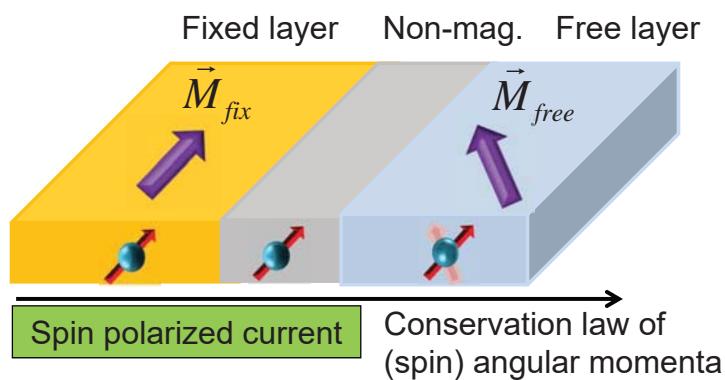

(5-7) Magnetic anisotropy energy: electron orbital, magnet shape

Magnetostatic contribution


$$E_{\text{d-d}} = \frac{1}{c^2} \sum_{R_i, R_j}^{i \neq j} \left\{ \frac{\vec{m}(R_i) \cdot \vec{m}(R_j)}{R_{ij}^3} - 3 \frac{[\vec{m}(R_i) \cdot (\vec{R}_i - \vec{R}_j)] [\vec{m}(R_j) \cdot (\vec{R}_i - \vec{R}_j)]}{R_{ij}^5} \right\}$$

in-plane contribution
2D square lat.
Shape aniso.


This depends on the arrangement of magnetic atoms, not so depend on electric field.

Electronic structure contribution

perturbation of spin-orbit interaction,
MA appears from an anisotropy of orbitals


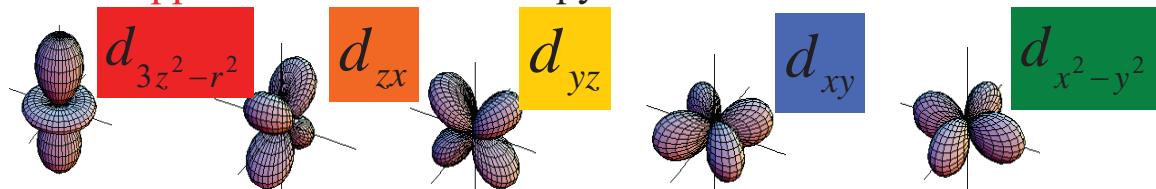


It is important to see the behavior of each angular orbitals.
Anisotropic occupation of electrons leads to MA.

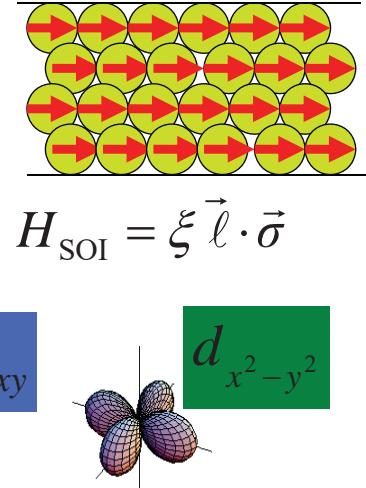

21

MAE from d-d interaction for Fe-multilayers

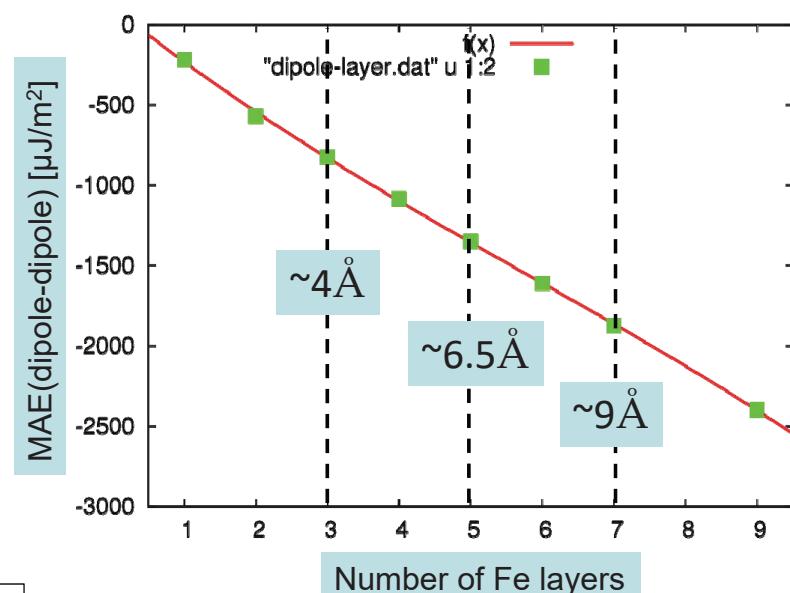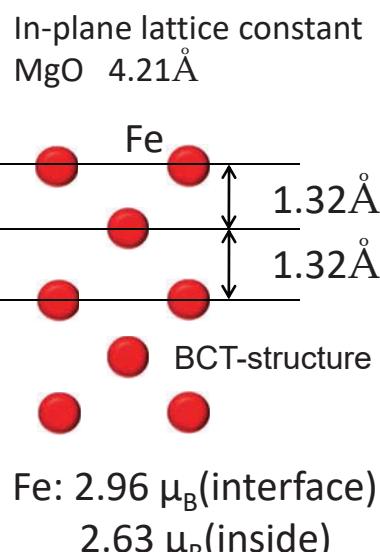

FeCo layer
> 6.3 Å in-plane
< 6.3 Å out-of-plane
Y. Shiota et. al., Appl. Phys. Exp., 4, 043305(2011).

In-plane MAE increases
by 250-300 $\mu\text{J}/\text{m}^2$ per Fe-layer
Ref.) L. Szunyogh et al., Phys. Rev. B, 51, 9552, (1995)


Origin of MAE in electronic structure

$$H_{\text{SOI}} = \xi \vec{\ell} \cdot \vec{\sigma}$$


- spin-orbit coupling contribution from band electrons

(A) 2nd perturbative contributions

$$\text{MAE} = E_x - E_z \approx (\xi)^2 \sum_{o,u} \frac{\left| \langle o_\downarrow | \ell_z | u_\downarrow \rangle \right|^2 - \left| \langle o_\downarrow | \ell_x | u_\downarrow \rangle \right|^2}{\epsilon_u^\downarrow - \epsilon_o^\downarrow}$$

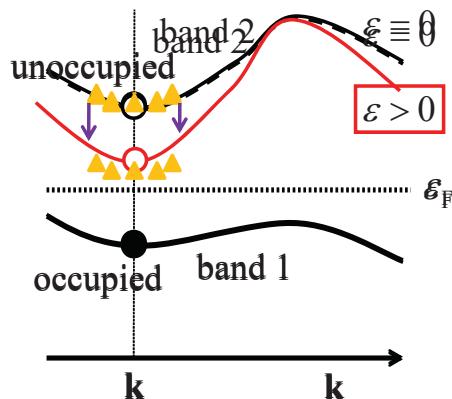

	matrix element
z	$\langle xz \ell_z yz \rangle = 1$ $\langle x^2 - y^2 \ell_z xy \rangle = 2$
x	$\langle 3z^2 - r^2 \ell_x yz \rangle = \sqrt{3}$ $\langle xy \ell_x xz \rangle = 1$ $\langle x^2 - y^2 \ell_x yz \rangle = 1$
y	$\langle 3z^2 - r^2 \ell_y xz \rangle = \sqrt{3}$ $\langle xy \ell_y yz \rangle = 1$ $\langle x^2 - y^2 \ell_y xz \rangle = 1$

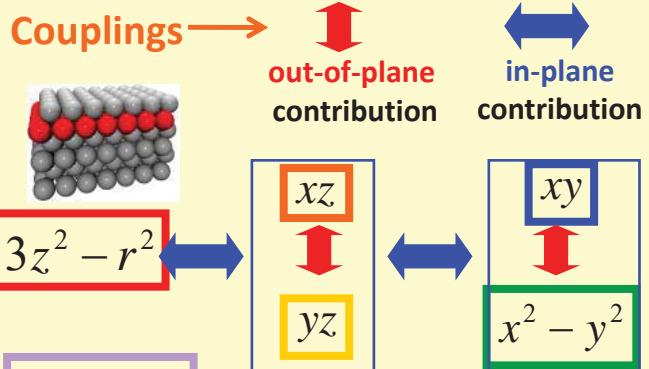

(B) Existence of partly-occupied degenerate levels

$$\xi m \cos \theta$$


Low dimensional system D. S. Wang, R. Wu, and A. J. Freeman, Phys. Rev. B 47, 14932 (1993).





example: Isolated iron chain

- MAE=3.23 meV/Fe
- Easy axis: parallel to the chain-axis (z direction).


red: mag. perpendicular to the axis
blue: mag. parallel to the axis

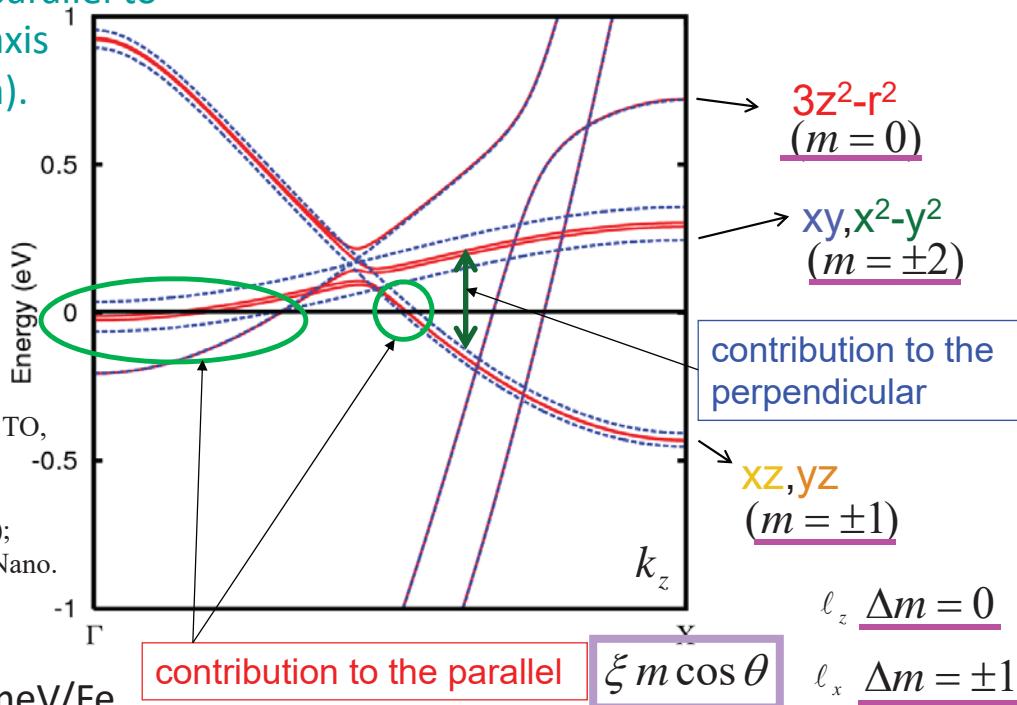

(5-8) Magnetic anisotropy: in-plane, perpendicular

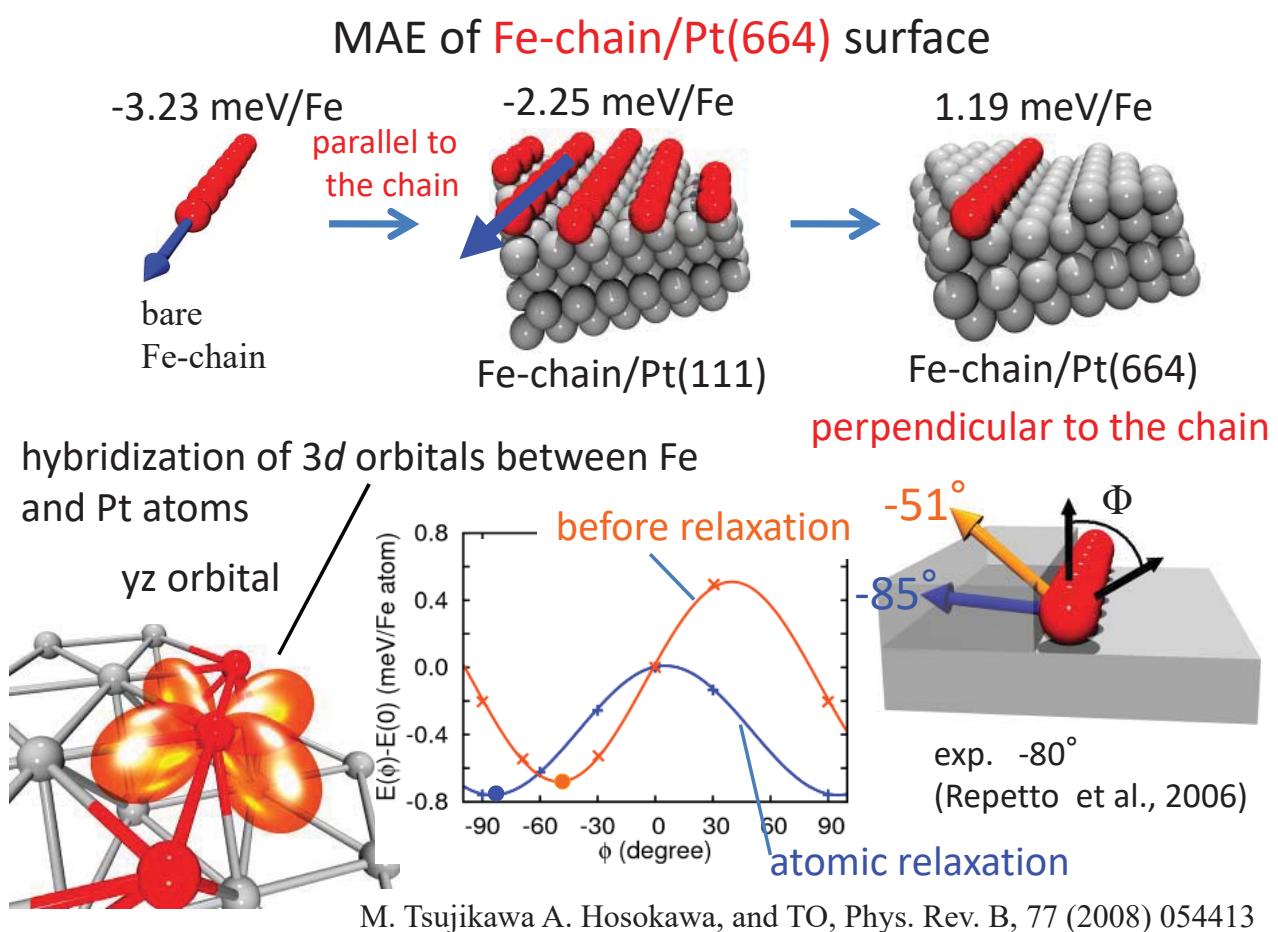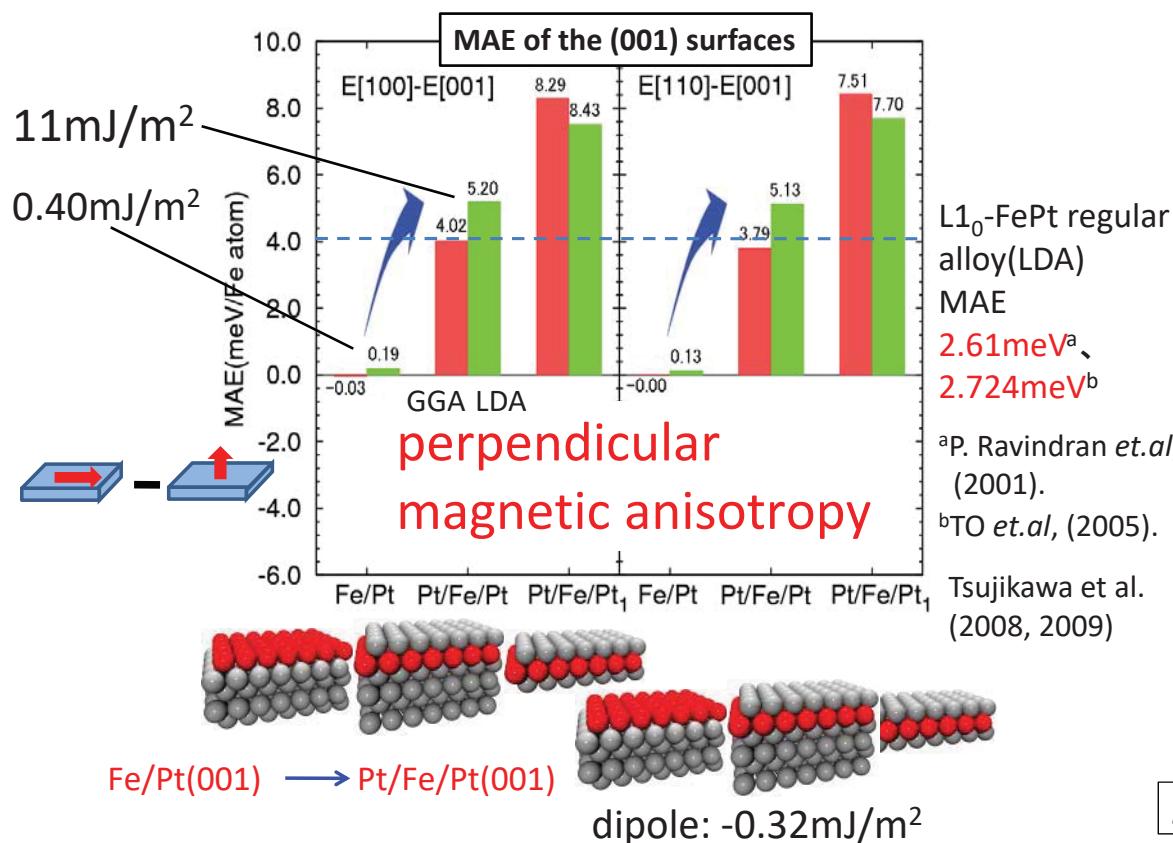

Trade-off property in magnetic memory

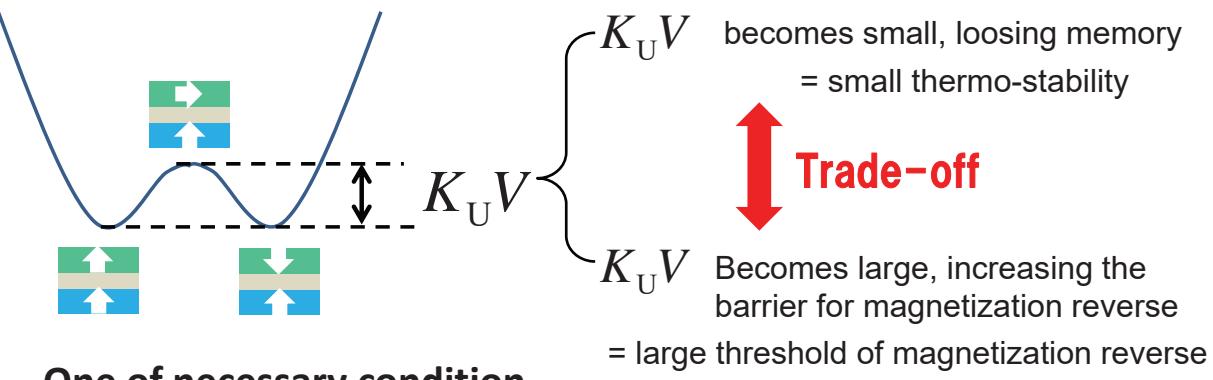

Non-volatile

$$\Delta \geq 60 \quad (\text{ten years}) \quad \Delta = \frac{K_U V}{k_B T}$$

Magnetic anisotropy energy of magnetic memory


K_U Magnetic anisotropy energy per volume

V Volume of magnet

Heat energy

27


Driving forces in dynamical control of magnetization

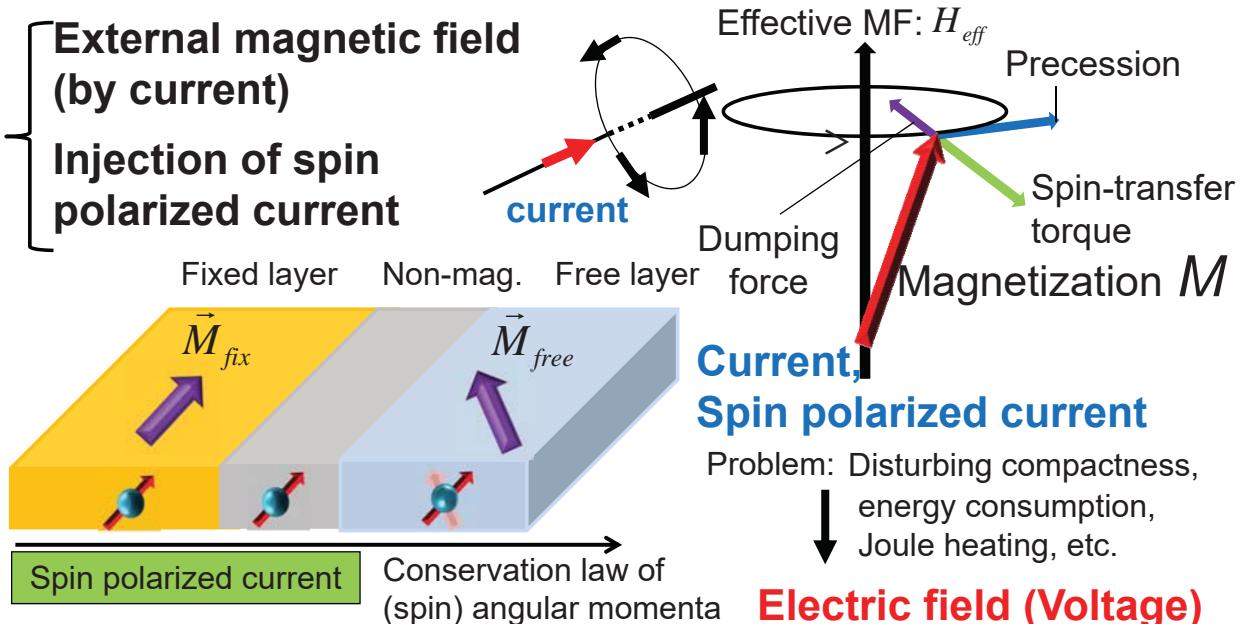

$$\vec{H}_{eff} = \vec{H}_{ext} + \vec{H}_{stt} + \vec{H}_{shape} + \vec{H}_{aniso}$$


Expectation: ultra-low energy consumption, non-volatile property, compactness(high density memory), enough high speed in reading&writing

Schematic diagram of magnetization reversal in imposing electric field

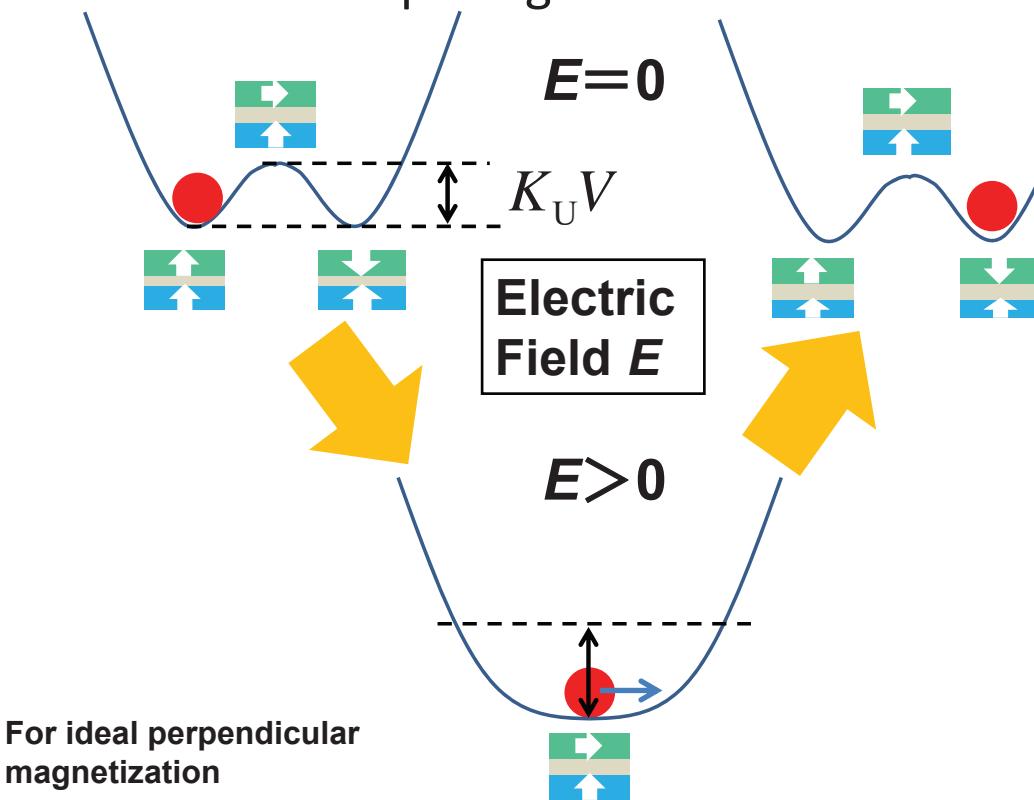

29

(5-9) Voltage-induced spin torque

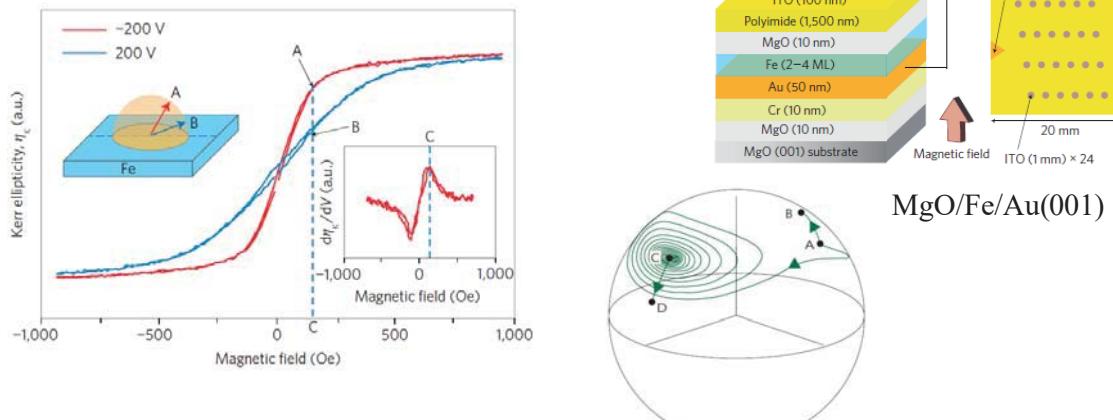


$$\frac{d\vec{M}}{dt} = \gamma \vec{M} \times \vec{H}_{eff} + \frac{\alpha \vec{M}}{M_s} \times \frac{d\vec{M}}{dt} \quad \vec{H}_{eff} = -\frac{1}{\mu_0 M_s} \vec{\nabla} E_{mag}$$

$$E_{mag} = -\mu_0 M_z H_{ext} + \frac{1}{2} K_u (V) \left(\frac{M_z}{M_s} \right)^2 + \frac{1}{2} K_{||} \left(\frac{M_x}{M_s} \right)^2$$

T. Maruyama et. al., Nature Nanotech. 4, 158 (2009)

30


A1-5. Applying the electric field (EF) on iron chain

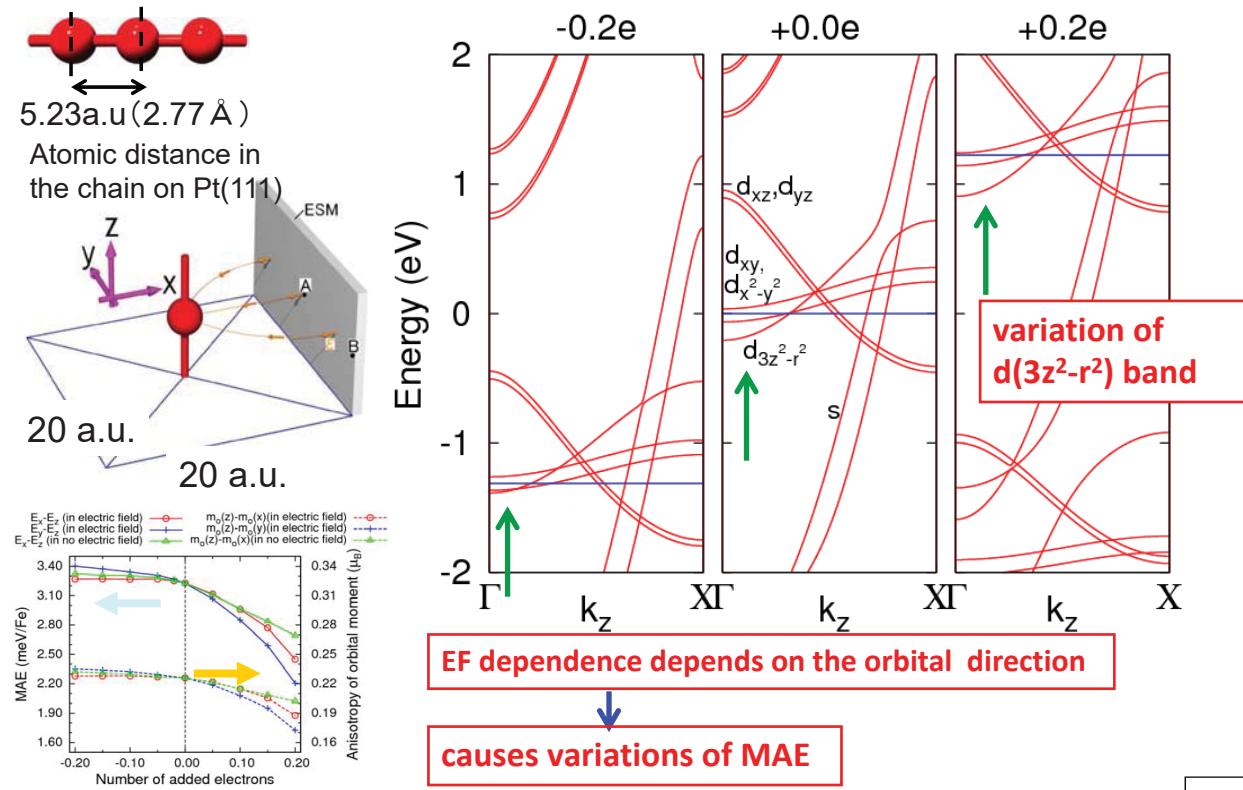

M. Tsujikawa and TO, J. Phys.: Condens. Matter, **21**, 064213 (2009)

31


A1-6. Imposing the electric field (EF) on iron chain (part 2)

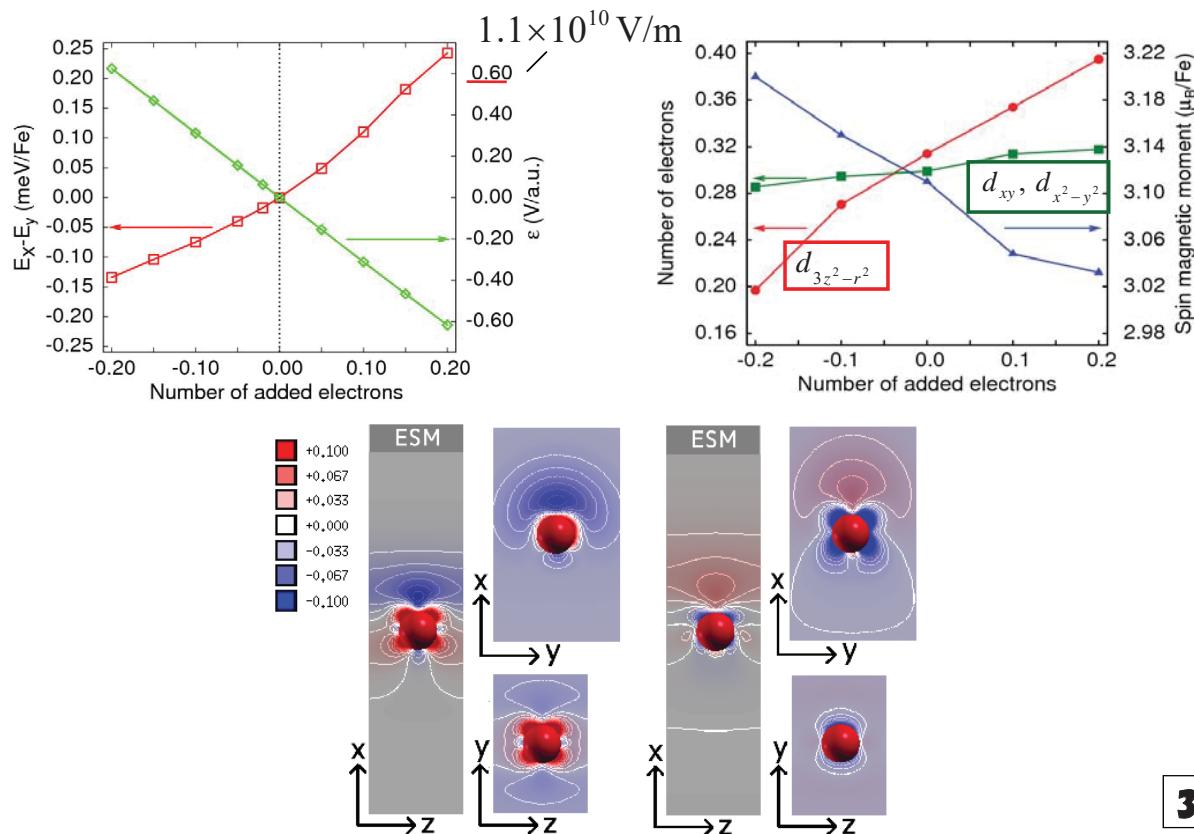

32

MAE and EF effects(comparison with exp.)


S. Haraguchi et. al., J. Phys. D: Appl. Phys. **44**, 064005 (2011). M. Weisheit et. al., Science **315**, 349 (2007).

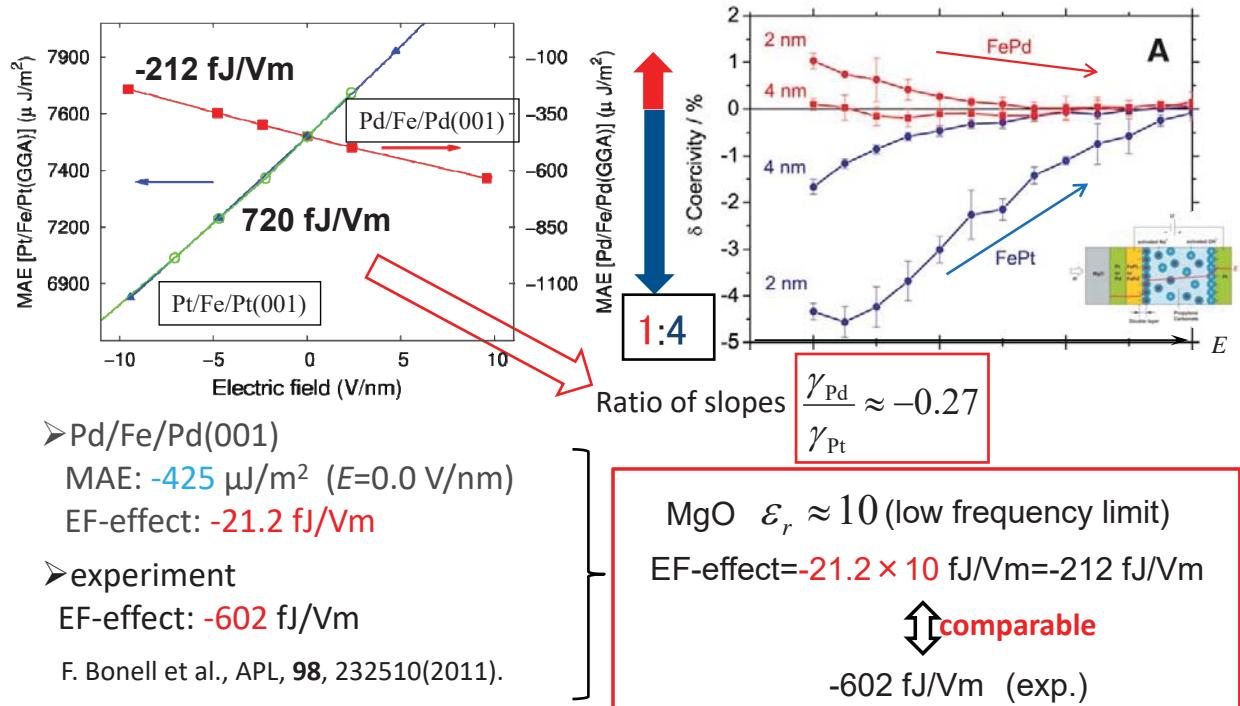

These signs of slopes and the ratio are in good qualitative agreement with the available experimental data.

33

EF-Induced modulation on density

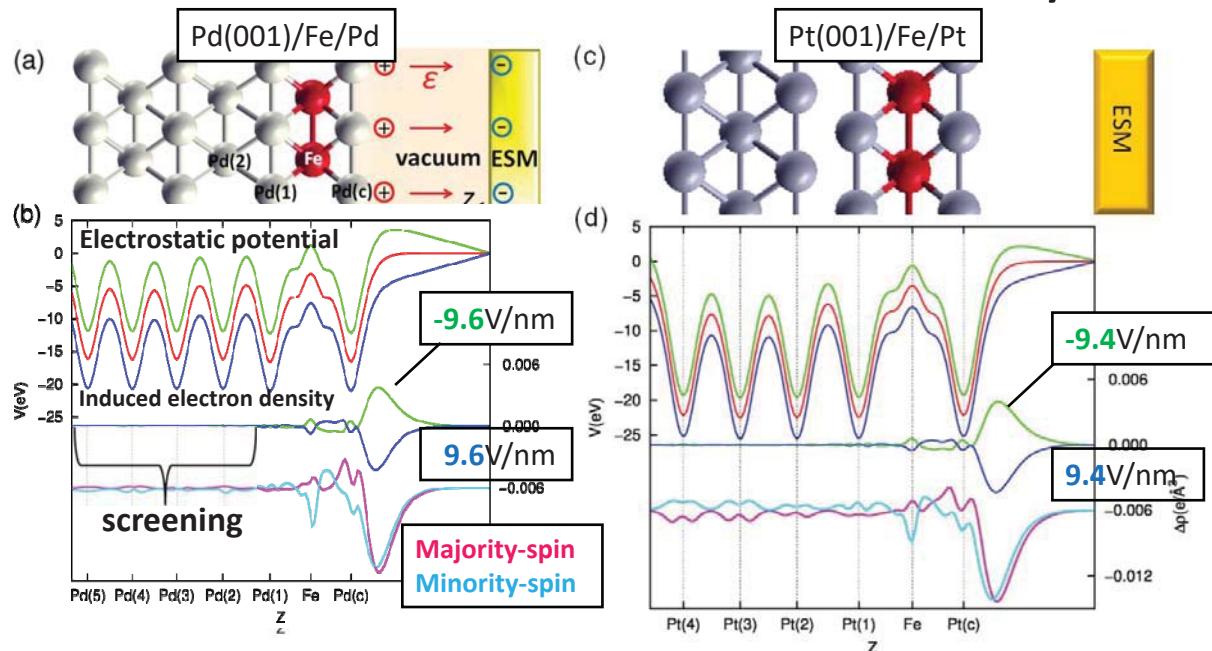


➤ The electric field is screened in a few number of surface layers.

➤ In these layers, EF effects are induced.


S. Haraguchi et. al., J. Phys. D: Appl. Phys. **44** (2011) 064005.

Effective Screening Medium(ESM method): Otani et al., PRB **73**,115407 (2006).



Electric field dependence of MAE in Pt(001)/Fe/Pt/MgO film

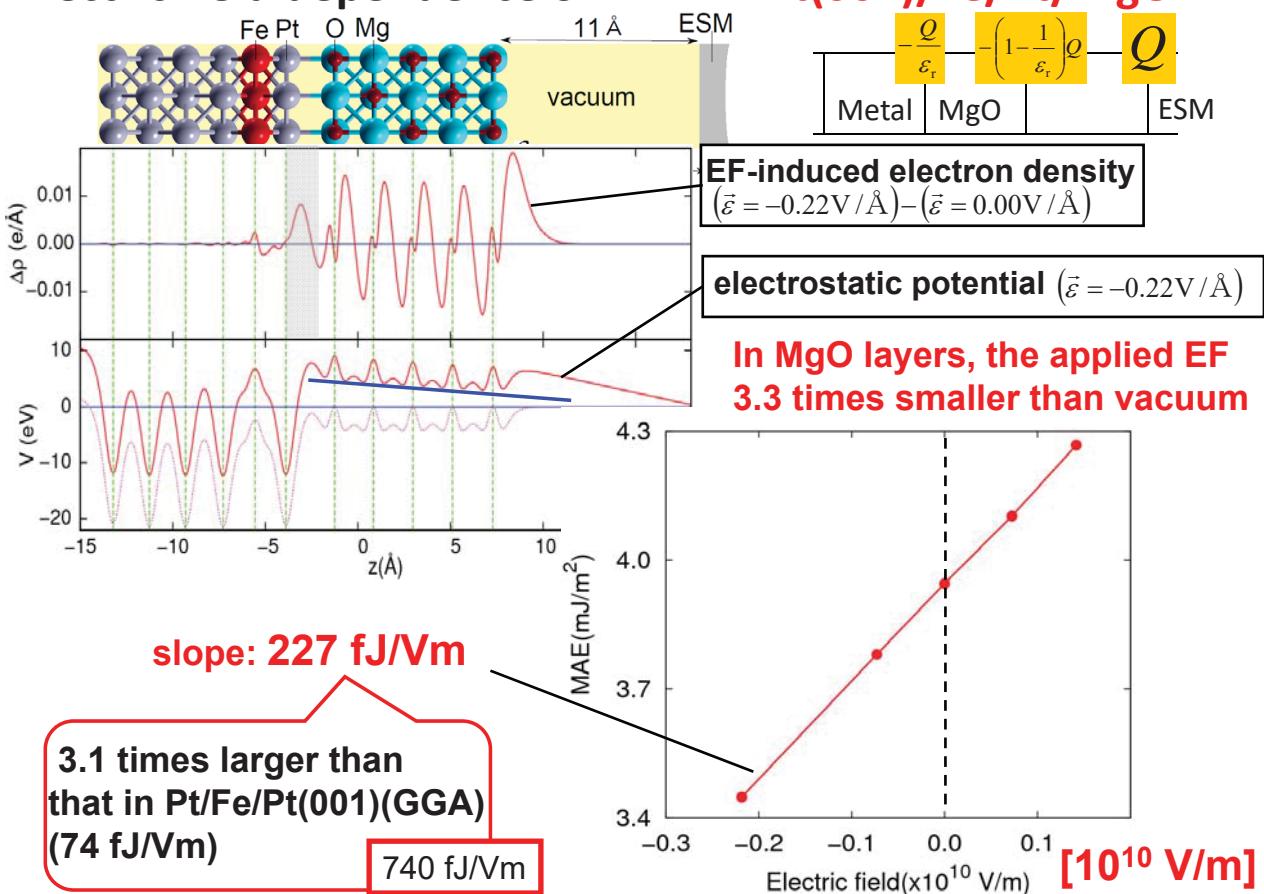


Interface: magnetic metal and dielectric insulator (Exp.)
magnetic anisotropy change by electric polarization switching

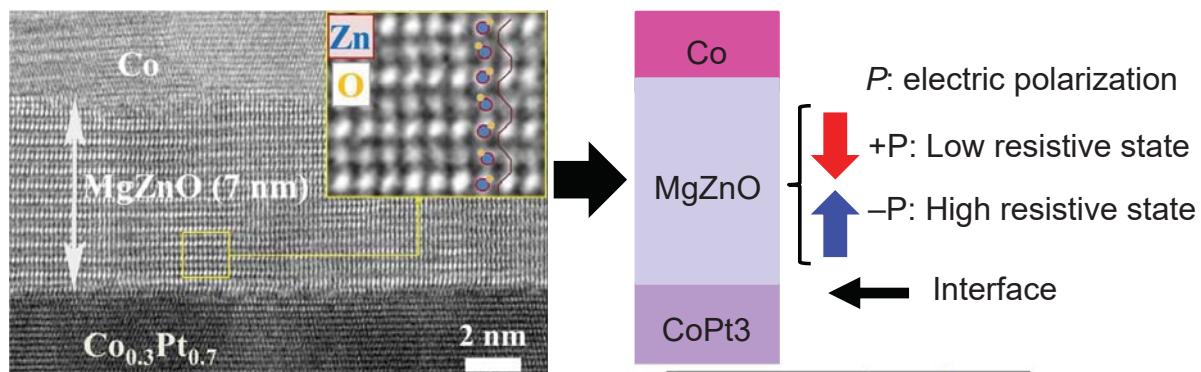

- Theory: "Multi-ferroic-like"
- Experiment: "New type MTJ"

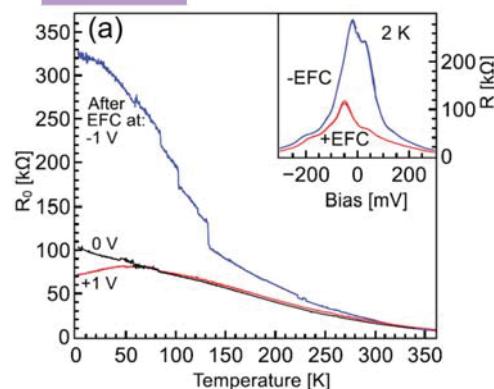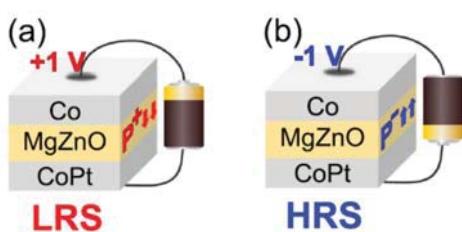

Interface: magnetic metal and dielectric insulator (DFT)

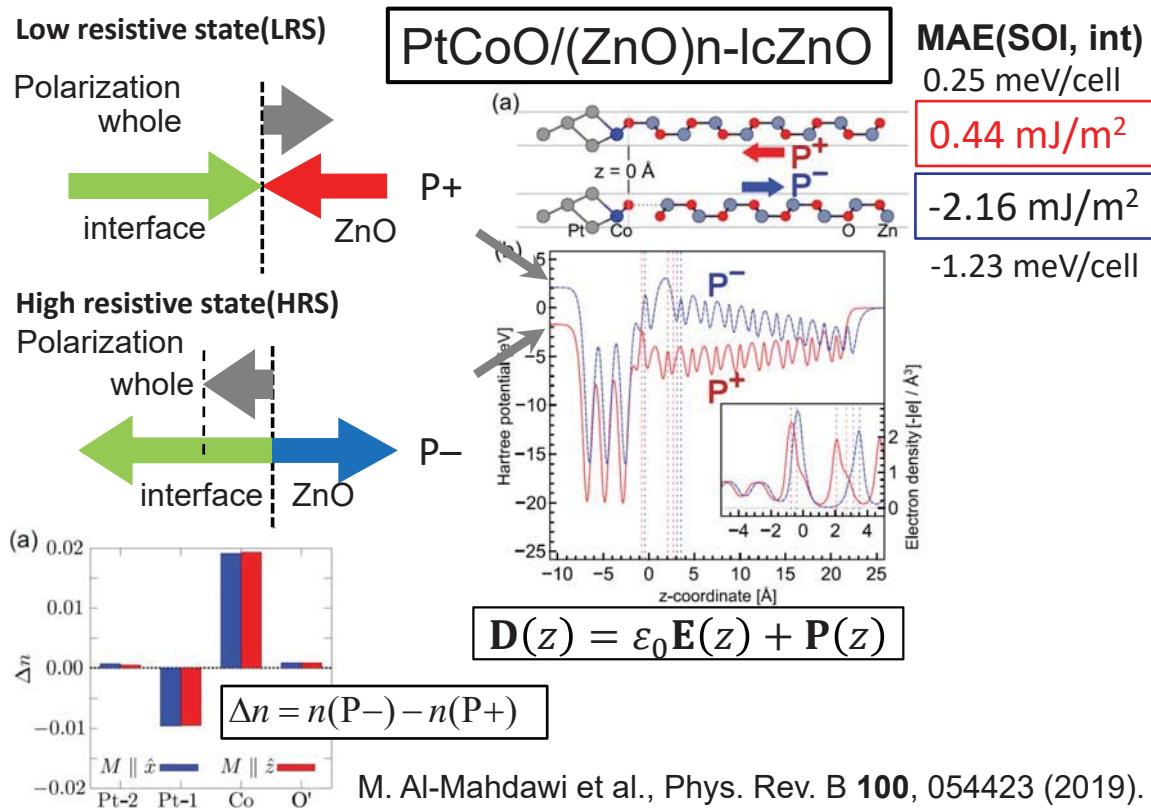

(5-10) Landau–Lifshitz–Gilbert equation (LLG-equation)

$$\frac{d\vec{M}}{dt} = -\gamma(\vec{M} \times \vec{H}_{\text{eff}}) + \frac{\alpha}{M_s} \vec{M} \times \frac{d\vec{M}}{dt} - \eta(\theta) \frac{\mu_B I}{eV} \frac{\vec{M}}{M_s} \times \left(\frac{\vec{M}}{M_s} \times \frac{\vec{M}_{\text{fix}}}{M_{\text{fix}}} \right)$$

precessional term

dumping term

spin transfer torque

\vec{M} :Magnetization vector at free layer α :Gilbert magnetic damping factor

γ :gyromagnetic factor


\vec{M}_{fix} :Magnetization vector at fixed layer

$\eta(\theta)$:spin transfer efficiency

$$\vec{H}_{\text{eff}} = \vec{H} + \vec{H}_{\text{shape}} + \vec{H}_{\text{cry-aniso}}$$

J. C. Slonczewski. Journal of Magnetism and Magnetic Materials 159(1996)L1-L7

Dynamics of the magnetization on the free layer

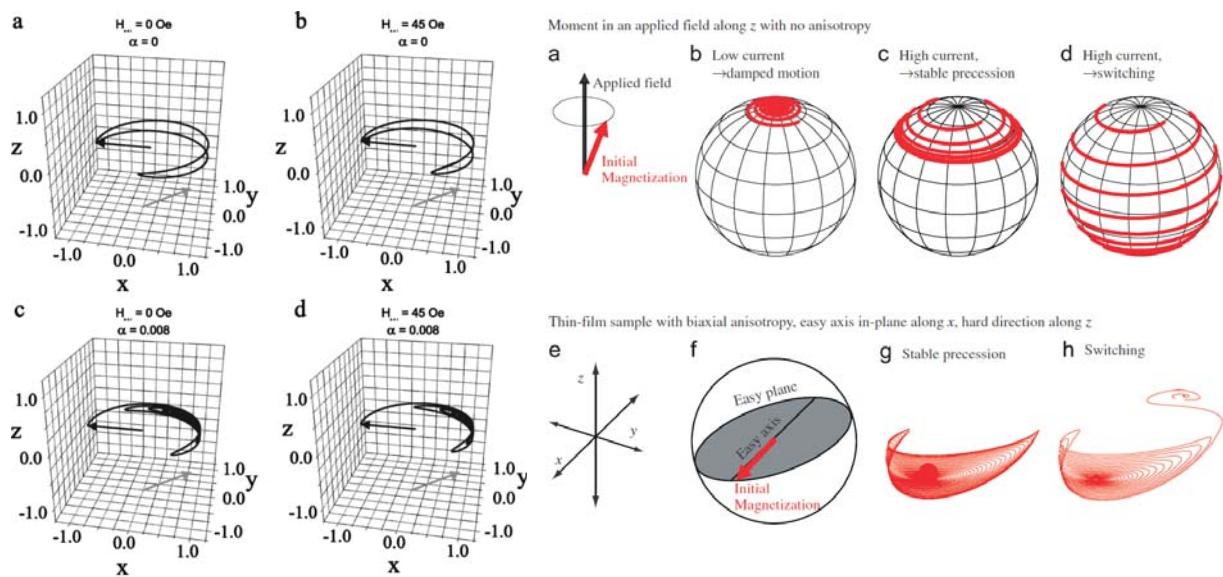

M. Bauer et al., Phy. Rev. B61, 3410-3416(2000)

D.C. Ralph, M.D. Stiles, J. Magn. Magn. Materials 320, 1190 (2008)

39

Shreshold current (derived from LLG equation)

$$I_c = \frac{2e}{\hbar} \frac{\alpha}{\eta(0)} V \mu_0 M_s \left(H + H_k + \frac{M_s}{2} \right) \propto \frac{\alpha}{\eta(0)} M_s$$

external anisotropy
 diamagnetism

V Free layer volume

α about 0.01


$$\eta(\theta) = \frac{q}{A + B \cos \theta} \quad \text{Anisotropy function}$$

θ : the angle between the directions of spin current and fixed magnetization M_s

Proto-type of the magnetic device for a voltage driven MRAM




Magnetization switching using voltage pulse

Y. Shiota, T. Nozaki, F. Bonell, S. Murakami, T. Shinjo and Y. Suzuki. Nat. Mat.. 11. 39(2012)

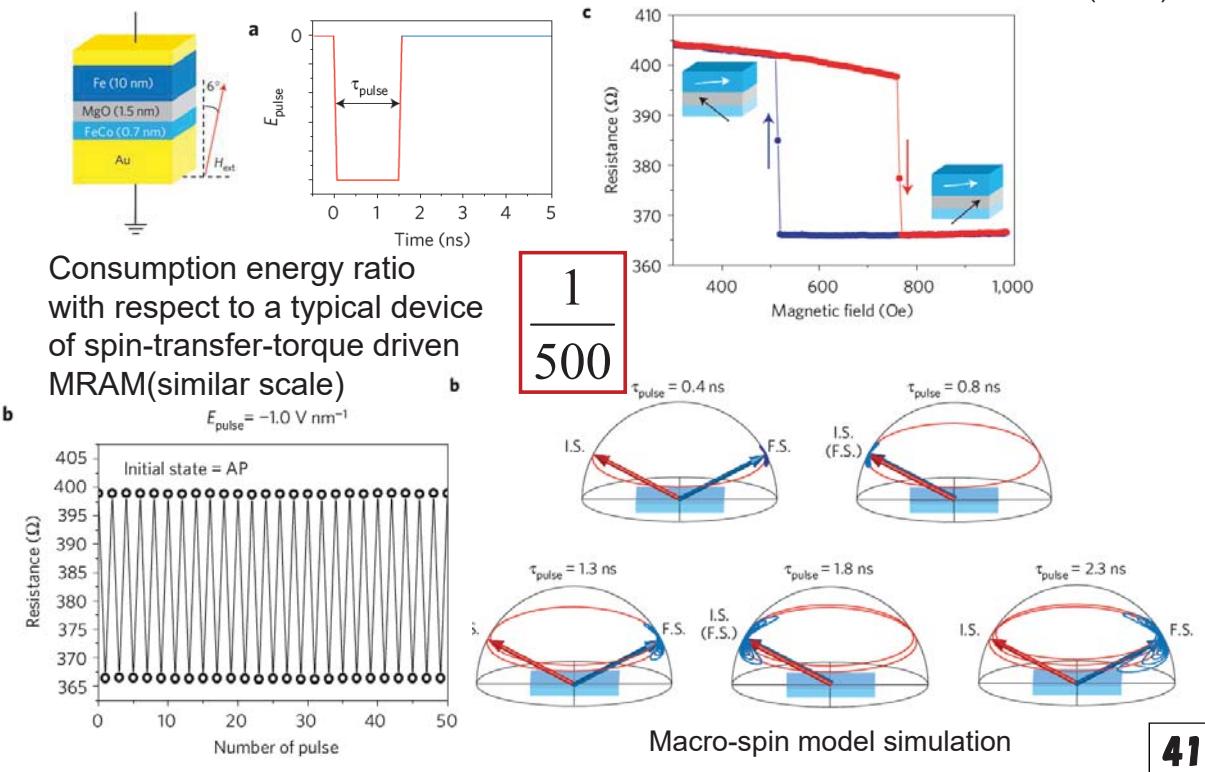


(5-11) Design on magnetic anisotropy in magnetic materials

Parameters for controlling MAE and its EF effect

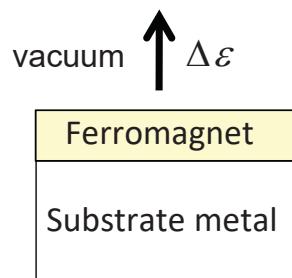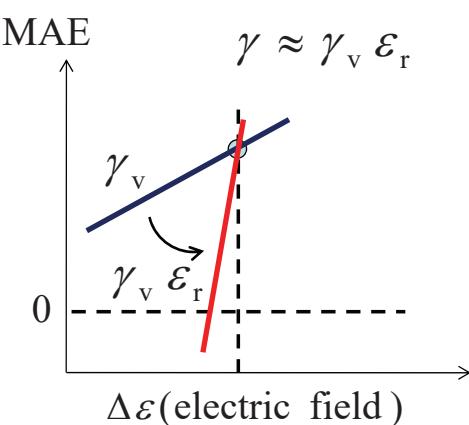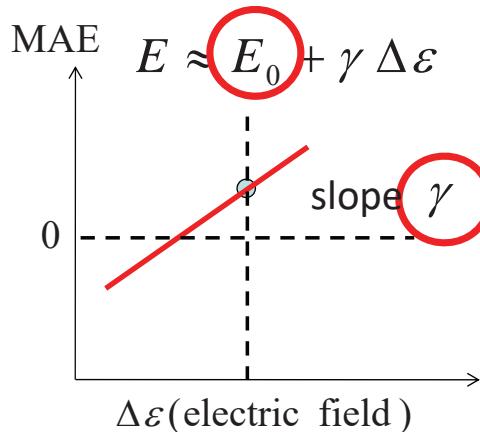

thickness
vicinity
effect

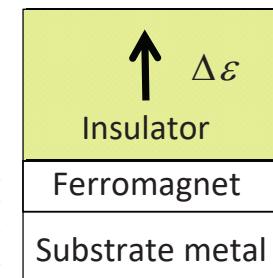

dielectric
constant

ε_r

42

Elements for controlling the MAE and EF variation in thin magnetic layers

Magnetic materials and interfaces.

Fe Fe/Pt Fe/Pd Fe/Au MgO/Fe Fe/Ni

MgO/FeCo MgO/Co₂FeAl (Huesler alloy)

Mn₃Ga Mn₃Ge

L1-0 MnGa: K. Z. Suzuki et al.,
Scientific Reports, 6, 30249 (2016).

Number of magnetic layers, layer-stacking alignment, etc.

(Fe_n/Ni_m)_ℓ

Ref.) K. Hotta et al., Phys. Rev. Lett., **110**, 267206 (2013).

Insulating materials: larger dielectric constant : ϵ_r

insulator/Fe

$\epsilon_r(\text{MgO}) = 9.8 \approx 10$

Magnetic interaction with neighboring layers.

Exchange bias between ferro- and antiferr-magnets.

43

Threshold to magnetic anisotropy transition

Films	E_b (mJ/m ²)	E_s (mJ/m ²)	$E_b + E_s$ (mJ/m ²)	MAE slope γ (fJ/Vm)	spin rotation EF (V/nm)
MgO/Fe/Pd(001)	0.36	-0.34	0.02	130	-0.2
MgO/Fe/Pt(001)	-1.18	-0.32	-1.50	615	2.4
MgO/Fe/Au(001)	0.96	-0.25	0.71	18	-40.2
MgO/Fe(2ML)/Au(001)	2.11	-0.57	1.54	-114	13.5
MgO/Pd/Fe/Au(001)	-0.68	-0.28	-0.96	-388	-2.5
MgO/Pt/Fe/Au(001)	1.52	-0.28	1.24	846	-1.5
MgO/Au/Fe/Au(001)	2.06	-0.26	1.80	-196	9.2
MgO/Pt/Fe(3ML)/Au(001)	0.69	-1.17	-0.48	633	0.8

$$\text{MAE } (\varepsilon) \approx E_b + E_s + \gamma \Delta \varepsilon$$

$$\varepsilon_c = - (E_b + E_s) / \gamma$$

Summary

- (5-1) Electronics structure: DOS
- (5-2) Magnetic moment: spin, orbital, localized and itinerant, spin-texture
- (5-3) Zeeman energy
- (5-4) Distance and interaction between magnetic carriers, magnetic and crystal structures
- (5-5) Spin-orbit interaction, electric field effects
- (5-6) Spin transfer Torque
- (5-7) Magnetic anisotropy energy: electron orbital, magnet shape
- (5-8) Magnetic anisotropy: in-plane, perpendicular
- (5-9) Voltage-induced spin torque
- (5-10) Landau–Lifshitz–Gilbert equation
- (5-11) Design on magnetic anisotropy in magnetic materials

45

(Appendix 1)
Imposing the electric field
perpendicular to
surface/interface

46

A1-1. Imposing electric field

ESM (effective screening medium) method
(M.Otani and O.Sugino,Phys.Rev.B**73**,115407,2006)

Energy functional

$$E[n_e, V] = K[n_e] + E_{xc}[n_e] - \int d\vec{r} \frac{\epsilon(\vec{r})}{8\pi} |\nabla V(\vec{r})|^2 + \int d\vec{r} [n_e(\vec{r}) + n_I(\vec{r})] V(\vec{r})$$


variation with the static potential

variation with the orbital

Poisson equation

$$\nabla \cdot [\epsilon(\vec{r}) \nabla] V(\vec{r}) = -4\pi n_{tot}(\vec{r})$$


$$\nabla \cdot [\epsilon(\vec{r}) \nabla] G(\vec{r}) = -4\pi \delta(\vec{r} - \vec{r}')$$

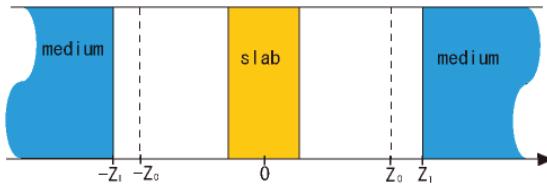

$$V(r) = \int d\vec{r}' G(\vec{r}, \vec{r}') n_{tot}(\vec{r}')$$

Kohn-Sham equation

$$\left[-\frac{1}{2} \nabla^2 + V(\vec{r}) + \hat{V}_{NL} + V_{xc}(\vec{r}) \right] \phi_\alpha(\vec{r}) = \epsilon_\alpha \phi_\alpha(\vec{r})$$

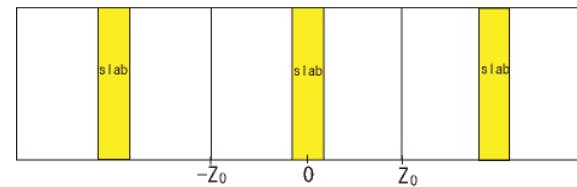

periodic boundary condition

Total energy representation by the Green's function

$$E[n_e] = K[n_e] + E_{xc}[n_e] + \frac{1}{2} \iint d\vec{r} d\vec{r}' n_e(\vec{r}) G(\vec{r}, \vec{r}') n_e(\vec{r}')$$

$$+ \iint d\vec{r} d\vec{r}' n_e(\vec{r}) G(\vec{r}, \vec{r}') n_I(\vec{r}') + \frac{1}{2} \iint n_I(\vec{r}) G(\vec{r}, \vec{r}') n_I(\vec{r}')$$

47

A1-2.

Usual first-principles approach
Electrostatic potential (solution of
Poisson's equation) ;

$$V_H(\vec{r}) = \int G(\vec{r}, \vec{r}') n(\vec{r}') d\vec{r}'$$


$$G(\vec{r}, \vec{r}') = \frac{1}{|\vec{r} - \vec{r}'|}$$

In practical, the above is calculated with
the Fourier transformation

$$V_H(\vec{r}) = \sum_{\vec{g}(\neq 0)} \frac{4\pi}{\vec{g}^2} n(\vec{G}) e^{i\vec{g} \cdot \vec{r}}$$

This procedure can not be applied for
the system on which the electric field is
imposed because of the breaking for the
periodic boundary condition.

Imposing the electric field
on a slab

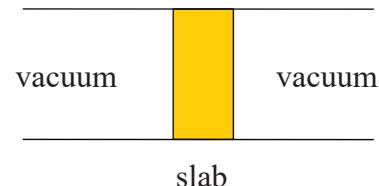


$$G(\vec{g}_\parallel, z, z') = \frac{4\pi}{2g_\parallel} e^{-g_\parallel |z-z'|}$$

$$V_H(\vec{g}_\parallel, z) = \int_{z_1}^{z_2} dz' G(\vec{g}_\parallel, z, z') \tilde{n}(\vec{g}_\parallel, z')$$

For small g_\parallel

$$G(\vec{g}_\parallel, z, z') = \frac{4\pi}{2g_\parallel} - 2\pi |z - z'|$$

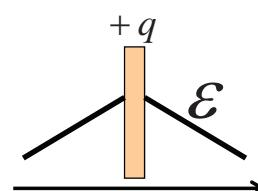

Green's function
for a charged sheet

48

A1-3. ESM method (when the electrode is placed at one side of the cell.)


(M.Otani and O.Sugino, Phys.Rev.B73,115407,2006)

$$\text{electrostatic potential } V(r) = \int d\vec{r}' G(\vec{r}, \vec{r}') n_{tot}(\vec{r}')$$


$$\text{boundary condition } \begin{cases} V_H(\mathbf{g}_{||}, z)|_{z=z_1} = 0 \\ \frac{\partial}{\partial z} V_H(\mathbf{g}_{||}, z)|_{z=-\infty} = 0 \end{cases} \quad \epsilon(z) = \begin{cases} 1 & \text{if } z \leq z_1 \\ \infty & \text{if } z \geq z_1 \end{cases}$$

$$G(\mathbf{g}_{||}, z, z') = \frac{4\pi}{2g_{||}} e^{-g_{||}|z-z'|} - \frac{4\pi}{2g_{||}} e^{-g_{||}(2z_1 - z - z')}$$

the contribution from mirror image charge

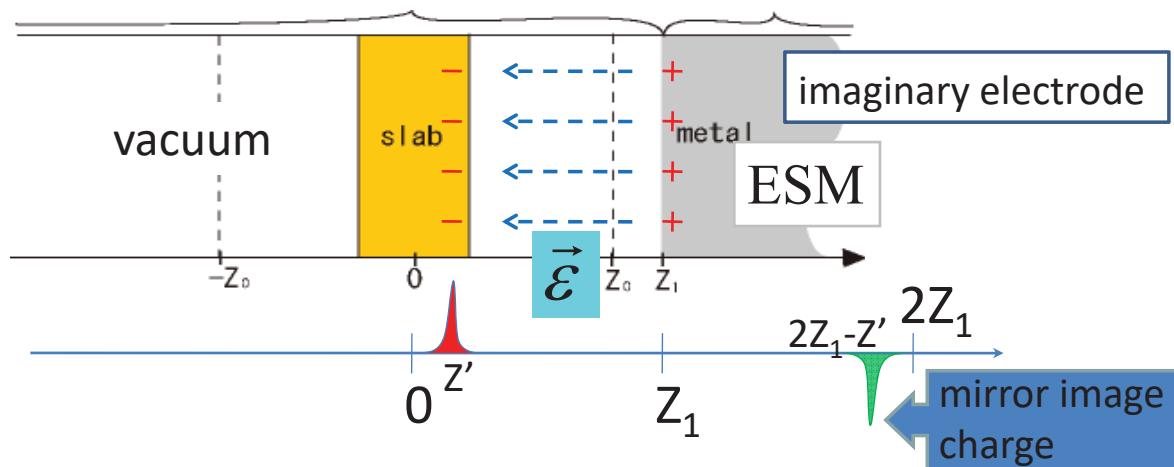


A1-4. Electric field induced in scanning tunnel microscope (STM)

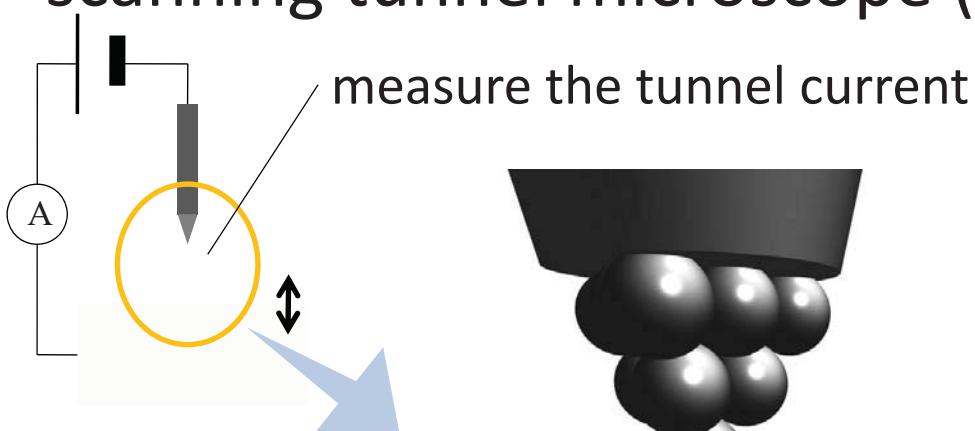

Scale of electric field


$$\approx 10^8 - 10^{10} \text{ V/m}$$

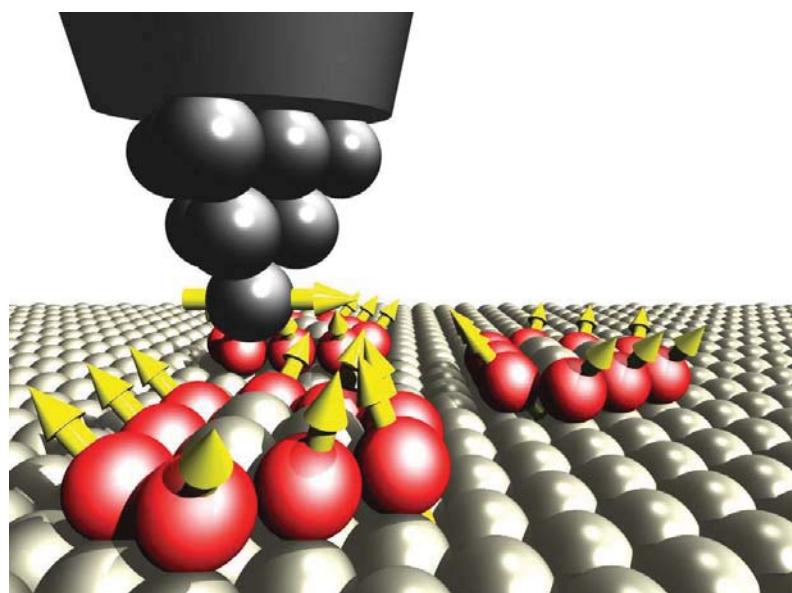

(Appendix 2)

Single spin-state valley in the surface states of Tl/Si(111) and Tl/Si(110)

51

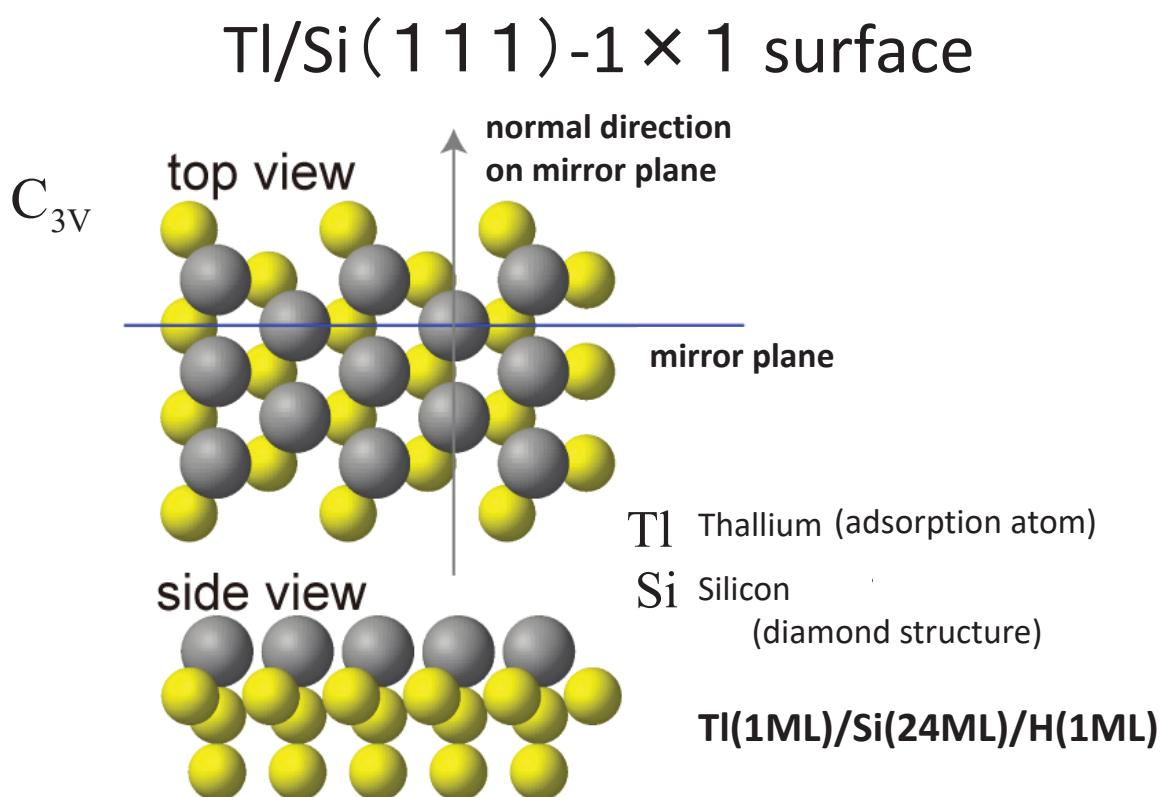

Full spin-orbit interaction other than the Rashba term

$$H_{SOI} = \frac{\hbar}{4m^2c^2} \vec{\sigma} \cdot (\text{grad } V(\vec{r}) \times \vec{p}) \quad \left(\varphi_{\vec{k}} | H_{SOI} | \varphi_{\vec{k}} \right)$$

$$(H_{SOI}) = \underbrace{\vec{\sigma} \cdot \{ \vec{\alpha}_n(\vec{k}) \times \vec{k} \}}_{\text{Rashba term}} + \underbrace{\vec{\sigma} \cdot \vec{B}_n(\vec{k})}_{\text{(Zeeman term)}}$$

$$\varphi_{nk}(\vec{r}) = \frac{1}{\sqrt{\Omega}} \exp(i\vec{k} \cdot \vec{r}) u_{nk}(\vec{r})$$


$$\vec{\alpha}_n = \frac{\hbar^2 N}{4m_e^2 c^2 \Omega} \int_{cell} d\vec{r} |u_{nk}(\vec{r})|^2 \vec{\nabla} V(\vec{r}) \quad \rightarrow \quad \vec{\alpha}_n = \alpha \vec{e}_z$$

$$\vec{B}_n(\vec{k}) \approx \frac{\hbar^2 N}{4m_e^2 c^2 \Omega} \int_{cell} d\vec{r} \frac{1}{r} \frac{dV}{dr} \{ u_{nk}^*(\vec{r})(\vec{\ell}) u_{nk}(\vec{r}) \}$$

Sakamoto, Oda, Kimura *et al.*, Phys.Rev. Lett., 102 (2009) 096805.




53

Surface band structure in Tl/Si(111)

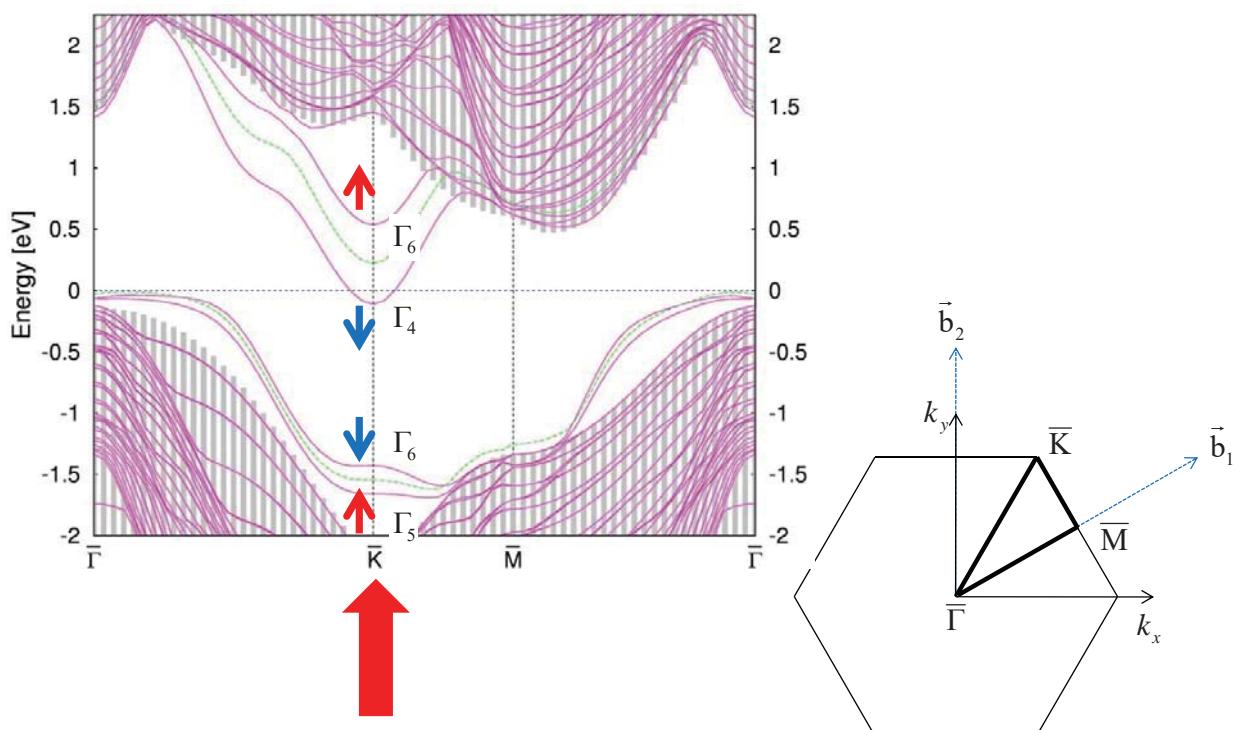


54


Spin splitting of Tl/Si(111) 1×1 surface band

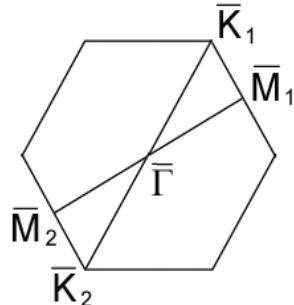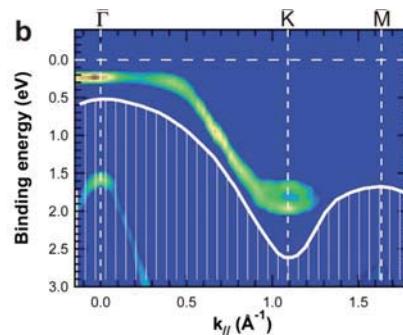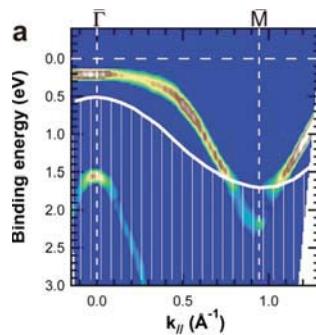

Clear splitting of electron levels in spin states at \bar{K}

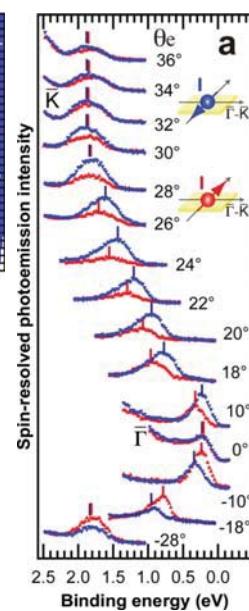

Spin splitting along Rashba direction

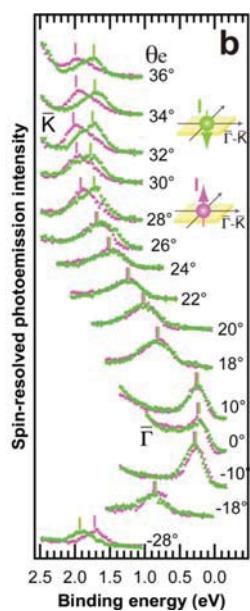


Normal to Rashba direction

Sakamoto, Oda, Kimura *et al.*, Phys.Rev. Lett., 102 (2009) 096805.


55

Wave vector dependence of spin direction : Voltical spin polarization

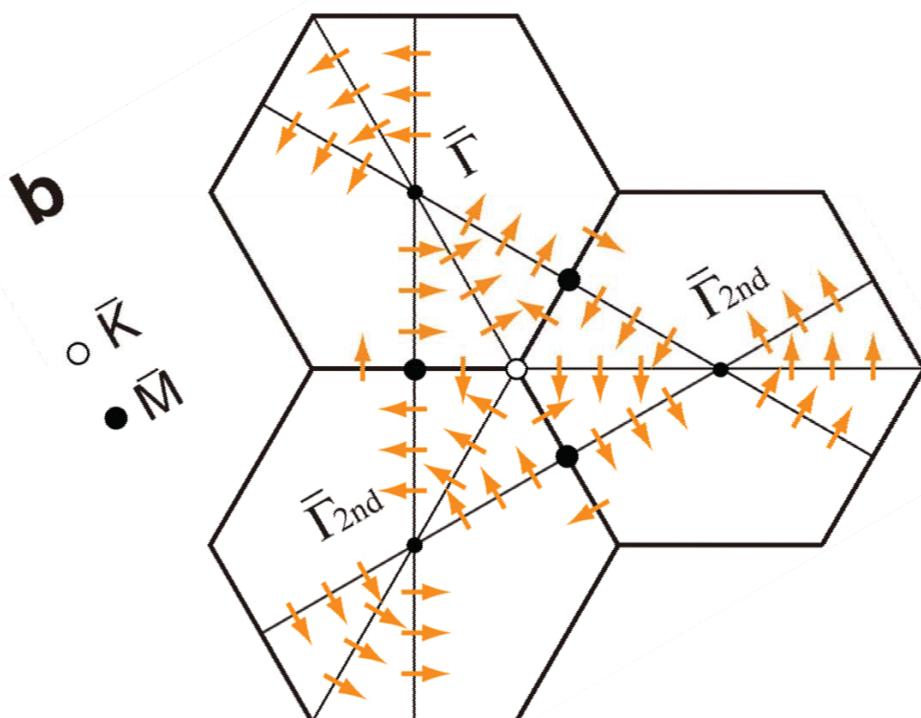

56

Wave vector dependence of electron spin direction : Tl site

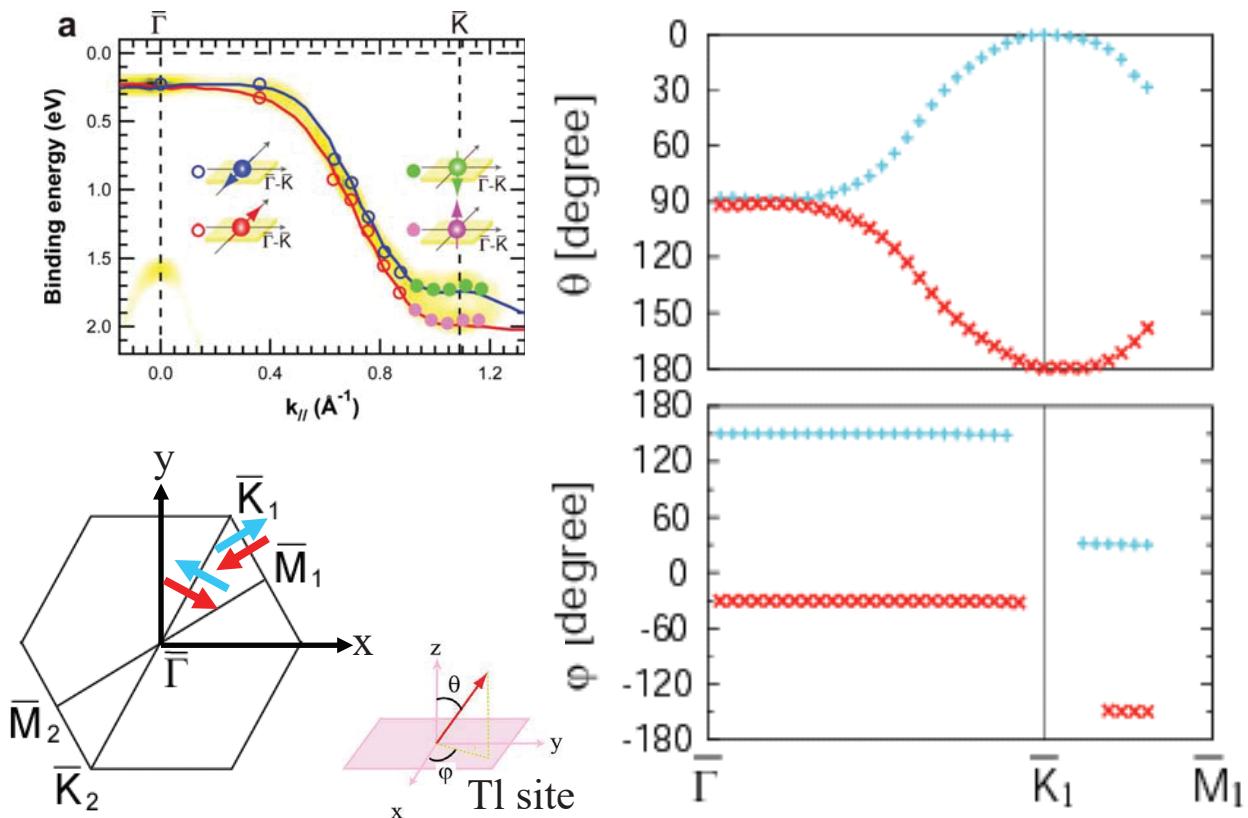

Atomic orbital components in the eigenstates at \bar{K}

\bar{K} point	$\langle \ell_z \rangle_{\text{Tl}}$	$\text{Tl}(p_x, p_y)$	(p_z)	$\text{Si}(1)(p_x, p_y)$	(p_z)	$\text{Si}(2)(p_x, p_y)$	(p_z)
Γ_6 -1.53eV	-0.047	$\downarrow 0.060$	---	---	$\downarrow 0.105$	$\downarrow 0.028$	---
Γ_5 -1.73eV	-0.068	$\uparrow 0.090$	$\downarrow 0.002$	---	$\uparrow 0.090$	$\uparrow 0.024$	$\downarrow 0.002$
C ₃ double group	$\langle \ell_z \rangle_{\text{Si}(2)} = -0.023$						

Good quantum state of ℓ_z


basis function of atomic orbital

Tl site, Si(2)

$$\Gamma_6 : \{(x+iy)\alpha, (x-iy)\beta\}$$

$$\Gamma_5 : \{(x-iy)\alpha, z\beta\}$$

$$\Gamma_4 : \{z\alpha, (x+iy)\beta\}$$




Si(1) site

$$\{(x-iy)\alpha, z\beta\}$$


$$\{z\alpha, (x+iy)\beta\}$$

$$\{(x+iy)\alpha, (x-iy)\beta\}$$

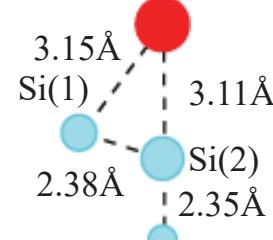


A. Araki, T. Nishijima,
M. Tsujikawa and TO,
J. Phys.: Conf. Ser.,
200 (2010) 062001.

Single spin-state valley with vertical spin direction

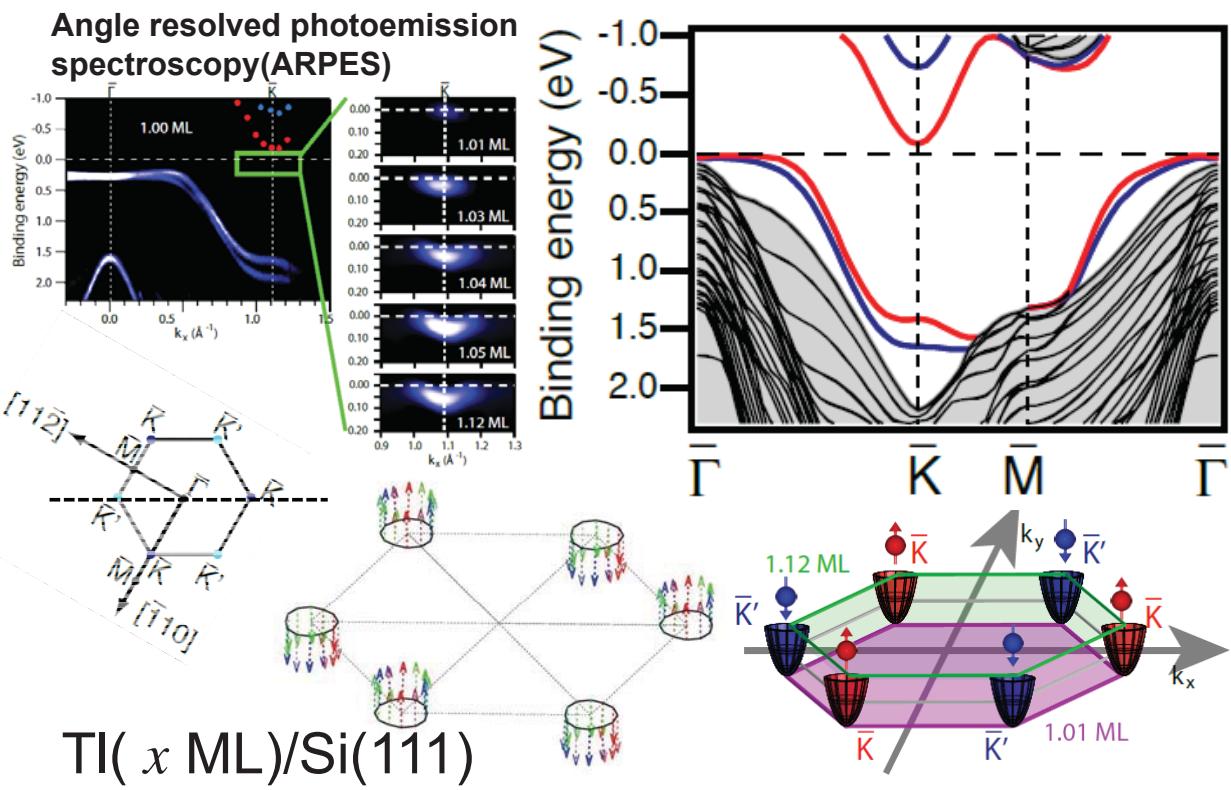





K. Sakamoto et al., Nat. Commun., 4, 2073, doi: 10.1038/ncomms3073, (2013)

Spin-splitting of the surface $\text{Ti}/\text{Si}(110)$

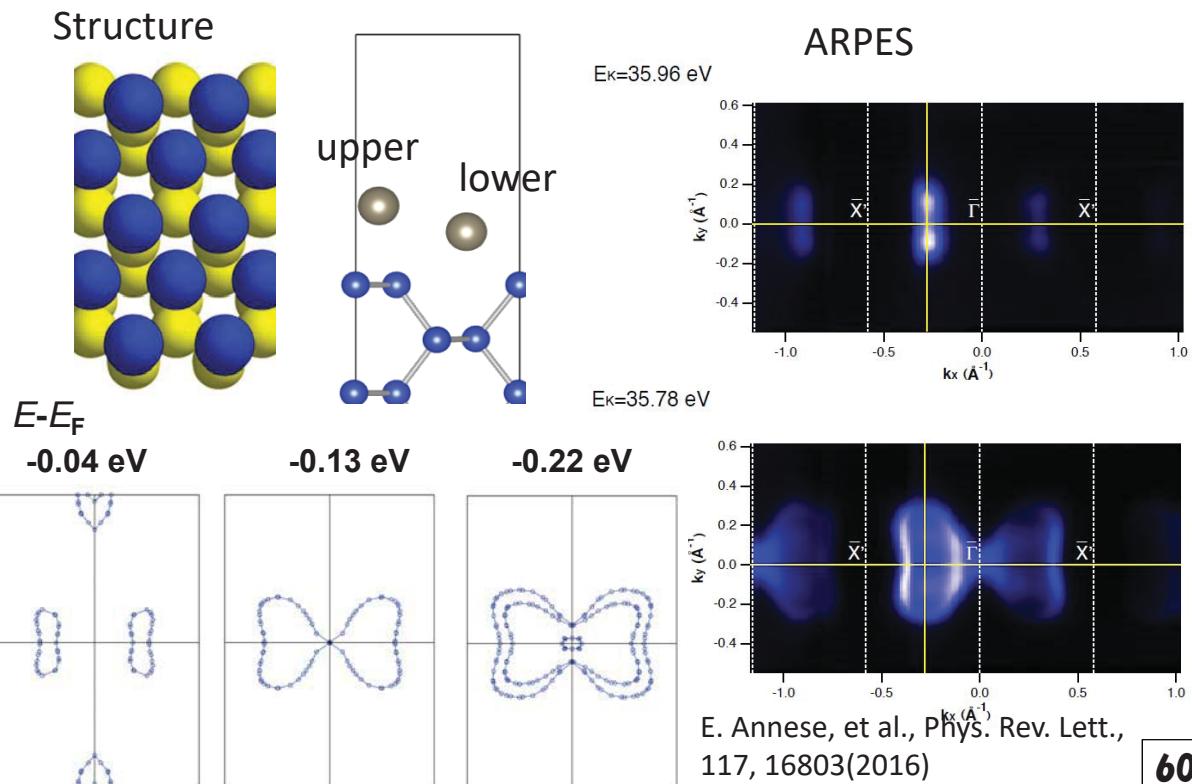


Band dispersion and Spin texture

Tl/Si(110)

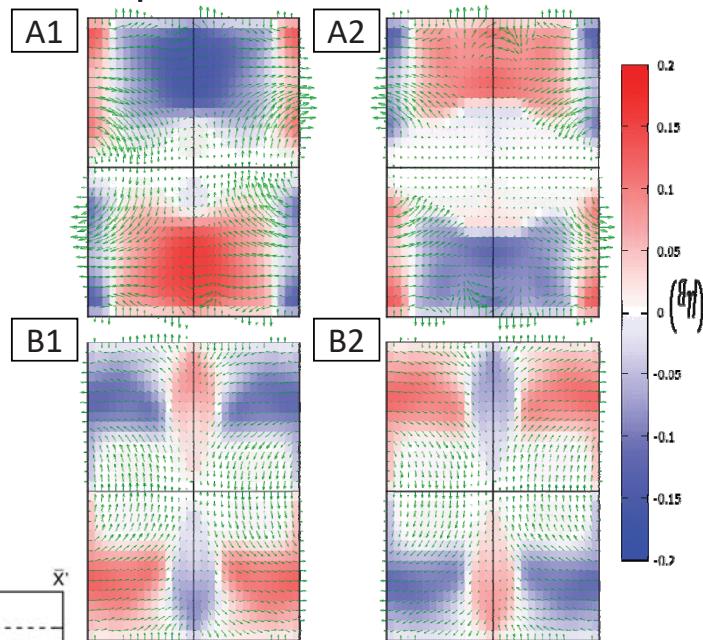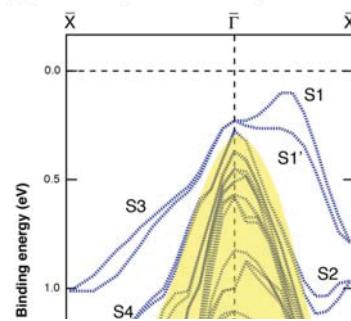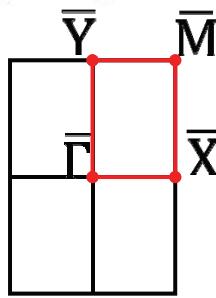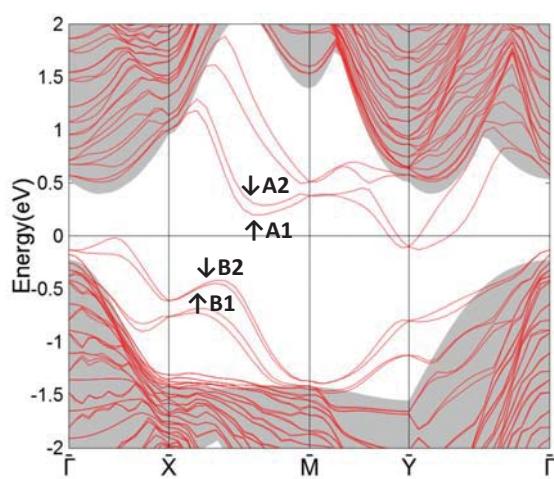


- The electron spins at

61

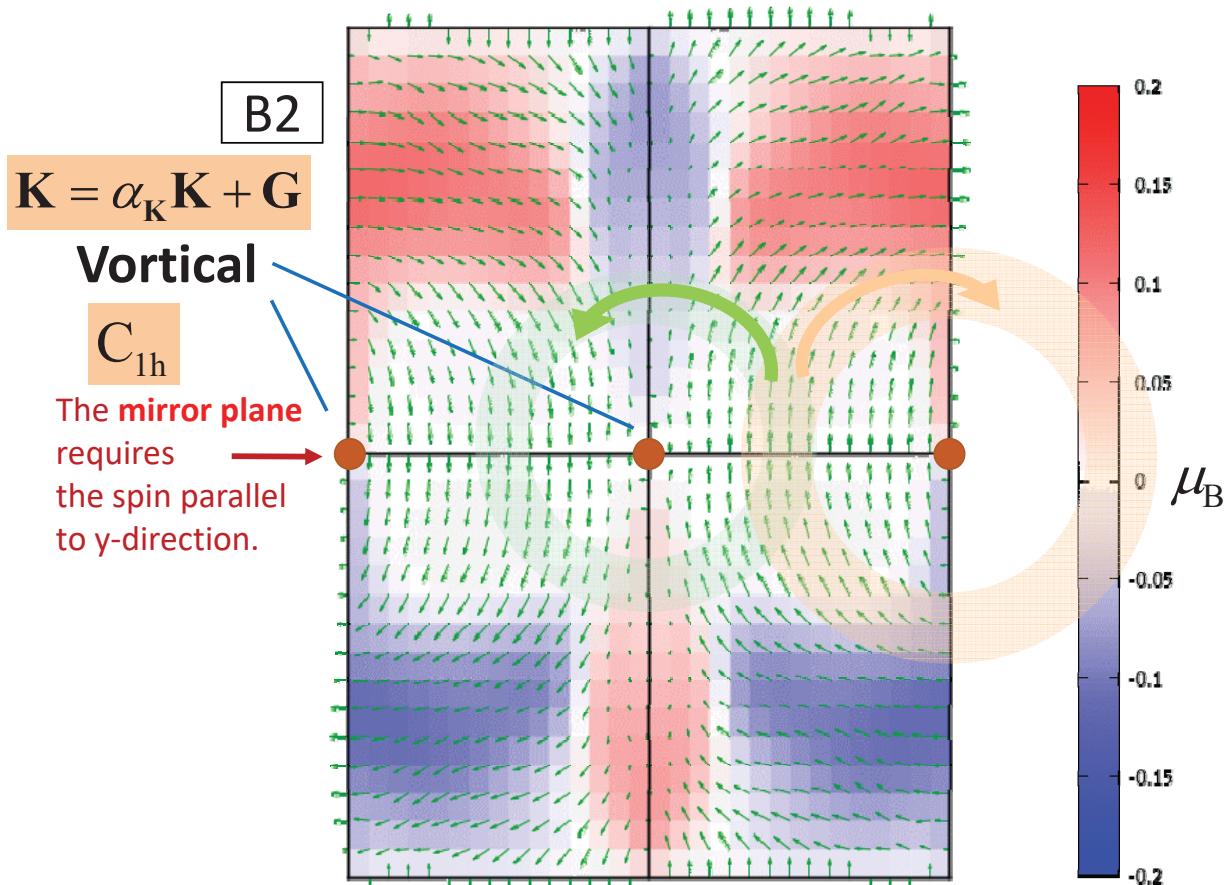

Discussion on group theory, see the paper, Nagano, Kodama, Shishido, Oguchi, JPCM, 2009.

Single spin-state valley with in-pane spin direction in TI/Si(110)

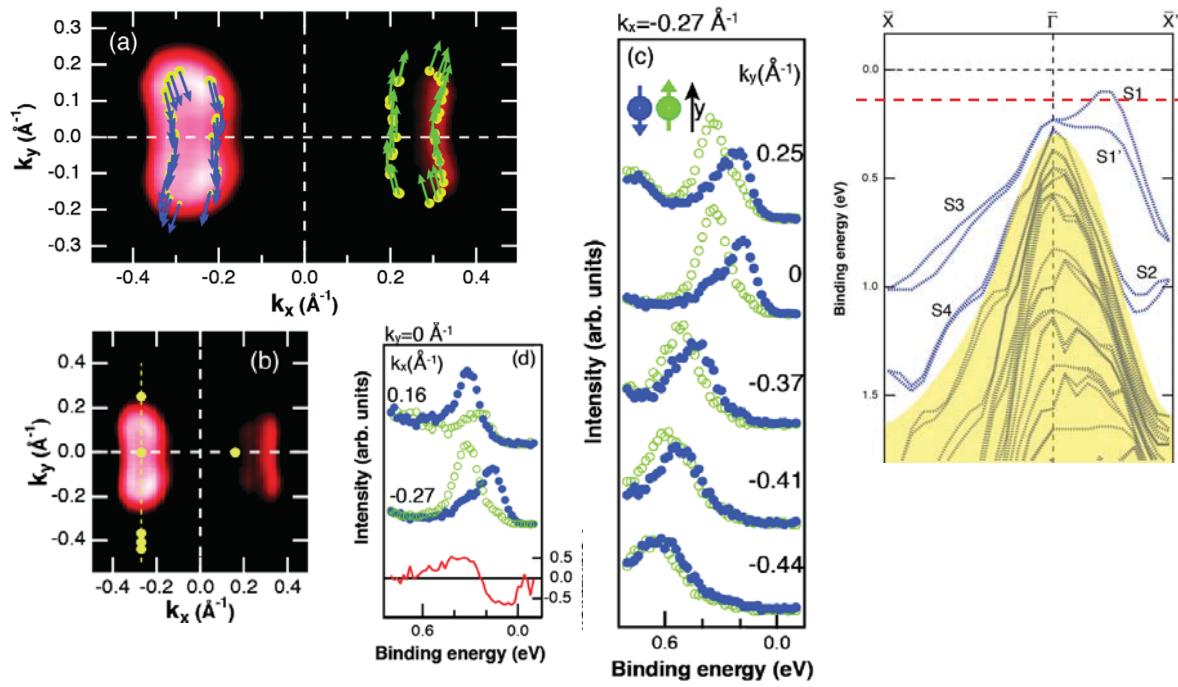

E. Annese et al., Phys. Rev. Lett., 117, 16803(2016)

63

(Appendix 3)
Spin and orbital magnetic
moments
in an electronic structure
calculation

64

Spin and orbital magnetic moments

spin magnetic moment

$$m_{\text{spin},k}^I = -\mu_B \langle m_k(\vec{r}) \rangle_I$$

orbital magnetic moment

$$m_{\text{orb},k}^I = -\mu_B \langle \ell_k \rangle_I$$

expansion with the local basis

$$\Psi_{i\alpha}(\vec{r}) = \sum_{\ell m} Y_{\ell m}(\hat{r}_I) R_{\ell m, i\alpha}(r)$$

$$\langle \ell_k \rangle_I = \langle \ell_k \rangle_{I,\text{PW}} + \langle \ell_k \rangle_{I,\text{VB}}$$

$$\langle \ell_k \rangle_{I,\text{PW}} = \sum_i f_i \langle \Psi_i | \ell_k | \Psi_i \rangle_I$$

$$\langle \ell_k \rangle_{I,\text{VB}} = \sum_{ipq} f_i \langle \Psi_i | \beta_q^I \rangle \ell_{k,pq}^I \langle \beta_p^I | \Psi_i \rangle$$

$$\ell_{k,pq}^I = \int_0^{r_c} \phi_p(r_I) \phi_q(r_I) r_I^2 dr_I \left\langle Y_{j_q \mu_q}^{\text{sgn}(\kappa_q)} \middle| \ell_k \middle| Y_{j_p \mu_p}^{\text{sgn}(\kappa_p)} \right\rangle$$

T. Oda and A. Hosokawa, Phys. Rev. B, 72, 224428 (2005)

Atomic magnetic moments in CoPt and FePt

$r_c = 2.5$ a.u.	spin (μ_B)				orbital(μ_B)		
		USPP	AE		USPP	AE	
CoPt [001]	Co	1.926	1.91	1.803	0.102	0.11	0.089
	Pt	0.377	0.38	0.394	0.061	0.07	0.056
CoPt [110]	Co	1.929		1.809	0.069		0.057
	Pt	0.377		0.398	0.078		0.073
FePt [001]	Fe	3.016	2.93	2.891	0.067	0.08	0.067
	Pt	0.338	0.33	0.353	0.046	0.05	0.042
FePt [110]	Fe	3.020		2.893	0.062		0.061
	Pt	0.340		0.355	0.059		0.055

AE: Sakuma,JPSJ(1994), Ravindran *et al.*,PRB(2001)

(Appendix 4)

Approximation in Dirac equation

67

Dirac equation (part 2)

(eq. in stationary-state)

$$p_0 = i\hbar \frac{\partial}{\partial(ct)} \rightarrow p_0 = \frac{\varepsilon}{c}$$

Coupled equations for the large and small components;

$$(\varepsilon - mc^2 + eA_0) \varphi_L = c \left(\vec{\sigma}, \vec{p} + \frac{e}{c} \vec{A} \right) \varphi_S$$

$$(\varepsilon + mc^2 + eA_0) \varphi_S = c \left(\vec{\sigma}, \vec{p} + \frac{e}{c} \vec{A} \right) \varphi_L$$

Eliminate the small component;

$$(\varepsilon - mc^2 + eA_0) \varphi_L = c^2 \underbrace{\left(\vec{\sigma}, \vec{p} + \frac{e}{c} \vec{A} \right)}$$

$$\underline{(\varepsilon + mc^2 + eA_0)^{-1}} \left(\vec{\sigma}, \vec{p} + \frac{e}{c} \vec{A} \right) \varphi_L$$

Commute the parts with underline:

68

Dirac equation (part 3)

$$(\varepsilon - mc^2 + eA_0) \phi_L = c^2 \underbrace{(\varepsilon + mc^2 + eA_0)^{-1}}_{+ c^2 (\varepsilon + mc^2 + eA_0)^{-2}} \left(\vec{\sigma}, \vec{p} + \frac{e}{c} \vec{A} \right)^2$$

$$+ c^2 \underbrace{(\varepsilon + mc^2 + eA_0)^{-2}}_{(\vec{\sigma}, (-e\vec{p}A_0))} \left(\vec{\sigma}, \vec{p} + \frac{e}{c} \vec{A} \right) \phi_L$$

For not heavy elements, the eigenvalue at valence electrons is larger than the rest energy by a small value. Therefore, we can take a following approximation;

$$\varepsilon' = \varepsilon - mc^2, \quad \frac{\varepsilon' + eV_0}{mc^2} \ll 1 \quad \begin{aligned} \varepsilon + mc^2 + eV_0 \\ \approx 2mc^2 \end{aligned}$$

Using this approximation, the equation for the large component;

69

Formula 1

(\vec{a}, \vec{b}) : Scalar product

Using following general properties;

$$(\vec{\sigma}, \vec{B})(\vec{\sigma}, \vec{C}) = (\vec{B}, \vec{C}) + i(\vec{\sigma}, \vec{B} \times \vec{C})$$

$$\vec{H} = \vec{\nabla} \times \vec{A}$$

We obtain the following formula related with Zeeman' term;

$$\left(\vec{\sigma}, \vec{p} + \frac{e}{c} \vec{A} \right)^2 = \left(\vec{p} + \frac{e}{c} \vec{A} \right)^2 + \frac{\hbar e}{c} (\vec{\sigma}, \vec{H})$$

$$(\vec{\sigma}, (-e\vec{p}A_0)) \left(\vec{\sigma}, \vec{p} + \frac{e}{c} \vec{A} \right) = \left((-e\vec{p}A_0), \vec{p} + \frac{e}{c} \vec{A} \right) + i \left(\vec{\sigma}, (-e\vec{p}A_0) \times \left(\vec{p} + \frac{e}{c} \vec{A} \right) \right)$$

$$= \left((-e\vec{p}A_0), \vec{p} + \frac{e}{c} \vec{A} \right) + \left(i \vec{\sigma} \times (-e\vec{p}A_0), \vec{p} + \frac{e}{c} \vec{A} \right)$$

$$c^2 (\varepsilon + mc^2 + eA_0)^{-1} = \frac{1}{2m} \left(1 + \frac{\varepsilon' + eA_0}{2mc^2} \right)^{-1} = \frac{1}{2m} \left(1 - \frac{\varepsilon' + eA_0}{2mc^2} + \dots \right)$$

$$c^2 (\varepsilon + mc^2 + eA_0)^{-2} = \frac{1}{4m^2 c^2} \left(1 + \frac{\varepsilon' + eA_0}{2mc^2} \right)^{-2} = \frac{1}{4m^2 c^2} \left(1 - \frac{\varepsilon' + eA_0}{mc^2} + \dots \right)$$

Formula 2

$$(\varepsilon' + eA_0)\phi_L =$$
$$\left(1 - \frac{\varepsilon' + eA_0}{2mc^2} + \dots\right) \left\{ \frac{1}{2m} \left(\vec{p} + \frac{e}{c} \vec{A} \right)^2 + \frac{\hbar e}{2mc} (\vec{\sigma}, \vec{H}) \right\} \phi_L +$$
$$\left(1 - \frac{\varepsilon' + eA_0}{mc^2} + \dots\right) \times$$
$$\left\{ \frac{1}{4m^2 c^2} \left((-e\vec{p}A_0), \vec{p} + \frac{e}{c} \vec{A} \right) + \frac{1}{4m^2 c^2} \left(i\vec{\sigma} \times (-e\vec{p}A_0), \vec{p} + \frac{e}{c} \vec{A} \right) \right\} \phi_L$$

Taking the leading terms in the approximation;
the approximation formula in (5-3).

71

(Appendix 5)
Spin-orbit splitting in the heavy
element

72

$$E_{\text{SO}}^j = \lambda \vec{\ell} \cdot \vec{s} = \frac{\lambda}{2} \{ j(j+1) - s(s+1) - \ell(\ell+1) \}$$


$$\left. \begin{array}{l} s, s_z = s, s-1, \dots, -s \\ \ell, m = \ell, \ell-1, \dots, -\ell \end{array} \right\} j = \ell + s, \dots, |\ell - s|$$

$$s = \frac{1}{2}, \quad s_z = \frac{1}{2}, -\frac{1}{2}$$

$$\ell = 1 \rightarrow j = \frac{3}{2}, \frac{1}{2}$$

$$\ell = 2 \rightarrow j = \frac{5}{2}, \frac{3}{2}$$

$\lambda > 0$

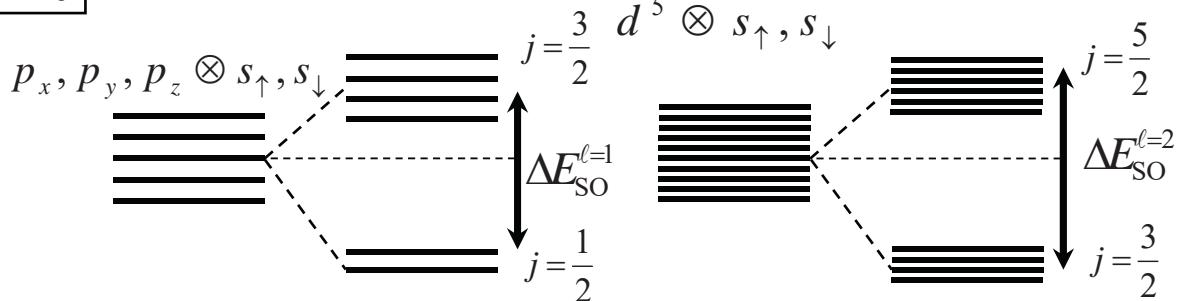

Eigenvalues of Pb atom

(in Ry energy unit)

Ref. State:
(Kr Core)(5d)¹⁰(6s)²(6p)²


$n\ell$	j	all electron	pseudo (ΔE)	$\Delta E_{\text{so}}(d)$
5d	3/2	-1.6734	-1.6733 (+0.0001)	0.1912
5d	5/2	-1.4823	-1.4821 (+0.0002)	2.601 eV
6s	1/2	-0.9016	-0.9014 (+0.0002)	
6p	1/2	-0.3547	-0.3545 (+0.0002)	$\Delta E_{\text{so}}(p)$
6p	3/2	-0.2440	-0.2439 (+0.0001)	0.1106 1.505 eV

These values are in good agreement with the previous data.

$$\Delta E_{\text{SO}}^\ell = E_{\text{SO}}^{\ell+1/2} - E_{\text{SO}}^{\ell-1/2} = \frac{\lambda}{2} (2\ell+1) \quad \lambda = \frac{2}{2\ell+1} \Delta E_{\text{SO}}^\ell \quad \lambda_{\ell=2}^{\text{Pb}} = 1.04 \text{ eV}$$


$$\lambda_{\ell=1}^{\text{Pb}} = 1.00 \text{ eV}$$

Band dispersion of fcc Pb

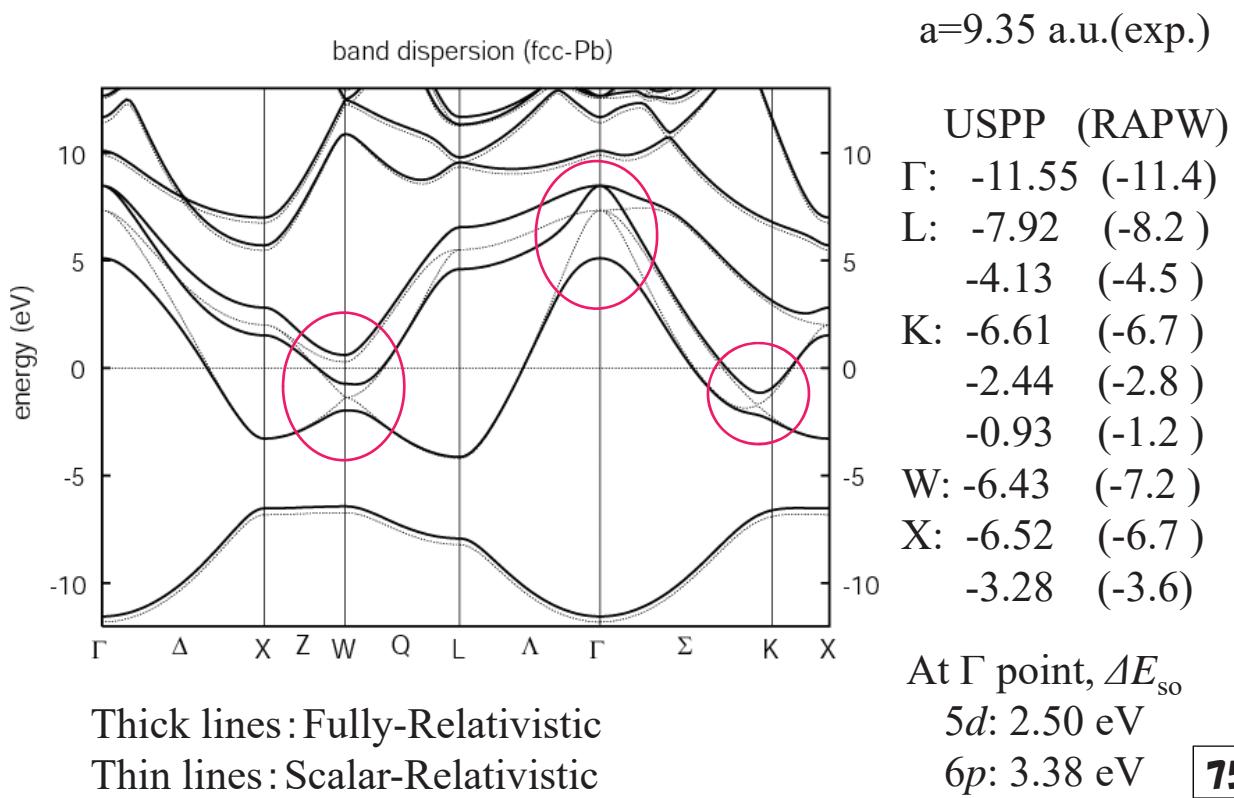


75

Band dispersion of fcc noble metals, Au

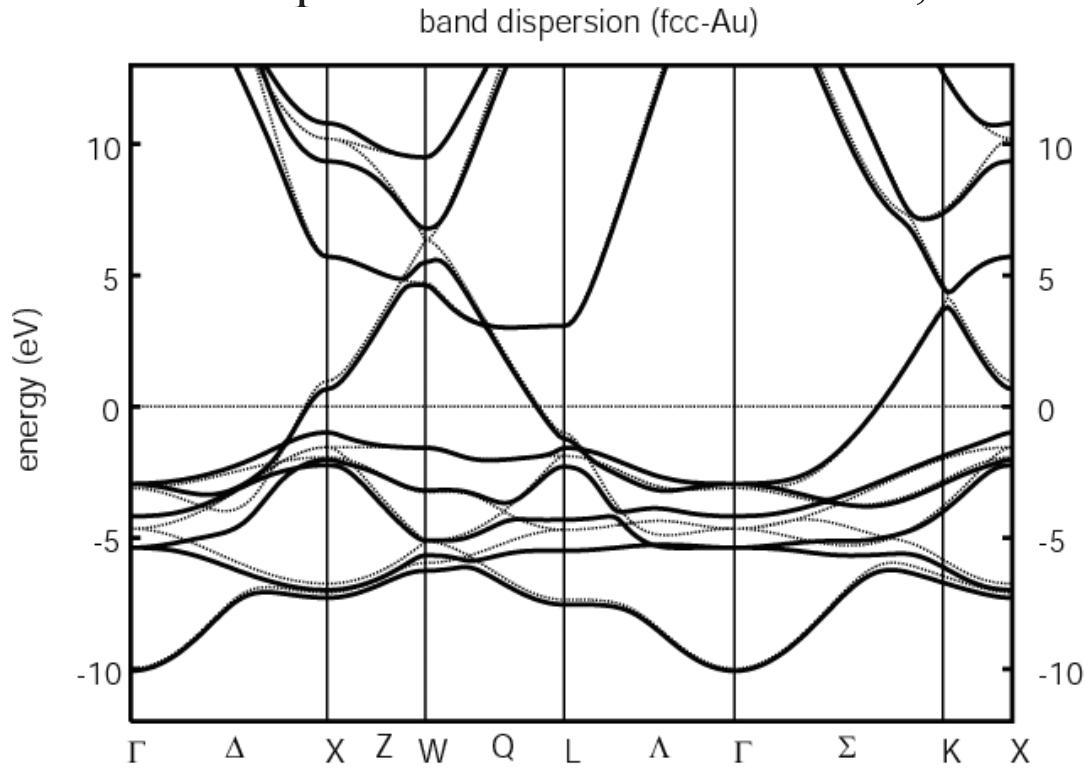

76

Band dispersion of fcc noble metals, Pt band dispersion (fcc-Pt)

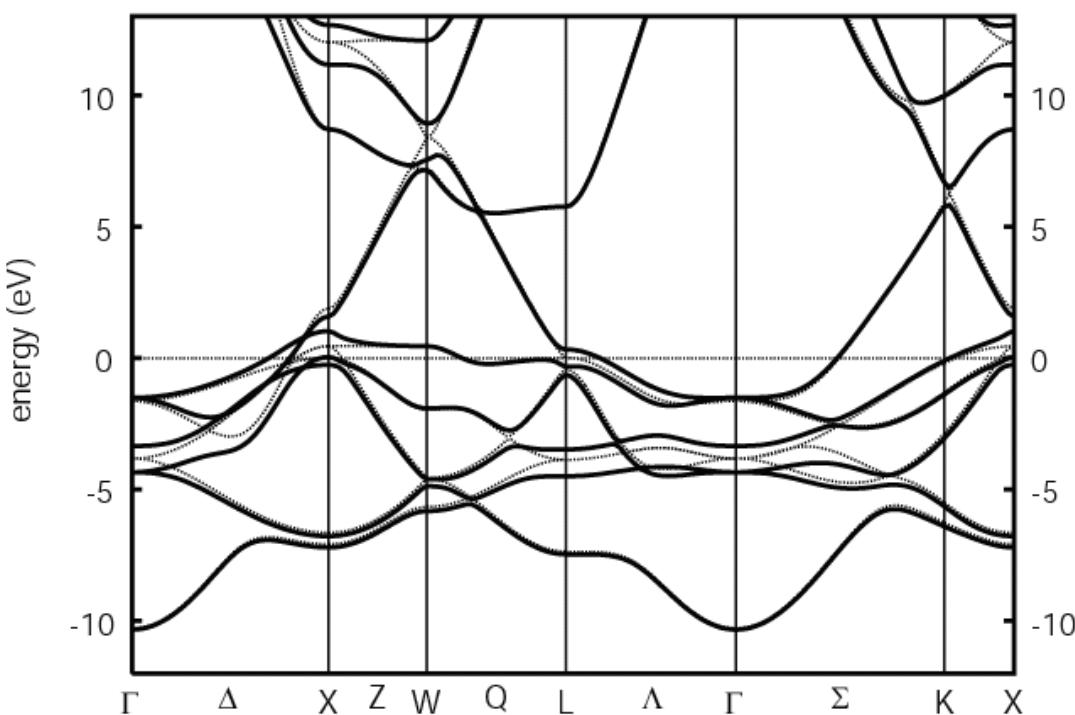

Pt: $a=7.41$ a.u.(exp.)

77

(Appendix 6)
Kohn-Sham equation,
variational principles,
Car-Parrinello molecular dynamics,
fully relativistic pseudo potential

78

Density functional theory: Kohn&Sham equation

Variational principles

$$\tilde{E}[n(\mathbf{r})] = E[n(\mathbf{r})] - \mu \left(\int n(\mathbf{r}) d\mathbf{r} - N_e \right)$$

$$\frac{\delta \tilde{E}}{\delta n(\mathbf{r})} = 0$$

Kohn&Sham equation → Electron density

$$\left\{ -\frac{1}{2} \nabla^2 + V_{\text{eff}}(\mathbf{r}) \right\} \Psi_i(\mathbf{r}) = \varepsilon_i \Psi_i(\mathbf{r}) \quad n(\mathbf{r}) = \sum_i^{\text{occ.}} |\Psi_i(\mathbf{r})|^2$$

Electron potential ← Poisson equation

$$V_{\text{eff}}(\mathbf{r}) = V_{\text{ext}}(\mathbf{r}) + \frac{1}{2} \int \frac{n(\mathbf{r}')}{|\mathbf{r} - \mathbf{r}'|} d\mathbf{r}' + \frac{\delta E_{\text{xc}}}{\delta n(\mathbf{r})}$$

79

Car-Parrinello Molecular Dynamics for Noncollinear Magnetism

- Bispinor Wave Functions for Single Electron States

$$\Phi_k(r) = \begin{pmatrix} \phi_{k1}(r) \\ \phi_{k2}(r) \end{pmatrix}$$

Soft part

Augmented part
(hard part)

- Density Matrix

$$\begin{aligned} \rho_{\alpha\beta}(r) &= \sum_k f_k \{ \phi_{k\alpha}(r) \phi_{k\beta}^*(r) + \sum_{lm} Q_{nm}^I(r) \langle \beta_n^I | \phi_{k\alpha} \rangle \langle \phi_{k\beta} | \beta_m^I \rangle \} \\ &= \frac{1}{2} (n(r) \sigma_0 + m_x(r) \sigma_x + m_y(r) \sigma_y + m_z(r) \sigma_z)_{\alpha\beta} \end{aligned}$$

unit matrix $\sigma_0 = \begin{pmatrix} 1 & 0 \\ 0 & 1 \end{pmatrix}$

Charge density $n(r)$
Spin density vector $m_\alpha(r)$

Pauli matrix $\sigma_x = \begin{pmatrix} 0 & 1 \\ 1 & 0 \end{pmatrix}$ $\sigma_y = \begin{pmatrix} 0 & -i \\ i & 0 \end{pmatrix}$ $\sigma_z = \begin{pmatrix} 1 & 0 \\ 0 & -1 \end{pmatrix}$

$$n(r) = \rho_{11} + \rho_{22}$$

$$m_x(r) = 2 \operatorname{Re} \rho_{12} \quad m_y(r) = -2 \operatorname{Im} \rho_{12} \quad m_z(r) = \rho_{11} - \rho_{22}$$

80

- Total Energy(Energy Functional)

$$E_{tot}[\{\Phi_k\}, \{R_I\}] = \sum_k f_k \langle \Phi_k | \left(-\frac{1}{2} \nabla^2 \sigma_0 + V_{NL} \right) | \Phi_k \rangle + \frac{1}{2} \iint \frac{n(r)n(r')}{|r-r'|} dr dr' \\ + \int V_{loc}^{ion}(r) n(r) dr + E_{XC}[n(r), m(r)] + U_{ion}[\{R_I\}]$$

$$V_{loc}^{ion}(r) = \sum_I V_{loc}^I(r - R) \quad V_{NL} = \left(\sum_{Inm} |\beta_m^I\rangle D_{nm}^{(0)I} \langle \beta_n^I| \right) \sigma_0$$

$$U_{ion}[\{R_I\}] = \frac{1}{2} \sum_{IJ} \frac{Z_I Z_J}{|R_I - R_J|} \quad m(r) = |\vec{m}(r)|$$

$$\beta_n^I(r) \quad D_{nm}^{(0)I} \quad Q_{nm}^I(r) \quad V_{loc}^I(r)$$

These quantities are transferred from an atomic reference configuration. The pseudo potential is the ultra-soft type.

- Density Functional for the Exchange-Correlation Term.
Local spin density approximation(LDA),
Generalized gradient approximation (GGA,PW91)
Van der Waals density functional (vdW-DF)

81

- Lagrangian (Car-Parrinello Molecular Dynamics)

$$L = m_\Phi \sum_k f_k \langle \dot{\Phi}_k | \dot{\Phi}_k \rangle + \frac{1}{2} \sum_I M_I \dot{R}_I^2 - E_{tot}[\{\Phi_k\}, \{R_I\}] \\ + \sum_{kl} \Lambda_{kl} (\langle \Phi_k | S | \Phi_l \rangle - \delta_{kl})$$

- Molecular Dynamics (Euler-Lagrange equation)

$$m_\Phi \ddot{\Phi}_k(r) = -H \Phi_k(r) + \sum_\ell \frac{1}{f_k} \Lambda_{kl} S \Phi_\ell(r) \\ \underline{\underline{M_I \ddot{R}_I = F_I + \sum_{kl} \Lambda_{kl} \langle \Phi_k | \frac{\partial S}{\partial R_I} | \Phi_\ell \rangle}}$$

$$H = \frac{1}{f_k} \frac{\delta E_{tot}}{\delta \Phi_k} \quad \begin{pmatrix} \bar{\phi}_{k1}(r) \\ \bar{\phi}_{k2}(r) \end{pmatrix} = - \begin{pmatrix} H11 & H12 \\ H21 & H22 \end{pmatrix} \begin{pmatrix} \phi_{k1}(r) \\ \phi_{k2}(r) \end{pmatrix}$$

$$F_I = -\frac{\partial E_{tot}}{\partial R_I}$$

R. Car and M. Parrinello, Phys. Rev. Lett. **55**, 2471 (1985).

Install to the plane wave method (I)

spinor wave function

$$\Phi_k(r) = \begin{pmatrix} \phi_{k1}(r) \\ \phi_{k2}(r) \end{pmatrix}$$

density matrix

$$\rho_{\alpha\beta}(r) = \sum_k f_k \{ \phi_{k\alpha}(r) \phi_{k\beta}^*(r) + \sum_{lpq} Q_{pq,\alpha\beta}^l(r) \langle \beta_p^l | \Phi_k \rangle \langle \Phi_k | \beta_q^l \rangle \}$$

spinor type projector function

$$\beta_p^I(r) = b_{j\kappa\tau}^I(r) Y_{j\mu}^{\text{sgn}(\kappa)}(r_I) \quad p = \{j\mu\kappa\tau\}$$

$$j = \ell + \frac{1}{2}, \mu = m + \frac{1}{2} \quad Y_{j,\mu}^{(-)} = \left(\frac{l+m+1}{2l+1} \right)^{1/2} Y_{l,m} \begin{pmatrix} 1 \\ 0 \end{pmatrix} + \left(\frac{l-m}{2l+1} \right)^{1/2} Y_{l,m+1} \begin{pmatrix} 0 \\ 1 \end{pmatrix}$$

$$j = \ell - \frac{1}{2}, \mu = m - \frac{1}{2} \quad Y_{j,\mu}^{(+)} = \left(\frac{l-m+1}{2l+1} \right)^{1/2} Y_{l,m-1} \begin{pmatrix} 1 \\ 0 \end{pmatrix} - \left(\frac{l+m}{2l+1} \right)^{1/2} Y_{l,m} \begin{pmatrix} 0 \\ 1 \end{pmatrix}$$

TO and A. Hosokawa, PRB, **72**, 224428 (2005)

Install to the plane wave method (II)

nonlocal potential

$$V_{NL} = \sum_{lpq} |\beta_q^l\rangle D_{pq}^{(0)I} \langle \beta_p^l|$$

transfer from the atomic generation code

$$\beta_p^I(r) \quad D_{pq}^{(0)I} \quad Q_{pq,\alpha\beta}^l(r) \quad V_{loc}^I(r)$$

Kohn-Sham equation

$$H \Phi_k(r) = \epsilon_k S \Phi_k(r)$$

$$H = \left(-\frac{1}{2} \nabla^2 \right) \sigma_0 + \bar{V}_{eff} + \sum_{lpq} |\beta_p^l\rangle D_{pq}^I \langle \beta_q^l| \quad S = 1 + \sum_{lpq} |\beta_q^l\rangle q_{pq}^I \langle \beta_p^l|$$

$$\bar{V}_{eff}(r) = \left(V_{loc}^{ion}(r) + \int \frac{n(r')}{|r-r'|} dr' + V_{xc}^N(r) \right) \sigma_0 + V_{xc}^M(r) \frac{1}{m(r)} \vec{m}(r) \cdot \vec{\sigma}$$

$$D_{pq}^I = D_{pq}^{(0)I} + \sum_{\alpha\beta} \int Q_{pq,\alpha\beta}^l(r) (V_{eff}(r))_{\alpha\beta} dr \quad V_{xc}^N(r) = \frac{\delta E_{xc}}{\delta n(r)} \quad V_{xc}^M(r) = \frac{\delta E_{xc}}{\delta m(r)}$$

TO and A. Hosokawa, PRB, **72**, 224428 (2005)

(Appendix 7)

Magnetic dipole-dipole interaction, Shape magnetic anisotropy energy

85

Shape Magnetic Anisotropy Energy (SMAE)

From magnetic dipole interaction(MDI)

$$\text{SMAE} = E_{\text{MDI}}^{[001]} - E_{\text{MDI}}^{[100]}$$

Continuum approach (CA)

M : Total magnetization

$$\text{MAE} = E_{\text{MDI}}^{[001]} - E_{\text{MDI}}^{[100]} = \frac{1}{2} \mu_0 \frac{M^2}{\Omega}$$

Ω : Volume of magnetic material
 μ_0 : Permeability of vacuum

Discrete approach (DA) [1,2]

$\mathbf{m}(\mathbf{R}_i)$: Atomic magnetic moment

$$E_{\text{MDI}}^{\mathbf{m}} = \frac{e^2}{4m^2c^2} \sum_{\mathbf{R}_i, \mathbf{R}_j}^{i \neq j} \left[\frac{\mathbf{m}(\mathbf{R}_i) \cdot \mathbf{m}(\mathbf{R}_j)}{R_{ij}^3} - 3 \frac{\mathbf{m}(\mathbf{R}_i) \cdot (\mathbf{R}_i - \mathbf{R}_j) \mathbf{m}(\mathbf{R}_i) \cdot (\mathbf{R}_i - \mathbf{R}_j)}{R_{ij}^5} \right]$$

Spin density approach (SDA) [3]

$$E_{\text{MDI}}^{\mathbf{m}} = \frac{e^2}{4m^2c^2} \iint d\mathbf{r}_1 d\mathbf{r}_2 \left[\frac{\mathbf{m}(\mathbf{r}_1) \cdot \mathbf{m}(\mathbf{r}_2)}{|\mathbf{r}_1 - \mathbf{r}_2|^3} - 3 \frac{\mathbf{m}(\mathbf{r}_1) \cdot (\mathbf{r}_1 - \mathbf{r}_2) \mathbf{m}(\mathbf{r}_2) \cdot (\mathbf{r}_1 - \mathbf{r}_2)}{|\mathbf{r}_1 - \mathbf{r}_2|^5} \right]$$

➤ High precision shape magnetic anisotropy from spin density distribution: magnetic interface/surface

[1] H. J. G. Draaisma and W. J. M. de Jonge, J. Appl. Phys. 64, 1988.




[2] L. Szunyogh et al, Phys. Rev. B 51, 9552, 1995.

[3] T. Oda and M. Obata, J. Phys. Soc. Jpn. 87, 064803, 2018.

86

Quadrupole atomic spin density distribution at interface/surface

MgO(5ML)/Fe(xML)/MgO(5ML)-lcMgO(1x1)

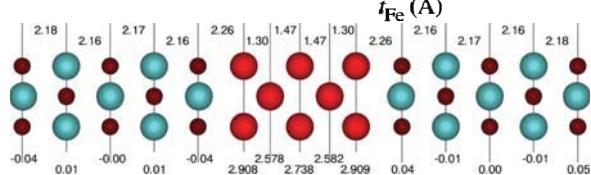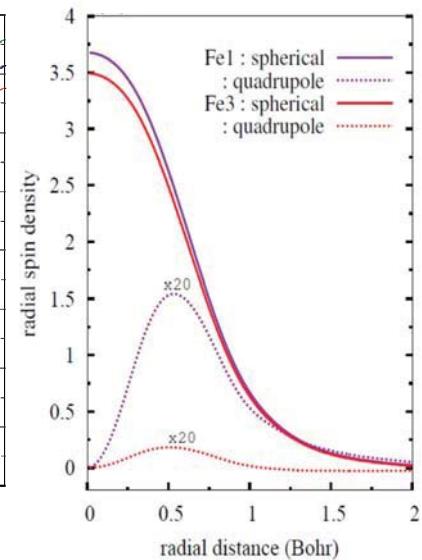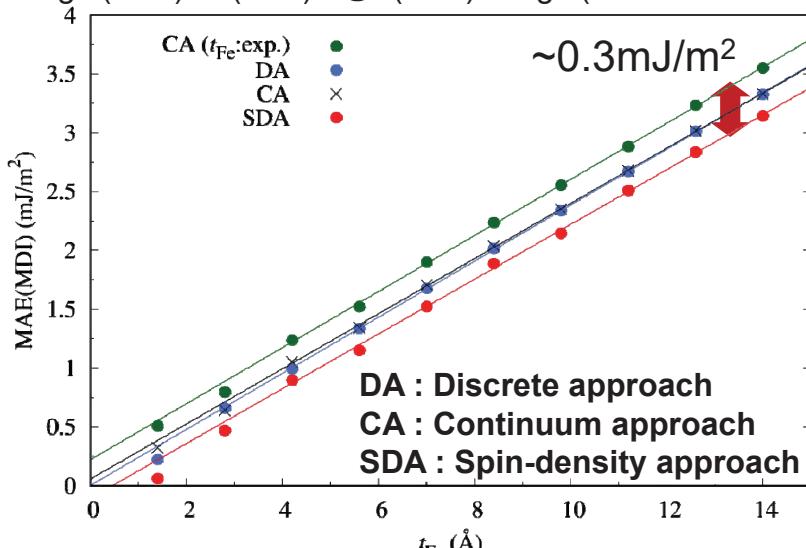

TO, I. Pardede, et al., IEEE Trans. Magn. 55, 1300104 (2018).